

NASA Contractor Report 175073

## High Temperature Dispersion Strengthening of NiAl


{(NASA-CR-175073) HIGH TEMPERATURE  
DISPERSION STRENGTHENING OF NiAl Final  
Report (Case Western Reserve Univ.) 15 p  
HC A02/MF A01 CSCL 11F

N86-22688

Unclas  
G3/26 05918

Mark Sherman and Krishna Vedula  
*Case Western Reserve University  
Cleveland, Ohio*

March 1986

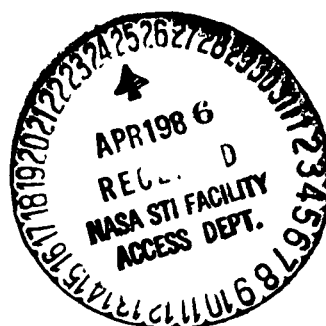

Prepared for  
Lewis Research Center  
Under Grant NAG 3-387

# HIGH TEMPERATURE DISPERSION STRENGTHENING OF NiAl

Mark Sherman

Sohio Research Center, Cleveland, Ohio

Krishna Vedula

Department of Metallurgy and Materials Science,  
Case Western Reserve University, Cleveland, Ohio

## SUMMARY

A potential high temperature strengthening mechanism for alloys based on the intermetallic compound NiAl has been investigated. This study forms part of an overall program at NASA Lewis Research Center for exploring the potential of alloys based on NiAl for high temperature applications. An alloy containing 2.26 at% Nb and produced by hot extrusion of blended powders has been examined in detail using optical and electron microscopy. Interdiffusion between the blended Nb and NiAl powders results in the formation of intermediate phases. A fine dispersion of precipitates of a hexagonal, ordered NiAlNb phase in a matrix of NiAl can be produced and this results in strengthening of the alloy by interfering with dislocation motion at high temperature. These precipitates are, however, found to coarsen during the high temperature (1300 K) deformation at slow strain rates and this may impose some limitations on the use of this strengthening mechanism.

## 1. INTRODUCTION

Ordered intermetallics have long been recognized as candidates for high temperature applications because thermally activated processes such as diffusion are inhibited by the ordered crystal structure. Recently, interest has been generated in developing certain intermetallic compounds for high temperature applications [1-4]. The ordered intermetallic NiAl is especially attractive since this compound offers oxidation and corrosion resistance, remains ordered up to its high congruent melting point of 1913 K, and has a density advantage over conventional superalloys because of its high aluminum content.

The drawbacks of NiAl, however, are its room temperature brittleness and its inadequate creep resistance at high temperatures, in spite of its ordered crystal structure. In this paper, we are concerned only with its high temperature mechanical properties. Previous work [5] has shown that the high temperature creep resistance of NiAl can be improved to levels comparable with those of some superalloys by macroalloying with ternary additions, using a powder metallurgy process. The powder metallurgy process involves blending of elemental ternary additions with binary NiAl followed by hot extrusion in a sealed steel container. Additions of Nb, Ta and Hf at the 2 at% level, in particular, have shown the most promise. The reasons for this improvement in high temperature creep resistance are, nevertheless, not clear.

The purpose of this study was to understand the interaction between the Nb powder and the NiAl powder during the powder metallurgy processing of an alloy containing 2.26 at% Nb and to identify the mechanism of high temperature strengthening in this alloy. This alloy has been microscopically examined before and after high temperature deformation in order to obtain this understanding.

## 2. MATERIALS AND PROCEDURE

The alloy was prepared at NASA Lewis Research Center by blending approximately 2 at% of -325 mesh commercially pure Nb powder, with -80 mesh prealloyed NiAl powder. The fine Nb powder was used in order to enhance interdiffusion between the matrix NiAl and the ternary addition. The powder blend was filled in a mild steel can (5 cm. dia. and 12.5 cm. long) which was evacuated and sealed. The sealed can was preheated to a temperature of 1366 K and extruded through a vertical die at an area reduction ratio of 16:1. The extruded can was air cooled and the steel can was then removed by grinding. The alloy specimens were subsequently homogenized at 1523 K in argon for 175 hours to ensure maximum interdiffusion between the ternary addition and the matrix NiAl. Spectrographic analysis of the as-homogenized alloy showed the alloy to have a nominal chemical composition of 50.19 at% Ni, 47.58 at% Al and 2.26 at% Nb.

Cross-sections of the as-extruded and as-homogenized specimens were examined using optical and scanning electron microscopy. Cylindrical specimens (5 mm. dia. and 10 mm. long) of the as-homogenized material were prepared by centreless grinding. Specimens were tested (at NASA Lewis Research Center) in compression on an Instron Testing machine at a temperature of 1300 K or 0.68  $T_m$  and at slow strain rates. The specimen tested at an initial strain rate of  $3 \times 10^{-3}$  /sec to a final strain of about 7% was examined in considerable detail using optical and scanning electron microscopy.

Transmission electron microscopy of the specimens before and after compression testing was used to identify the second phases and to examine the substructure of the specimens in order to understand the strengthening mechanism. Thin foils for TEM were prepared by electropolishing in a 2:1 methanol / nitric acid solution cooled to 253 K.

## 3. RESULTS AND DISCUSSION

### (A) AS-EXTRUDED AND AS-HOMOGENIZED SPECIMENS

The as-extruded microstructure (illustrated in Figure 1a) contains recrystallized NiAl grains with very little porosity. The second phase particles observed are the undissolved Nb particles which have a wide range of sizes, the average size being roughly 4 micrometers.

The as-homogenized microstructure (illustrated in Figure 1b) shows a well developed grain structure with an average grain size of about 25 micrometers which is somewhat larger than the as-extruded grain size. A slight increase in the amount of porosity is observed and is suspected to be

due to pull out of particles during specimen preparation. The average size of the second phase particles has increased by about 50% to roughly 5.5 micrometers. The increase in size of the second phase particles, which were originally Nb powder particles, is believed to be a result of transformation of the Nb to a ternary intermetallic of Ni, Al and Nb by interdiffusion.

The distribution of the second phase particles is clearly observed in the scanning electron micrograph in Figure 2a. Some of the larger particles reveal the presence of two phases, one surrounding the other, as illustrated in Figure 2b. Energy Dispersive Analysis of X-Rays from the two regions shows that the inner phase contains more Nb than the outer phase and the compositions of the phases correspond in general to the phases  $\text{NiAlNb}_2$  and  $\text{NiAlNb}$  respectively (Figure 3). A more definite confirmation of their compositions could not be made since standards were not used for the analyses. These two phases are in agreement with an earlier study by Kornilov [6] on the phase equilibrium between  $\text{NiAl}$  and Nb. This kind of a layered structure results from incomplete interdiffusion between the matrix of  $\text{NiAl}$  and the elemental addition of Nb.

The pseudo-binary phase diagram for  $\text{NiAl-Nb}$  is reproduced in Figure 4 from Kornilov [6]. With increasing Nb, the phases present in this pseudo binary section are  $\text{NiAl}$  (with a very limited solubility of Nb),  $\text{NiAlNb}$  and  $\text{NiAlNb}_2$ .  $\text{NiAl}$  and  $\text{NiAlNb}$  exhibit a eutectic at about 1710 K. The solubility of Nb in  $\text{NiAl}$ , according to this diagram is less than 1 at% at low temperatures, but increases significantly above about 1450 K and can approach 5 at% near the eutectic temperature. Hence, during the homogenization treatment (1523 K), the matrix of  $\text{NiAl}$  and the Nb powder particles act as a finite spherical diffusion couple and the phases corresponding to the two intermediate ternary intermetallics form between the  $\text{NiAl}$  and the Nb.

Since the solubility of Nb in  $\text{NiAl}$  is much higher at the homogenization temperature than at room temperature, the slow cooling after the homogenization treatment results in reprecipitation of a second phase of  $\text{NiAlNb}$  in the matrix of  $\text{NiAl}$ . A distribution of very fine precipitates is, in fact, observed when a thin foil is examined on the Transmission Electron Microscope at a high magnification (Figure 5a). These precipitates are, however, only 10 to 50 nm. in size and too small to be detected at the low magnifications used in the optical and scanning electron micrographs. A diffraction pattern showing the spots for the matrix as well as the precipitates is shown in Figure 5b. The diffraction spot used to obtain the dark field image of the precipitates in Figure 5a is indicated by the arrow in Figure 5b.

#### (B) DEFORMED SPECIMEN

Cylindrical specimens were tested at slow strain rates in compression and the behavior of a specimen with an initial strain rate of  $3 \times 10^{-3}$  / sec is plotted in the form of a true stress- true plastic strain curve in Figure 6 and compared with similar curves for binary  $\text{NiAl}^*$ . Plastic flow in the ternary alloy is initiated at a stress of about 35.0 MPa which is significantly higher than that for the binary alloy, indicating a substantial strengthening due to the ternary addition. The flow stress, however, drops

\*Unpublished results from J.D. Whittenberger of NASA Lewis Research Center.



during the deformation to a lower value of about 29 MPa after a plastic strain of about 4%. A possible explanation for the strengthening can be obtained from an understanding of the microstructure of the tested specimen.

The matrix NiAl grains appear to have grown somewhat during the testing as evidenced by comparing the optical microstructure of the tested specimen in Figure 7a with that of the untested specimen in Figure 1b. The average grain size measured shows an increase from about 25 micrometers to about 33 micrometers. A considerable amount of etch pitting within the grains is suspected to be associated with dislocations within these grains. Voids appear to have coalesced along the triple points and grain boundaries during the testing, presumably due to grain boundary sliding.

A striking feature of the deformed specimen when compared with the undeformed specimen is the presence of many precipitates within the grains of the deformed specimen when compared on the scanning electron microscope in the backscatter mode (Figure 7b compared with Figure 2a). These precipitates are between 0.5 to 1 micrometer in size and much smaller than the original Nb powder particles. These precipitates have been shown to be NiAlNb precipitates and could be a result of coarsening of much finer precipitates which were not resolved on the SEM in the homogenized specimen.

An interesting aspect of the microstructure of the deformed specimen is the presence of regions around the large particles which are devoid of the fine precipitates. Such a precipitate-free zone must be a consequence of dissolution of smaller precipitates in the vicinity of the larger particles and redeposition on the surface of the larger particles due to Ostwald ripening.

Transmission electron microscopy of the deformed specimen reveals precipitates of the size of about 500 nm (Figure 8), thus, providing direct evidence that the precipitates have coarsened significantly during the high temperature testing (compare Figure 5 with Figure 8). The size of the precipitates observed in the transmission electron micrograph is in agreement with the size observed in the scanning electron micrograph of the tested specimen. A possible reason for the rapid coarsening during deformation may be increased diffusion through dislocation pipes.

### (C) STRENGTHENING MECHANISM

The mechanism of strengthening in the ternary alloy is believed to be due to the interaction between the fine precipitates and dislocations. Dislocation bowing as well as development of dislocation networks between the precipitates are observed throughout the thin foil of the deformed specimen. Typical examples are illustrated in Figures 9a and 9b. This kind of interaction is generally observed when the precipitates act as obstacles to dislocation motion and hence strengthen the material [7,8,9].

Dislocation networks with segments parallel to  $\langle 101 \rangle$  and  $\langle 110 \rangle$ g vectors developed between precipitate particles. Curved dislocation lines are dominant at and near precipitates, whereas straight parallel dislocations were observed in groups in the matrix and piled up at elongated particles. Subgrain boundaries were observed at grain boundaries and at the

precipitates. The burgers vectors of dislocations in the deformed specimen were not uniquely determined. However, in general, the dislocations were strongly visible with (110) reflections and invisible with (112) reflections.

The identification of the precipitates which are believed to cause the strengthening was carried out using selected area and microdiffraction on the transmission electron microscope using the deformed specimen. The precipitates in the undeformed specimen were too small to be properly analyzed and it is assumed that they have the same composition and crystal structure as those identified in the tested specimen. The precipitates in the deformed specimen are found to be NiAlNb with a hexagonal crystal structure. A TEM bright field image of one of the precipitates and the corresponding SAD and microdiffraction patterns of a zone axis are shown in Figure 10. Measurements from several diffraction patterns confirm the hexagonal phase NiAlNb. The d-spacings from the Inorganic Powder Diffraction File for NiAlNb and those measured from electron diffraction patterns are presented in Table 1. X-Ray diffraction of the deformed specimen in a powder form, also agreed with the conclusion that the second phase present in the matrix of NiAl is the hexagonal phase NiAlNb. These data are also presented in the same table for comparison. The possibility of the second phase being Ni<sub>2</sub>AlNb (a Heusler alloy) was very carefully checked and ruled out.

In terms of the strengthening mechanism in the ternary alloy, since the ternary intermetallic phase NiAlNb is harder than the binary NiAl [6], dislocation motion at the testing temperature appears to be hindered by the presence of these fine precipitates. Such a mechanism is very sensitive to the average spacing between and hence the size of the precipitates for a given volume fraction. Coarsening of these precipitates could, therefore, have dramatic consequences for strengthening. In fact, the drop of flow stress during the test is suspected to have been caused by coarsening of the precipitates from about 50 nm observed in the undeformed as-homogenized specimen to about 500 nm in the deformed specimen. At the same time, the dislocations present between the precipitates may act as rapid paths for diffusion in the matrix, thereby enhancing the kinetics of the coarsening of the precipitates.

It should be pointed out here that these results are in agreement with the proposed strengthening mechanism in an alloy containing 2 at% Ta [10], investigated as part of the same overall program for investigating the effect of ternary additions on NiAl at NASA Lewis Research Center.

#### 4. CONCLUSIONS

The results of this investigation suggest the following conclusions:

- 1) Homogenization of ternary alloys of NiAl and Nb, prepared by hot extrusion of powder blends of NiAl and Nb, results in the formation of the intermediate phases NiAlNb and NiAlNb<sub>2</sub>.
- 2) The high temperature strengthening of this alloy appears to be due to a dispersion of fine precipitates (~50 nm in size) of NiAlNb which have a hexagonal crystal structure. These precipitates interfere with dislocation

motion during high temperature deformation.

- 3) The strengthening precipitates coarsen significantly during the testing (from about 50 nm to 500 nm) and this coarsening may be responsible for the drop in flow stress during the deformation.

#### ACKNOWLEDGEMENTS

The authors would like to acknowledge the support of Sohio Research Center for the use of their microscopy facilities and NASA Lewis Research Center for supplying the materials.

#### REFERENCES

1. "Structural Uses for Ductile Ordered Alloys", NMAB Report No. 419, August 31, 1984, National Research Council, Washington, D.C.
2. J.R. Stephens, "The B2 Aluminides as Alternative Materials", NASA Technical Memorandum 86937, prepared for the 1984 Fall Meeting of the Materials Research Society, Boston, Nov., 1984.
3. N.S. Stoloff, International Metals Reviews, 1984, Vol. 29. No. 3, p. 123.
4. C.T. Liu, 'Design of Ordered Intermetallic Alloys for High Temperature Structural Uses'. Paper presented at the AIME Symposium on High Temperature Alloys, Theory and Design, April 1984, Bethesda, Maryland.
5. K.M. Vedula, V. Pathare, I. Aslanidis and R.H. Titran, to be published in the Proceedings of a Symposium on High Temperature Ordered Intermetallic Alloys at the Materials Research Society Meeting, Boston, November, 1984.
6. I.I. Kornilov, R.S. Mints, L.N. Guseva, Yu.S. Malkov, Russian Metallurgy, No.6, 1965, p.83.
7. O.D. Sherby, R.H. Klundt and A.K. Miller, Met. Trans. 1977, Vol. 8A, p.843.
8. G.S. Ansell and J. Weertman, Trans. AIME, 1959, Vol. 215, p.838.
9. J.J. Petrovic and L.J. Ebert, Met. Trans. Vol. 4, 1973, p.1309.
10. V.M. Pathare, M.S. Thesis, Department of Metallurgy and Materials Science, Case Western Reserve University, Cleveland, Ohio, 1984.

TABLE 1: COMPARISON OF d-VALUES FROM POWDER DIFFRACTION (PD) FILE FOR  $\text{NiAlNb}$  WITH THOSE DETERMINED BY ELECTRON DIFFRACTION (ED) FROM PRECIPITATES AND X-RAY DIFFRACTION (XRD) OF PULVERIZED HOMOGENIZED ALLOY IN THIS STUDY.

Hexagonal 12H      a = 5.00      c = 8.093			
hkl	PD FILE	ANGSTROMS MEASURED, ED	MEASURED, XRD
100	4.33	4.35	
002	4.05	4.06	
101	3.82	3.83	
102	2.96	2.96	
201	2.09	2.11	2.10
110	2.50		2.47
103	2.29	2.25	2.26
213	1.39		1.38
220	1.25		1.23

ORIGINAL PAGE IS  
OF POOR QUALITY

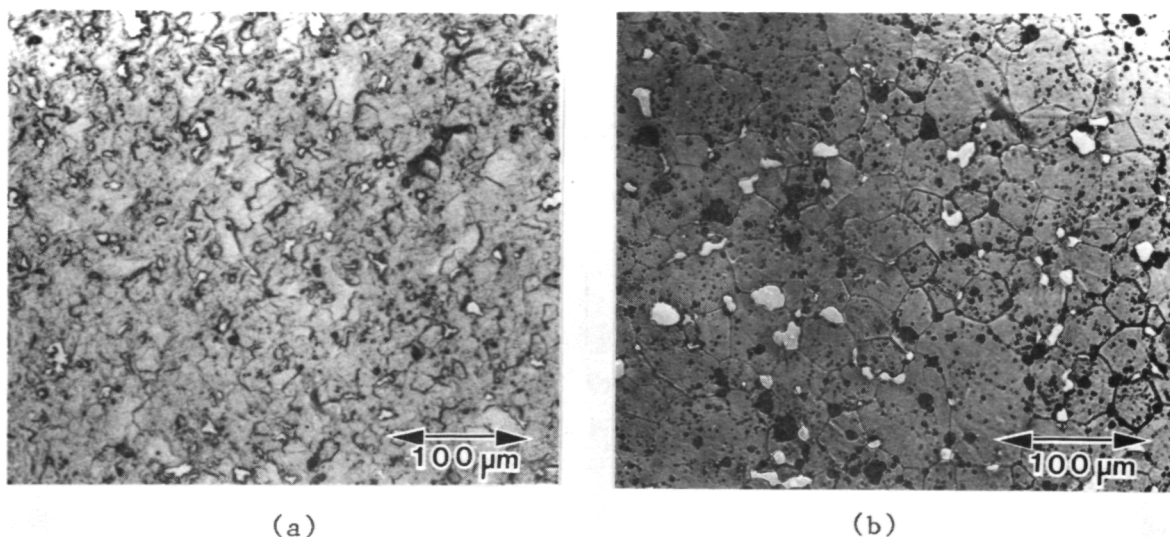


Figure 1. Comparison of Optical Micrographs of Cross-sections of (a) As-Extruded and (b) As-Homogenized specimens of the NiAl-2.26 at% Nb alloy (Marbles Reagen Etch)


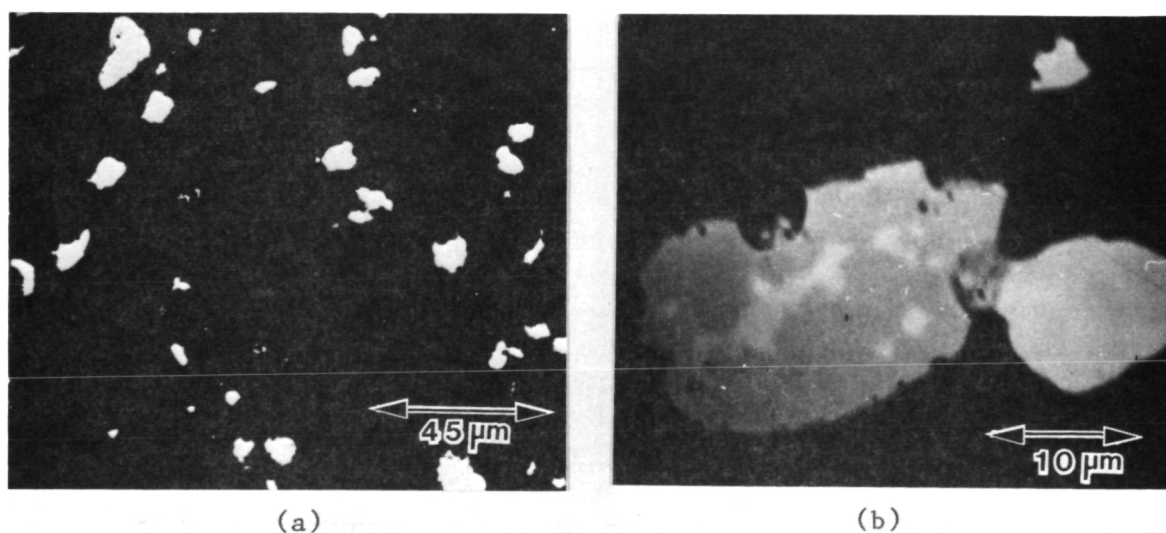


Figure 2. SEM Backscattered Electron Images of the Homogenized Alloy Showing (a) A Typical Distribution of Nb-rich Particles and (b) The Existence of a Layered Two Phase Structure within some of the Larger Particles. (Cross-section).

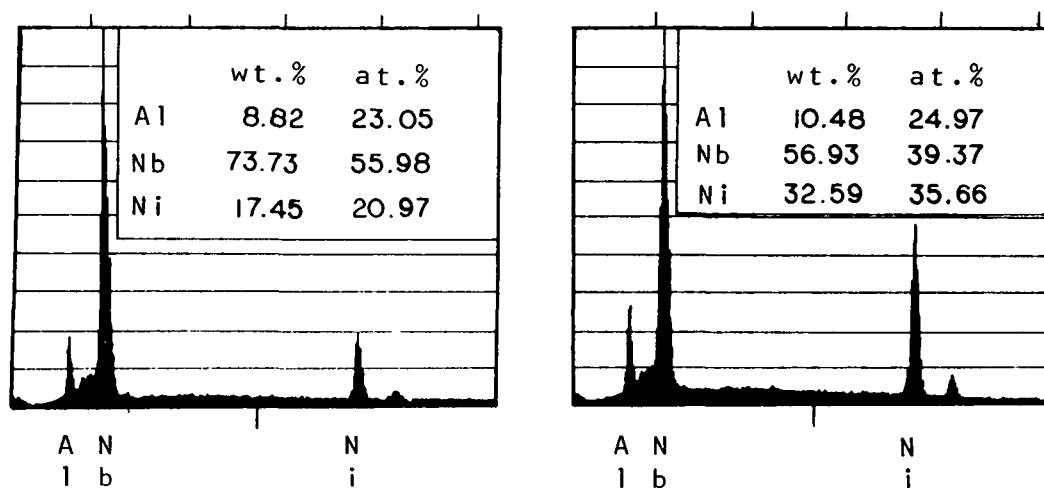

(a) (b)

Figure 3. EDS Analysis of the Two Regions of Particle in Figure 2b  
 (a) The Inner Phase Corresponding Roughly to  $\text{NiAlNb}_2$  and  
 (b) The Outer Phase Corresponding Roughly to  $\text{NiAlNb}$ .

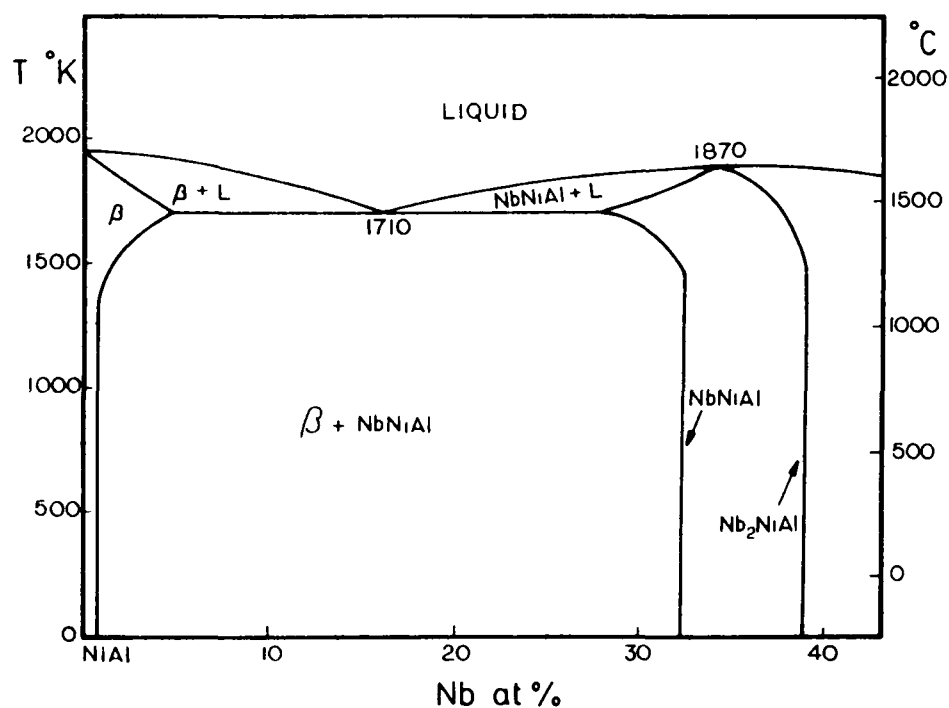


Figure 4. Pseudo-Binary Phase Diagram of the NiAl-Nb system.  
 (Kornilov, Ref. 6).

ORIGINAL PAGE IS  
OF POOR QUALITY

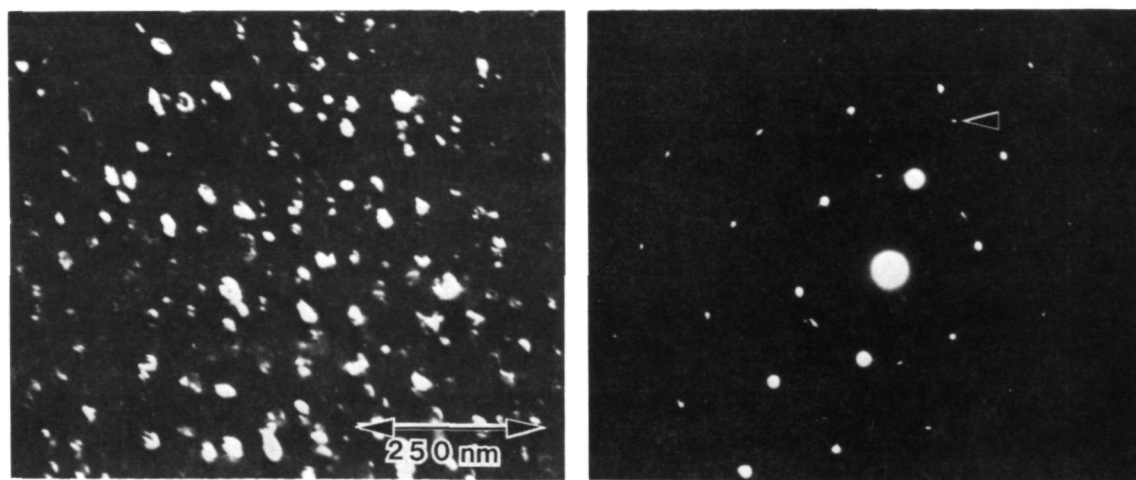


Figure 5. (a) TEM Dark Field Image of Precipitates in the Homogenized Alloy and (b) The Corresponding Diffraction Pattern with Arrow Indicating the Reflection used for Imaging.


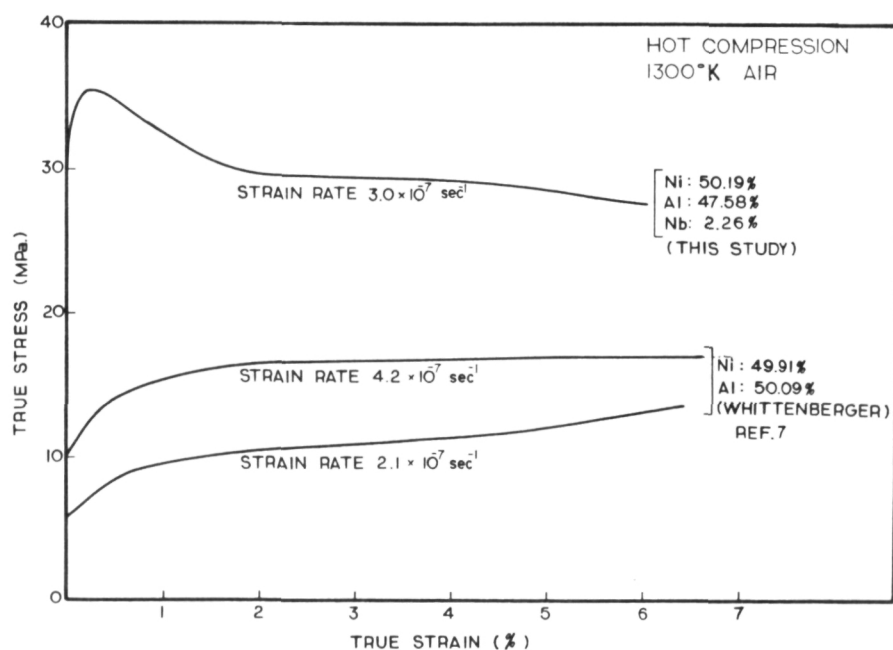


Figure 6. Comparison of the True Stress- True Plastic Strain Behavior of the Nb Containing Alloy with a Binary NiAl Alloy (Ref. 7). Specimens Tested in Compression at 1300 K and Slow strain Rates.



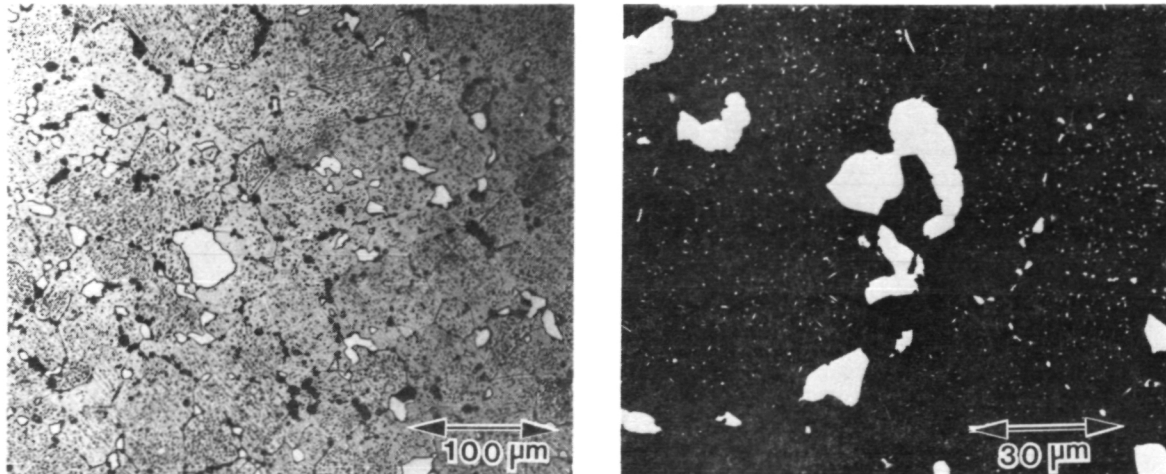

(a)

(b)

Figure 7. (a) Optical Microstructure of Specimen after Testing Showing Grain Boundary Void Formation (Etched), (b) SEM Backscattered Electron Image of Same Specimen Showing Coarsened NiAlNb Precipitates and Precipitate Depleted Regions Around Original Nb-Rich Particles.

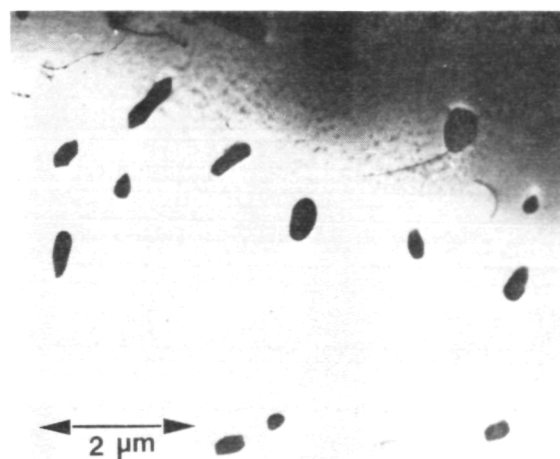


Figure 8. TEM Bright Field Image of Deformed Specimen Showing Coarsened Precipitates of NiAlNb.

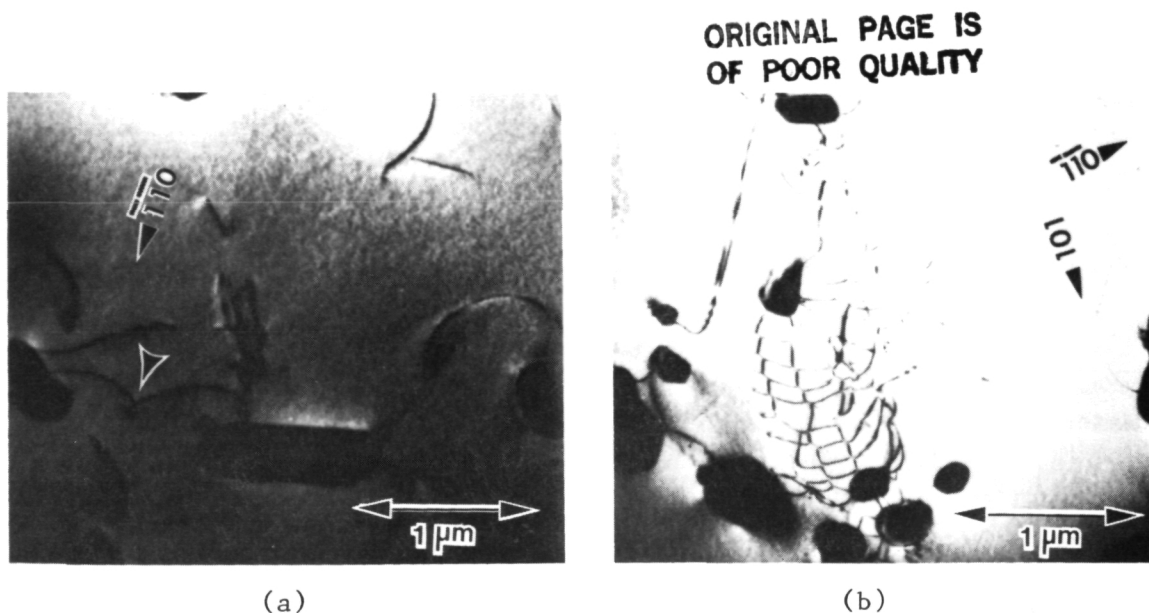


Figure 9. Transmission Electron Micrographs of Deformed Specimen Illustrating (a) Dislocations Pinned at and bowing Between Precipitates and (b) Dislocation Networks Formed Between Precipitates.

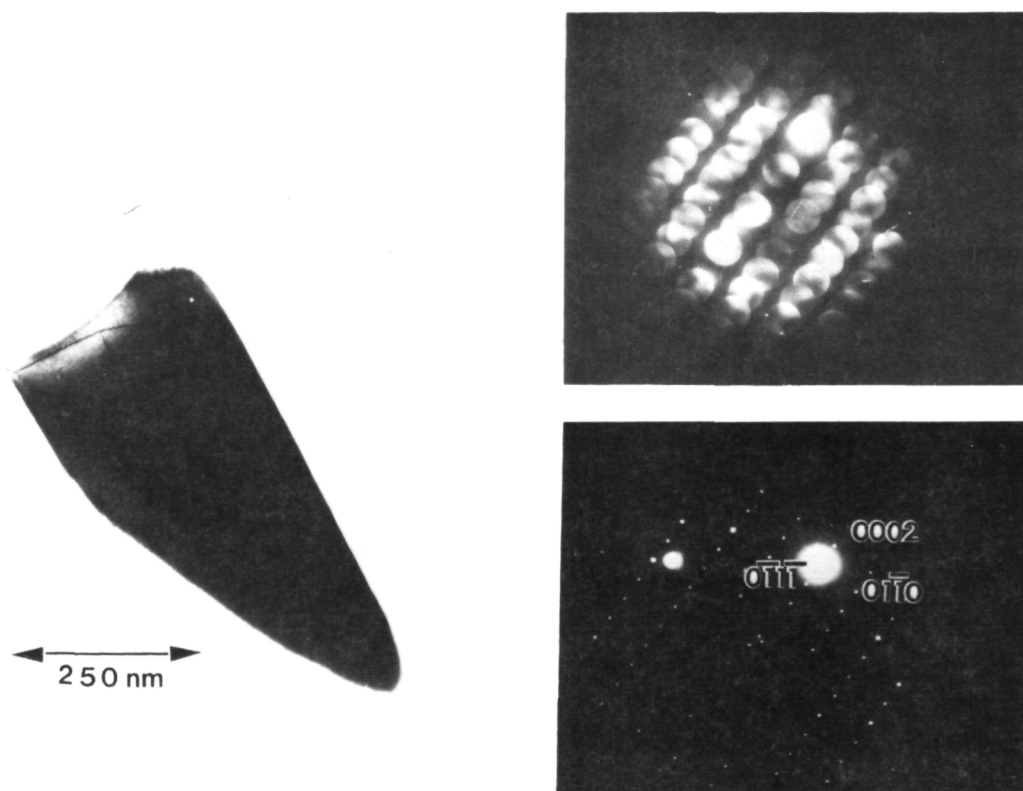


Figure 10. TEM Bright Field Image of a Large Precipitate in the Deformed Specimen and Corresponding SAD and Micro-diffraction Patterns of a Zone Axis Indexed as  $(2\bar{1}10)$ .

1. Report No. <b>NASA CR-175073</b>		2. Government Accession No.		3. Recipient's Catalog No.	
4. Title and Subtitle  <b>High Temperature Dispersion Strengthening of NiAl</b>				5. Report Date <b>March 1986</b>	
				6. Performing Organization Code	
7. Author(s) <b>Mark Sherman and Krishna Vedula</b>				8. Performing Organization Report No. <b>None</b>	
				10. Work Unit No.	
9. Performing Organization Name and Address <b>Case Western Reserve University Dept. of Metallurgy and Materials Science Cleveland, Ohio</b>				11. Contract or Grant No. <b>NAG 3-387</b>	
				13. Type of Report and Period Covered <b>Contractor Report</b>	
12. Sponsoring Agency Name and Address <b>National Aeronautics and Space Administration Washington, D.C. 20546</b>				14. Sponsoring Agency Code <b>505-63-01</b>	
15. Supplementary Notes <b>Final report. Project Manager, Robert H. Titran, Materials Division, NASA Lewis Research Center, Cleveland, Ohio 44135. Mark Sherman is presently at Sohio Research Center, Cleveland, Ohio.</b>					
16. Abstract <b>A potential high temperature strengthening mechanism for alloys based on the intermetallic compound NiAl has been investigated. This study forms part of an overall program at NASA Lewis Research Center for exploring the potential of alloys based on NiAl for high temperature applications. An alloy containing 2.26 at% Nb and produced by hot extrusion of blended powders has been examined in detail using optical and electron microscopy. Interdiffusion between the blended Nb and NiAl powders results in the formation of intermediate phases. A fine dispersion of precipitates of a hexagonal, ordered NiAlNb phase in a matrix of NiAl can be produced and this results in strengthening of the alloy by interfering with dislocation motion at high temperature. These precipitates are, however, found to coarsen during the high temperature (1300 K) deformation at slow strain rates and this may impose some limitations on the use of this strengthening mechanism.</b>					
17. Key Words (Suggested by Author(s)) <b>Aluminide; Nickel; Intermetallic; Dispersion strengthening</b>				18. Distribution Statement <b>Unclassified - unlimited STAR Category 26</b>	
19. Security Classif. (of this report) <b>Unclassified</b>	20. Security Classif. (of this page) <b>Unclassified</b>		21. No. of pages <b>14</b>	22. Price* <b>A02</b>	

National Aeronautics and  
Space Administration

**Lewis Research Center**  
Cleveland, Ohio 44135

Official Business  
Penalty for Private Use \$300

**SECOND CLASS MAIL**

**ADDRESS CORRECTION REQUESTED**



Postage and Fees Paid  
National Aeronautics and  
Space Administration  
NASA-451

**NASA**

---