



# **Correlations of Capacitance-Voltage Hysteresis with Thin-Film CdTe Solar Cell Performance During Accelerated Lifetime Testing**

David Albin and Joseph del Cueto

*Presented at the 2010 IEEE International Reliability Physics Symposium (IRPS)  
Garden Grove, California  
May 2-6, 2010*

**NREL is a national laboratory of the U.S. Department of Energy, Office of Energy Efficiency & Renewable Energy, operated by the Alliance for Sustainable Energy, LLC.**

**Conference Paper**  
NREL/CP-5200-47761  
March 2011

Contract No. DE-AC36-08GO28308

## NOTICE

The submitted manuscript has been offered by an employee of the Alliance for Sustainable Energy, LLC (Alliance), a contractor of the US Government under Contract No. DE-AC36-08GO28308. Accordingly, the US Government and Alliance retain a nonexclusive royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for US Government purposes.

This report was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or any agency thereof.

Available electronically at <http://www.osti.gov/bridge>

Available for a processing fee to U.S. Department of Energy  
and its contractors, in paper, from:

U.S. Department of Energy  
Office of Scientific and Technical Information

P.O. Box 62  
Oak Ridge, TN 37831-0062  
phone: 865.576.8401  
fax: 865.576.5728  
email: <mailto:reports@adonis.osti.gov>

Available for sale to the public, in paper, from:

U.S. Department of Commerce  
National Technical Information Service  
5285 Port Royal Road  
Springfield, VA 22161  
phone: 800.553.6847  
fax: 703.605.6900  
email: [orders@ntis.fedworld.gov](mailto:orders@ntis.fedworld.gov)  
online ordering: <http://www.ntis.gov/help/ordermethods.aspx>

Cover Photos: (left to right) PIX 16416, PIX 17423, PIX 16560, PIX 17613, PIX 17436, PIX 17721



Printed on paper containing at least 50% wastepaper, including 10% post consumer waste.

# Correlations of Capacitance-Voltage Hysteresis with Thin-film CdTe Solar Cell Performance During Accelerated Lifetime Testing

David S. Albin and Joseph A. del Cueto  
National Renewable Energy Laboratory (NREL)  
1617 Cole Boulevard, M.S. 3219  
Golden, CO 80401  
Phone: +1-303-384-6550, e-mail: david.albin@nrel.gov

**Abstract**—In this paper we present the correlation of CdTe solar cell performance with capacitance-voltage hysteresis, defined presently as the difference in capacitance measured at zero-volt bias when collecting such data with different pre-measurement bias conditions. These correlations were obtained on CdTe cells stressed under conditions of 1-sun illumination, open-circuit bias, and an acceleration temperature of approximately 100 °C.

**Keywords**— Photovoltaic, Cadmium Telluride (CdTe), Capacitance Voltage Hysteresis, Transient Ion Drift (TID), Transient Capacitance, Deep Level Transient Spectroscopy (DLTS).

## I. INTRODUCTION

Polycrystalline CdS/CdTe thin film solar cells have demonstrated small-area, laboratory efficiencies of 16.5% [1]. The highest reported efficiency for CdTe modules in [2] is 10.9% though this value is nearly a decade old. Higher performance levels for industrial products based on CdTe are likely but not openly disseminated for strategic reasons. In addition to considerable research addressing efficiency, recent work has focused on the intrinsic durability of these thin film semiconductor devices. The effects of back contact and doping strategies have been heavily researched for example [3, 4, 5]. This is driven by the inherent difficulty in fabricating ohmic contacts on wide band gap, p-type CdTe. More recently, the detrimental effects of localized shunts [6], the general effects of polycrystalline thin film micro-nonuniformities [7], and cell fabrication details revealed through factorial, design-of-experiment research [8] have been openly presented.

The basic structure of a thin film CdS/CdTe solar cell is that of a glass superstrate design in which light passes through a conducting/insulating (buffer) oxide film layer stack deposited on glass. Most laboratory and industrial cells use tin-oxide (SnO<sub>2</sub>) for these layers, though there is considerable interest in more advanced stannate materials (Cd<sub>2</sub>SnO<sub>4</sub> and ZnSnO<sub>x</sub>). Once transmitted through the glass/TCO/buffer superstrate, light is then absorbed in the n-CdS/p-CdTe heterojunction structure which provides the field necessary for separating photo-generated carriers. A back contact structure completes the cell. A schematic of this basic design is shown in Figure 1.

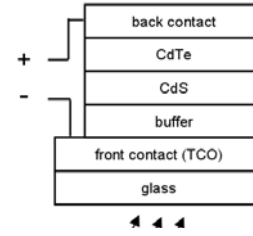


Fig. 1. Basic CdS/CdTe Solar Cell Design.

In order to ascertain the long term reliability of modules based upon CdS/CdTe, cells of this basic design were exposed to 1-sun illumination under open-circuit,  $V_{oc}$ , bias and acceleration temperatures of 60 – 120 °C for times exceeding 1000 hours [9]. Under field-use conditions, series-connected cells nominally see voltages somewhat less than  $V_{oc}$ , thus, open-circuit conditions represent an additional form of acceleration. In this study, two dominant degradation mechanisms were identified in the temperature range studied. As shown in Fig. 2(a), between 60-80 °C, an activation energy of 2.94 eV was measured and was attributed to S-outdiffusion from the CdS layer into the CdTe based upon a reported value of 2.8 eV for bulk diffusion of S in CdTe [10]. This assertion was also based upon the observation of Kirkendall-like voiding of the CdS layer in cells that underwent stress. In the temperature range 100-120 °C, an activation energy of 0.63 eV was determined which agreed well with the reported value of 0.67 eV for Cu diffusion in CdTe [11].

Since cell efficiency,  $\eta\%$ , is determined by the equation:

$$\eta\% = \frac{V_{oc} \times J_{sc} \times FF}{\Phi_{inc}} \quad (1)$$

(where  $\Phi_{inc}$ , the incident power density is typically normalized to a solar value of 100 mW/cm<sup>2</sup>), a correlation analysis  $\Delta\eta\%$  versus changes in  $V_{oc}$ , short-circuit current density,  $J_{sc}$ , and fill factor, FF, during stress testing as a function of stress temperature was performed. This analysis is shown in Figure 2(b).

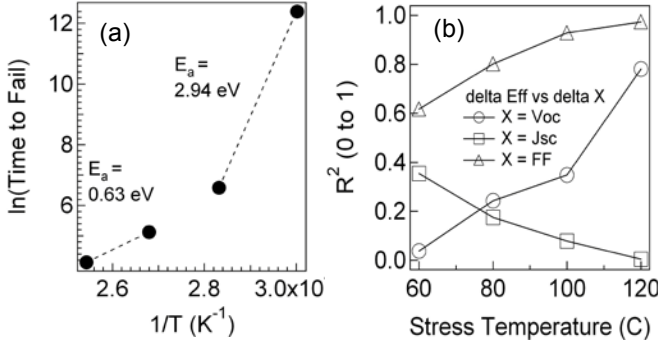


Fig. 2. Degradation activation energies (a) and correlation analysis (b) of how efficiency (Eff) changes versus changes in  $V_{oc}$ ,  $J_{sc}$ , and FF.

The moderate correlation of  $\eta\%$  with  $J_{sc}$  seen at lower stress temperatures is due to reduced optical attenuation associated with S-outdiffusion from the CdS. The most important variable affecting  $\eta\%$  at all temperatures, approaching a near ideal correlation at 120 °C, was FF. FF represents the efficiency by which photons absorbed in a solar cell are collected by a combination of field and diffusion-limited collection mechanisms. Within the space-charge, photo-generated electrons and holes are swept towards the n and p-sides of the junction respectively by the built-in field. In the quasi-neutral region, carrier diffusion length determines whether they are collected. Recombination of carriers before collection is the greatest impediment to improving the overall performance, primarily  $V_{oc}$ , for these cells.

The fundamental current-density,  $J$ , and voltage,  $V$ , behavior of a solar cell is represented by:

$$J = J_{SCR} + J_{QNR} + \left( \frac{V - JR_s}{R_{sh}} \right) - J_{ph} \quad (2)$$

where  $J_{SCR}$ ,  $J_{QNR}$ , and  $J_{ph}$  represent recombination currents in the space-charge and quasi-neutral regions of the cell, as well as the photo-generated current, while  $R_s$  and  $R_{sh}$  represent series and parallel (shunt) resistance losses.  $J_{SCR}$  and  $J_{QNR}$  are further represented by the following:

$$J_{QNR} = J_{01} \left( e^{\frac{q(V-JR_s)}{kT}} - 1 \right) \quad (3)$$

$$J_{SCR} = J_{02} \left( e^{\frac{q(V-JR_s)}{2kT}} - 1 \right) \quad (4)$$

where  $J_{01}$  and  $J_{02}$  are further dependent upon minority carrier transport properties.

In the fourth quadrant, maximum power output is achieved by maximizing the term,  $J_{ph}$ , and minimizing the first three terms in (2), often referred to collectively as the “forward” current. Each of the forward current terms contributes to decreased cell performance. It should be noted that the

recombination currents,  $J_{QNR}$ , and  $J_{SCR}$  are themselves dependent upon resistive effects as shown in (3) and (4).

The loss parameters  $J_{QNR}$ ,  $J_{SCR}$ ,  $R_s$ , and  $R_{sh}$  can be determined graphically or by direct modeling with programs like Pspice. Using the latter approach, the percent contribution each parameter contributes to the forward current (and thus loss) in the power quadrant for a laboratory made 14.4% CdS/CdTe solar cell is shown in Fig. 3.

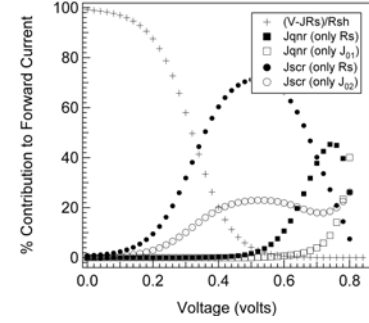


Fig. 3. Percent contribution to forward current losses modeled for a 14.4% CdS/CdTe cell.

The results shown in Fig. 3 use a model-fitted value of 3 ohms\*cm<sup>2</sup> for  $R_s$  which is a reasonable upper value observed during stress testing of these cells [9]. As seen in this figure, recombination occurs mostly in the space-charge except near  $V_{oc}$  where recombination in the quasi-neutral region, i.e., between the depletion width and back contact begins to dominate. Note that resistive contributions for both effectively go to zero at  $V_{oc}$  where  $J = 0$  in equations (3) and (4).

The effect of addressing recombination within the quasi-neutral region is shown in Fig. 4.

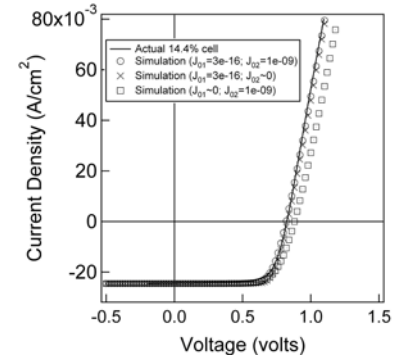


Fig. 4. The effect of reducing quasi-neutral recombination on the  $V_{oc}$  of CdTe solar cells (all  $J$  terms given in A/cm<sup>2</sup>).

Shown in this figure is the Pspice model simulation used to extract the loss mechanisms shown in Fig. 3 along with actual cell data in a conventional J-V diagram. In this case  $J_{01}$  and  $J_{02}$  equal  $3e^{-16}$  and  $1e^{-09}$  A/cm<sup>2</sup> respectively. Having obtained a good fit, the model is then perturbed by simulating conditions where recombination is removed in either the space-charge ( $J_{02} \sim 0$ ) or quasi-neutral ( $J_{01} \sim 0$ ) regions. As can be deduced from Fig. 4, improving CdTe material quality within the depletion width (space-charge) does not improve cell performance. However, an additional 60 mV (0.82 to 0.88) can result if recombination in the quasi-neutral region is reduced.

The results of this fundamental calculation make understanding the depletion width position important when determining why FF changes during stress testing of cells. With this goal in mind, a new technique for collecting capacitance-voltage (C-V) data quickly during accelerated stress testing was developed [12]. This technique collects capacitance data first in a reverse direction (rev) voltage scan followed by a subsequent, forward direction (fwd) scan. This approach yields two distinct C-V curves as shown in Fig. 5 for representative cells with and without Cu added intentionally as a dopant during back contact fabrication.

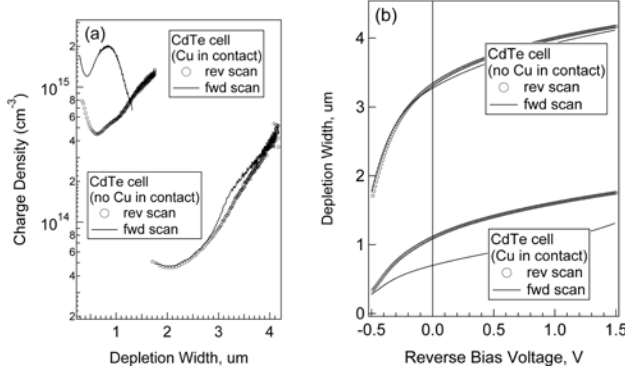


Fig. 5. Mott-Schottky plot (a) and corresponding depletion width vs. bias diagram (b) for CdS/CdTe cells with and without intentional Cu.

Fig. 5(b) clearly shows how Cu affects the space-charge depletion width,  $W_d$ . The strong decrease in  $W_d$  with Cu reflects an obvious increase in ionized acceptors,  $N_a^-$  in the CdTe possibly as  $Cu_{Cd}$  or as a paired, defect complex [13]. The decrease in  $W_d$  (since it can be so easily explained by doping) is not surprising. What is less obvious is the large degree of hysteresis associated with the introduction of Cu. When Cu is not intentionally added (Cu is well-known to be a naturally occurring trace impurity in CdTe for instance), we see little indication of hysteresis within our experimental error. This has been confirmed in every cell made in which Cu was intentionally absent. The presence of Cu introduces significant hysteresis in which  $W_d$  measured during the second (fwd) scan is always lower than the value of  $W_d$  determined during the first (rev) scan. Hysteresis in C-V measurements on polycrystalline thin film cells is also regularly reported by others [14, 15] in which the authors attribute this to the presence of deep states. The basis for this possibility is explained in more detail in [12].

Recently however, capacitance transients were used by Enzenroth, et al. [16] and Lyubomirsky, et al. [17] to determine the diffusion parameters of mobile  $Cu_i^+$  ions in CdTe and  $CuInSe_2$  cells and materials based upon a transient ion drift (TID) method first developed by Heiser and Mesli [18]. In particular, Enzenroth used the TID approach to quantify an increase in mobile  $Cu_i^+$  as a function of increased Cu added during cell fabrication. The presence of mobile charge, in particular,  $Cu_i^+$ , is thus plausible as an explanation for the effects shown in Fig. 5.

## II. EXPERIMENTAL DESIGN

Two sets of CdS/CdTe cells were fabricated in which the only difference between sets were the TCO/buffer structure used. In one set, a conventional bi-layer  $SnO_2$  structure consisting of undoped (insulating) and doped (conducting)  $SnO_2$ /Corning 7059 borosilicate glass superstrates were used to grow CdS/CdTe devices.  $SnO_2$  layers were grown by chemical vapor deposition (CVD) of tetramethyltin with bromotrifluoromethane ( $CBrF_3$ ) added when F-doping was required. Cells using these superstrate structures will be referred to as c $SnO_2$ /i $SnO_2$  cells. In the other set, cadmium (CTO) and zinc (ZTO) stannate materials were used as the conducting and buffer layer oxides. Stannate superstrate structures were fabricated by sputtering CTO and ZTO onto unheated borosilicate glass substrates with subsequent 650 °C anneals in He used to obtain the best optical and electrical properties. CdS and CdTe layers were deposited by chemical bath deposition (CBD) and close-spaced sublimation (CSS) respectively. Both sets used Cu-doped graphite prior to Ag paste metallization. Further details regarding the fabrication of cells can be found in references [1] and [19].

Performance data using standard J-V scans were made on cells after fabrication and during subsequent stress testing with a current-calibrated Oriel solar simulator. C-V measurements were performed in the dark at room temperature using an Agilent 4294A Precision Impedance Analyzer operated manually at 100 kHz with a 50 mV oscillation voltage. Capacitance data was collected by scanning voltage in two directions. Immediately upon applying a voltage of +0.5 V forward bias, capacitance was measured as voltage was quickly swept (~3 s) in a reverse (rev) direction to -1.5 V where bias was maintained for exactly 5 m. During the subsequent forward (fwd) sweep back to +0.5 V, capacitance data was again collected.

For stress testing, cells were placed glass-side up, under an Atlas CPS+ solar light source (~AM 1.5; 1-sun) in machined Al blocks designed to keep the cells at  $V_{oc}$  bias. Cell temperature was set at 100 °C. At times equal to 1, 4.4, 10, 28, 73, and 115 hrs cells were removed and allowed to relax in the dark for 12-24 hrs. After measurements of J-V and C-V, cells were again placed under stress. Some problems with temperature control were encountered during this test. It is very likely that actual stress temperatures exceeded 100 °C though the design of the Al blocks insured that all cells were at identical temperature.

## III. RESULTS AND DISCUSSION

The performance of cells, both initially as well as during stress testing are discussed in [12]. The uniformity of initial performance in cells grown on the  $SnO_2$ -based superstrates was very good. The highest performance achieved with this substrate was  $V_{oc} = 0.832$ ,  $J_{sc} = 23.2$ ,  $FF = 71.8$ , and  $\eta\% = 13.8$ . In contrast, considerable variation in performance was observed when using the CTO/ZTO superstrates. Some cells exhibited very high  $R_s$  due to cracking of the CTO/ZTO layers. However, the best performance ( $V_{oc} = 0.827$ ,  $J_{sc} = 24.6$ ,  $FF = 71.1$ ,  $\eta\% = 14.5$ ) was obtained using the CTO/ZTO substrate.

CTO/ZTO cell durability was also inferior to the  $\text{cSnO}_2/\text{iSnO}_2$  cells. This has been a somewhat consistent observation when testing CTO/ZTO cells fabricated at NREL. The durability of CTO/ZTO cells is determined however by both TCO and cell processing conditions and some discussion of this is presented in [12].

Of interest to this paper was the correlation observed between C-V hysteresis and cell performance during stress. Hysteresis is defined as the difference in  $W_d$  at  $V = 0$  between reverse and forward direction scans, i.e.,  $W_{d,\text{rev}} - W_{d,\text{fwd}}$ . Fig. 6 summarizes the variation of hysteresis with stress time as well as the correlation between  $V_{oc}$  and FF with hysteresis.

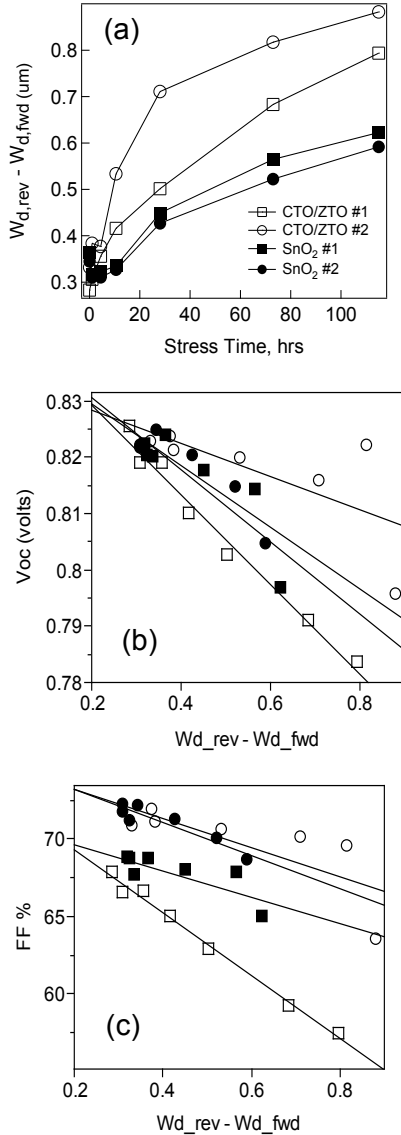


Fig. 6. Correlations during CdS/CdTe cell stress testing: (a) hysteresis vs. stress time, (b)  $V_{oc}$  vs. hysteresis, and (c) FF vs. hysteresis.

During stress, hysteresis was observed to increase as cell performance decreased. This increase with stress is shown in Fig. 6(a). The correlation of hysteresis with both  $V_{oc}$  and FF (shown in Fig. 6(b) and 6(c) respectively) was also apparent.

The correlation coefficient,  $R^2$  of  $V_{oc}$  with hysteresis for CTO/ZTO cells #1 and #2, and  $\text{SnO}_2$  cells #1 and #2 were 0.98, 0.46, 0.75, and 0.82. The same values for FF were 0.99, 0.58, 0.63, and 0.87. Similar correlations with either  $W_{d,\text{fwd}}$  or  $W_{d,\text{rev}}$  were not nearly as good and did not show the monotonic behavior shown in Fig. 6(b) and 6(c).

The origin of capacitance hysteresis during stress is not presently clear. Recent TID research suggesting an ionic basis is further supported by the early work by Snow, et al, who used hysteresis to measure ionic transport in insulating films [20]. In the context of this experiment, an ionic explanation would infer an important result. Since cells fabricated using the different TCO structures used identical Cu-doped back contacts, then the additional hysteresis shown in Fig. 6(a) for CTO/ZTO cells must be associated with the introduction of additional ions. In this case, the likely source would be from either the CTO or ZTO layers. C-V measurements are capable of detecting changes in charge below  $10^{15} \text{ cm}^{-3}$  and thus, this technique might be a useful way to measure ionic changes in the space-charge of cells in a non-destructive, and easily implementable way during stress testing. For example, the durability, in particular, chemical reactivity of new TCOs and buffers could be evaluated in such a fashion prior to costly scale-up of such structures in module manufacturing. Similarly, the effectiveness of various diffusion barriers to mitigate  $\text{Na}^+$  diffusion from soda-lime glasses might also be evaluated in such a fashion.

Regardless, an understanding of how best to interpret pre-bias dependent determinations of either  $W_{d,\text{fwd}}$  or  $W_{d,\text{rev}}$  are important since again, this is a key metric in understanding FF. The correlation of  $\eta\%$  with FF is extremely high for both initial performance as well as performance during stress testing.

#### IV. SUMMARY

An easy-to-implement, quick, and non-destructive technique was demonstrated for obtaining capacitance hysteresis measurements in thin-film polycrystalline solar cells. Initial results on CdS/CdTe solar cells stressed at approximately  $100^\circ\text{C}$  show a strong correlation between capacitance hysteresis (defined in this study as the difference in depletion width at  $V=0$ ) with cell  $V_{oc}$  and FF was shown. The origin of this hysteresis, whether electronic or ionic, is unclear though past work suggests an ionic nature. The technique shows potential for being an important diagnostic tool for understanding why FF in these cells change with stress.

#### ACKNOWLEDGMENT

The authors thank Drs. Jian Li, Tim Gessert, and Xiaonan Li of NREL for discussions concerning C-V measurements, CTO/ZTO, and  $\text{SnO}_2$  respectively. We acknowledge the support of the U.S. Department of Energy under Contract No. DOE-AC36-08G028308 with NREL.



## REFERENCES

- [1] X. Wu, "High efficiency polycrystalline CdTe thin-film solar cells," *Solar Energy* 77, 2004, pp. 803-814.
- [2] M. A. Green, K. Emery, Y. Hishikawa, and W. Warta, "Solar Cell Efficiency Tables (Version 34)," *Prog. Photovolt: Res. Appl.*, 17, 2009, pp. 320-326.
- [3] K. Dobson, I. Visoly-Fisher, G. Hodes, and D. Cahen, "Stabilizing CdTe/CdS Solar Cells with Cu-Containing Contacts to p-CdTe," *Advanced Materials*, 13 (9), 2001, pp. 1495-1499.
- [4] C. Corwine, A. Pudov, M. Gloeckler, S. Demtsu, and J. Sites, "Copper inclusion and migration from the back contact in CdTe solar cells," *Sol. Energy Mater. Sol. Cells*, 82, 2004, pp. 481-489.
- [5] D. Albin, D. Levi, S. Asher, A. Balcioğlu, "Precontact surface chemistry effects on CdS/CdTe solar cell performance and stability," *Proc. 28<sup>th</sup> IEEE Photovoltaics Specialists Conference*, New York, 2000, pp. 583-586.
- [6] T. McMahon, T.J. Berniard, and D.S. Albin, "Nonlinear shunt paths in thin-film CdTe solar cells," *J. Appl. Phys.*, 97, 2005, pg. 054503.
- [7] V.G. Karpov, A.D. Compaa, and D. Shvydka, "Effects of nonuniformity in thin-film photovoltaics," *Appl. Phys. Lett.*, 80 (22), 2005, pp. 4256-4258.
- [8] D.S. Albin, S.H. Demtsu, and T.J. McMahon, "Film thickness and chemical processing effects on the stability of cadmium telluride solar cells," *Thin Solid Films*, 515, 2006, pp. 2659-2668.
- [9] D.S. Albin, "Accelerated Stress Testing and Diagnostic Analysis of Degradation in CdTe Solar Cells," in *Reliability of Photovoltaic Cells, Modules, Components, and Systems*, edited by Neelkanth G. Dhere, *Proceedings of SPIE Vol. 7048 (SPIE, Bellingham, WA, 2008)* 70480N.
- [10] B. McCandless, M. Engelmann, and R. Birkmire, "Interdiffusion of CdS/CdTe thin films: Modeling x-ray diffraction line profiles," *J. Appl. Phys.* 89(2), 2001, pp. 988-994.
- [11] H. Woodbury and M. Aven, "Some Diffusion and Solubility Measurements of Cu in CdTe," *J. Appl. Phys.* 39(12), 1968, pp. 5485-5488.
- [12] D.S. Albin, R.G. Dhere, S.C. Glynn, J.A. del Cueto, and W.K. Metzger, "Degradation and Capacitance-Voltage Hysteresis in CdTe Devices," in *Reliability of Photovoltaic Cells, Modules, Components, and Systems II*, edited by Neelkanth G. Dhere, *Proceedings of SPIE Vol. 7412 (SPIE, Bellingham, WA, 2009)* 74120I.
- [13] S. Wei and S.B. Zhang, "Chemical trends of defect formation and doping limit in II-VI semiconductors: The case of CdTe," *Phy. Rev. B* 66, 2002, pp. 15521.
- [14] M. Wimbör, A. Romeo, and M. Igalson, "Electrical characterization of CdTe/CdS photovoltaic devices," *Opto-Electronics Review*, 8(4), 2000, pp. 375-377.
- [15] S. Hegedus and W.N. Shafarman, "Thin-Film Solar Cells: Device Measurements and Analysis," *Prog. Photovolt: Res. Appl.*, 12, 2004, pp. 155-176.
- [16] R. A. Enzenroth, K. L. Barth, and W.S. Sampath, "Transient Ion Drift Measurements of Polycrystalline CdTe PV Devices," *4<sup>th</sup> IEEE World Conference Photovoltaic Energy Conversion*, Hawaii, 2006, pp. 449-452.
- [17] I. Lyubomirsky, M.K. Rabinal, and D. Cahen, "Room-temperature detection of mobile impurities in compound semiconductors by transient ion drift," *J. Appl. Phys.* 81(10), 1997, pp. 6648-6691.
- [18] T. Heiser and A. Mesli, "Determination of the Copper Diffusion Coefficient in Silicon from Transient Ion-Drift," *Appl. Phys. A* 57, 1993, pp. 325-328.
- [19] D. Rose et al., "Fabrication Procedures and Process Sensitivities for CdS/CdTe Solar Cells," *Prog. Photovolt: Res. Appl.* 7, 1999, 331-340.
- [20] E.H. Snow, A.S. Grove, B.E. Deal, and C.T. Sah, "Ion Transport Phenomena in Insulating Films," *J. Appl. Phys.* 36, 1965, pp. 1664-1673.

**REPORT DOCUMENTATION PAGE**Form Approved  
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Executive Services and Communications Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

**PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ORGANIZATION.**

<b>1. REPORT DATE (DD-MM-YYYY)</b> March 2011			<b>2. REPORT TYPE</b> Conference Paper		<b>3. DATES COVERED (From - To)</b>	
<b>4. TITLE AND SUBTITLE</b> Correlations of Capacitance-Voltage Hysteresis with Thin-Film CdTe Solar Cell Performance During Accelerated Lifetime Testing					<b>5a. CONTRACT NUMBER</b> DE-AC36-08GO28308	
					<b>5b. GRANT NUMBER</b>	
					<b>5c. PROGRAM ELEMENT NUMBER</b>	
<b>6. AUTHOR(S)</b> D. Albin and J. del Cueto					<b>5d. PROJECT NUMBER</b> NREL/CP-5200-47761	
					<b>5e. TASK NUMBER</b> PVA9.2450	
					<b>5f. WORK UNIT NUMBER</b>	
<b>7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)</b> National Renewable Energy Laboratory 1617 Cole Blvd. Golden, CO 80401-3393					<b>8. PERFORMING ORGANIZATION REPORT NUMBER</b> NREL/CP-5200-47761	
<b>9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)</b>					<b>10. SPONSOR/MONITOR'S ACRONYM(S)</b> NREL	
					<b>11. SPONSORING/MONITORING AGENCY REPORT NUMBER</b>	
<b>12. DISTRIBUTION AVAILABILITY STATEMENT</b> National Technical Information Service U.S. Department of Commerce 5285 Port Royal Road Springfield, VA 22161						
<b>13. SUPPLEMENTARY NOTES</b>						
<b>14. ABSTRACT (Maximum 200 Words)</b> In this paper we present the correlation of CdTe solar cell performance with capacitance-voltage hysteresis, defined presently as the difference in capacitance measured at zero-volt bias when collecting such data with different pre-measurement bias conditions. These correlations were obtained on CdTe cells stressed under conditions of 1-sun illumination, open-circuit bias, and an acceleration temperature of approximately 100°C.						
<b>15. SUBJECT TERMS</b> Photovoltaic; Cadmium Telluride (CdTe); Capacitance Voltage Hysteresis; Transient Ion Drift (TID); Transient Capacitance; Deep Level Transient Spectroscopy (DLTS)						
<b>16. SECURITY CLASSIFICATION OF:</b>			<b>17. LIMITATION OF ABSTRACT</b> UL	<b>18. NUMBER OF PAGES</b>	<b>19a. NAME OF RESPONSIBLE PERSON</b>	
<b>a. REPORT</b> Unclassified	<b>b. ABSTRACT</b> Unclassified	<b>c. THIS PAGE</b> Unclassified			<b>19b. TELEPHONE NUMBER (Include area code)</b>	

Standard Form 298 (Rev. 8/98)  
Prescribed by ANSI Std. Z39.18