



# Comparison of the Isothermal Oxidation Behavior of As-Cast Cu-17%Cr and Cu-17%Cr-5%Al

## Part I: Oxidation Kinetics

*S.V. Raj*  
*Glenn Research Center, Cleveland, Ohio*

## NASA STI Program . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) program plays a key part in helping NASA maintain this important role.

The NASA STI Program operates under the auspices of the Agency Chief Information Officer. It collects, organizes, provides for archiving, and disseminates NASA's STI. The NASA STI program provides access to the NASA Aeronautics and Space Database and its public interface, the NASA Technical Reports Server, thus providing one of the largest collections of aeronautical and space science STI in the world. Results are published in both non-NASA channels and by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA counterpart of peer-reviewed formal professional papers but has less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.
- **CONFERENCE PUBLICATION.** Collected

papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or cosponsored by NASA.

- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services also include creating custom thesauri, building customized databases, organizing and publishing research results.

For more information about the NASA STI program, see the following:

- Access the NASA STI program home page at <http://www.sti.nasa.gov>
- E-mail your question via the Internet to [help@sti.nasa.gov](mailto:help@sti.nasa.gov)
- Fax your question to the NASA STI Help Desk at 301-621-0134
- Telephone the NASA STI Help Desk at 301-621-0390
- Write to:  
NASA Center for AeroSpace Information (CASI)  
7115 Standard Drive  
Hanover, MD 21076-1320



# Comparison of the Isothermal Oxidation Behavior of As-Cast Cu-17%Cr and Cu-17%Cr-5%Al

## Part I: Oxidation Kinetics

*S.V. Raj*

*Glenn Research Center, Cleveland, Ohio*

National Aeronautics and  
Space Administration

Glenn Research Center  
Cleveland, Ohio 44135

## Acknowledgments

The author thanks Mr. Donald Humphrey for conducting the isothermal oxidation tests and Mr. Dereck Johnson for conducting chemical analyses of the specimens.

This work was sponsored by the Fundamental Aeronautics Program  
at the NASA Glenn Research Center.

*Level of Review:* This material has been technically reviewed by technical management.

Available from

NASA Center for Aerospace Information  
7115 Standard Drive  
Hanover, MD 21076-1320

National Technical Information Service  
5285 Port Royal Road  
Springfield, VA 22161

Available electronically at <http://gltrs.grc.nasa.gov>

# **Comparison of the Isothermal Oxidation Behavior of As-Cast Cu-17%Cr and Cu-17%Cr-5%Al**

## **Part I: Oxidation Kinetics**

S.V. Raj  
National Aeronautics and Space Administration  
Glenn Research Center  
Cleveland, Ohio 44135

### **Abstract**

The isothermal oxidation kinetics of as-cast Cu-17%Cr and Cu-17%Cr-5%Al in air were studied between 773 and 1173 K under atmospheric pressure. These observations reveal that Cu-17%Cr-5%Al oxidizes at significantly slower rates than Cu-17%Cr. The rate constants for the alloys were determined from generalized analyses of the data without an *a priori* assumption of the nature of the oxidation kinetics. Detailed analyses of the isothermal thermogravimetric weight change data revealed that Cu-17%Cr exhibited parabolic oxidation kinetics with an activation energy of  $165.9 \pm 9.5 \text{ kJ mol}^{-1}$ . In contrast, the oxidation kinetics for the Cu-17%Cr-5%Al alloy exhibited a parabolic oxidation kinetics during the initial stages followed by a quartic relationship in the later stages of oxidation. Alternatively, the oxidation behavior of Cu-17%Cr-5%Al could be better represented by a logarithmic relationship. The parabolic rate constants and activation energy data for the two alloys are compared with literature data to gain insights on the nature of the oxidation mechanisms dominant in these alloys.

### **1. Introduction**

Uncoated copper alloy combustor liners are used extensively in rocket engines primarily due to their high thermal conductivity and suitable mechanical properties (Refs. 1 and 2). However, many of these commercial copper alloys are prone to extensive oxidation at temperatures exceeding 673 K (Ref. 3). Environmental damage of uncoated copper alloy liners, termed “blanching”, is observed in a liquid hydrogen (LH<sub>2</sub>) and liquid oxygen (LOX) rocket engine due to repeated oxidation-reduction cycles of the copper matrix (Ref. 2). As a result, the initially highly polished liner surface becomes very rough leading to a degradation in the heat transfer characteristics of the engine. Repeated polishing of the liner surface of a reusable launch vehicle (RLV) after each mission cycle results in a corresponding decrease in the cross-sectional area of the cooling channels with a decreased ability to carry the mechanical stresses. Thus, it is clear that a fundamental understanding of the oxidation behavior of copper and its alloys being considered for use in rocket engines either as combustion liners or as coatings is desirable.

The oxidation of pure copper has been extensively studied by several investigators since the 1930's (Refs. 3 to 22). These studies have elucidated the oxidation rate kinetics for copper (Refs. 6 to 8, 10, 14 to 16, 19 and 22) while largely confirming the applicability of the Wagner's parabolic oxidation rate theory for this metal above 473 K (Refs. 14 and 15). More recent studies have focused on the effect of a second phase on the oxidation kinetics of an almost pure Cu matrix (Refs. 20, 21, and 23 to 25). In this regard, the Cu-Cr system has proved to be a model alloy system for these types of studies owing to the limited solubility of Cr in Cu (Refs. 26 and 27). Several studies have demonstrated that Cu-Cr alloys generally exhibit parabolic oxidation kinetics although the compositions of the oxide scales appeared to depend on how the alloys were processed (Refs. 20 and 21) and their grain size (Refs. 20, 21, 23, and 25). Although copper oxides have been reported in the surface scales after isothermal oxidation in these investigations, there is less commonality in the observed results as to whether these alloys form a protective chromia subsurface layer. This lack of consistency in the formation of a protective Cr<sub>2</sub>O<sub>3</sub> is presumably due to variations in composition, alloy processing and microstructures.

Although Cu-17%Cr<sup>1</sup> (Ref. 25) and Cu-Cr alloys with Cr  $\geq$  26% (Refs. 28 to 30) have been proposed as protective coatings for copper alloy rocket engine combustion liners, there is an inherent danger in relying on alloys which do not consistently form a continuous protective Cr<sub>2</sub>O<sub>3</sub> scales as coatings. Moreover, in developing coatings for copper alloy liners, it is especially important that the coating be deposited by a commercially viable processing method, such as a thermal spray technique, to reduce cost. Recent studies have demonstrated that vacuum plasma sprayed Cu-26%Cr overlay coated GRCop-84 (Cu-8at.%Cr-4%Nb) copper alloy substrates form blisters in a high heat flux H<sub>2</sub>/O<sub>2</sub> combustion flame (Ref. 31). Further research has shown that while the oxidation resistance of the Cu-Cr alloys increase with increasing Cr content, their oxidation behavior remains essentially identical when 40%  $\leq$  Cr  $\leq$  55% (Ref. 32).

Early research by Nishimura (Ref. 5) has demonstrated that the oxidation resistance of Cu-Al alloys improves significantly with increasing Al content with the oxidation of Cu-Al being relatively insignificant when the Al content increases above 5%. Later research on Cu-Al alloys also confirmed these early observations (Refs. 33 to 40). Limited data published by Nishimura (Ref. 5)] on Cu-0.25-1.0%Cr-8-10%Al alloys showed that the oxidation resistance of these alloys, while excellent, was essentially independent of Al content.

Based on Nishimura's early research (Ref. 5), it is intriguing to pose the question: How will Al addition to Cu-Cr alloys change its oxidation behavior? It has been shown that Al and Cr act synergistically in MCrAl coatings, where M is either Co, Fe or Ni, resulting in the formation of a continuous, thermodynamically stable, protective Al<sub>2</sub>O<sub>3</sub> external scale at lower values of Al of 5% than in binary M-Al alloys, where Al  $\geq$  17% for the formation of the alumina scale (Ref. 41). Unlike the MCrAl alloys, where both Al and Cr are in solid solution to a significant extent in the Co, Fe or Ni matrix, the binary phase Cu-Cr and Cu-Al phase diagrams suggest that there is comparatively small dissolution of Cr in Cu while Al dissolves up to 10% in Cu (Ref. 27). Similarly, the Cu-Cr-Al ternary phase diagram shows that the solubility of Al in the  $\alpha$ -Cr and  $\alpha$ -Cu phases is relatively small in Cu-Cr-Al alloys containing smaller amounts of Al but increases with increasing Al content in the two phase  $\alpha$ -Cr/ $\alpha$ -Cu region (Refs. 42 and 43). This raises the question as to whether the observed synergism between Al and Cr in the MCrAl alloys in forming a protective alumina scale is also applicable to the Cu-Cr-Al system. Recently, Niu et al. (Refs. 44 and 45) conducted limited studies on the oxidation behavior of Cu-2 to 4 (at.%)Al and Cu-4 to 8 (at.%)Cr-2 to 4%Al alloys at 1073 K and reported the formation of an outer CuO external scale and an Al<sub>2</sub>O<sub>3</sub> scale at the interface with the unoxidized matrix with a mixture of CuO and (Cr,Al)<sub>2</sub>O<sub>3</sub> transition subsurface layer lying in between the external and innermost scales. It was observed that the continuity of the subsurface Al<sub>2</sub>O<sub>3</sub> alumina scale depended on the amount of Cr present in the alloy although it was observed in all the Cr containing alloys. A major problem with this and other studies is that the time for oxidation was typically 24 h, which maybe too short to establish steady-state oxidation behavior. Recently, it has been demonstrated that a Cu-23%Cr-5%Al coating developed for rocket engine applications provided excellent protection to the Cu-8 at.%Cr-4%Nb copper alloy substrate (Ref. 46).

The present two part paper compares the oxidation behavior of as-cast Cu-17%Cr and Cu-17%Cr-5%Al alloys with the objective of understanding the role of Al in influencing oxidation behavior. An examination of the phase diagrams shows that these are two phase alloys containing  $\alpha$ -Cr and  $\alpha$ -Cu (Refs. 26, 27, 42, and 43). In this regard, the key question to be answered is: Does Al addition to the Cu-17%Cr base alloy change the nature of the oxidation kinetics? The addition of 5% Al to the Cu-Cr composition was governed by earlier observations on MCrAl alloys that this is the minimum amount of Al required to form a protective alumina scale (Ref. 41). Thus, a second objective of this paper is to determine if the scale composition and microstructural characteristics are significantly altered by this amount of Al addition. There appears to be no previous research on the oxidation behavior of Cu-17%Cr-5%Al. The first part discusses the kinetics of the oxidation behavior of the two alloys while details of the scale compositions and microstructures are presented in the second part.

---

<sup>1</sup>All compositions reported in this paper are in wt% unless otherwise noted.

## 2. Experimental Procedures

The Cu-17%Cr and Cu-17%Cr-5%Al alloys were prepared by arc-melting chunks of high purity Al, Cr and Cu metals. These metals were carefully weighed in the appropriate amounts for the formulation of the correct composition and each charge was melted in an arc-melter under flowing argon. Care was taken in the melting procedures to ensure that each alloy preparation was remelted and flipped several times in the arc melting furnace to homogenize the composition of the melt before casting it into a button. Each button was then re-melted and drop cast into cylindrical copper molds to produce castings with the dimensions of the cylindrical region below the hot top approximately 13 mm diameter and 50 mm long. The alloys were homogenized annealed at 1223 K for 24 h under flowing argon to minimize elemental segregation. Figures 1(a) and (b) show the optical microstructures of the Cu-17%Cr and Cu-17%Cr-5%Al alloys, respectively, which essentially confirm that the alloys consist of two phases. Table 1 gives the composition of the two alloys, where the main elements were determined by the inductive coupled plasma (ICP) technique. Oxygen and nitrogen were determined by the inert gas fusion technique. In the case of the Cu-17%Cr-5%Al alloy, it was found necessary to conduct several measurements in order to minimize the effect of large segregated  $\alpha$ -Cr particles on the results, where the weighted average from three measurements are reported in Table 1.

TABLE 1.—COMPOSITIONS OF THE AS-CAST AND HEAT TREATED ALLOYS WITH  
NOMINAL COMPOSITIONS OF Cu-17%Cr AND Cu-17%Cr-5%Al IN wt. %

Nominal composition	Al	Cr	Cu	Fe	N	O	Remarks
Cu-17%Cr	0.05	15.6	84.2	0.0050	0.0003	0.0700	Readings from one specimen
Cu-17%Cr-5%Al	4.78	17.8	77.4	0.0013	0.0002	0.0048	Weighted average of three large pieces (> 400 mg)

Oxidation disk specimens 12.7 mm in diameter and 2 mm thick were sliced from the cylindrical portions of each casting by wire electrodischarge machining (EDM). Although a number of specimens were sliced from the ingots, it was observed that many had shrinkage porosity thereby limiting the number of good specimens available for the oxidation tests. A 1.5 mm diameter hole was machined in each specimen about 1.5 mm from the edge to allow it to hang from Pt wires in the furnace during oxidation. The two faces of each specimen were polished to a final finish on 600 grit SiC paper to remove the EDM damaged layers and ultrasonically cleansed in ethanol prior to oxidation. Isothermal oxidation was conducted in a thermogravimetric analyzer (TGA) fitted with a Cahn-1000 microbalance, where the change in weight of the specimen was periodically recorded as a function of time by a computerized data acquisition system. The oxidation tests were conducted between 773 and 1173 K for 100 h under dry flowing oxygen at 0.1 MPa, where the flow rate of the gas was 100 standard ccm. In the case of the Cu-17%Cr specimens, tests were conducted at absolute temperatures, T, between 773 and 973 K since there were insufficient good specimens to conduct tests at 1073 and 1173 K.

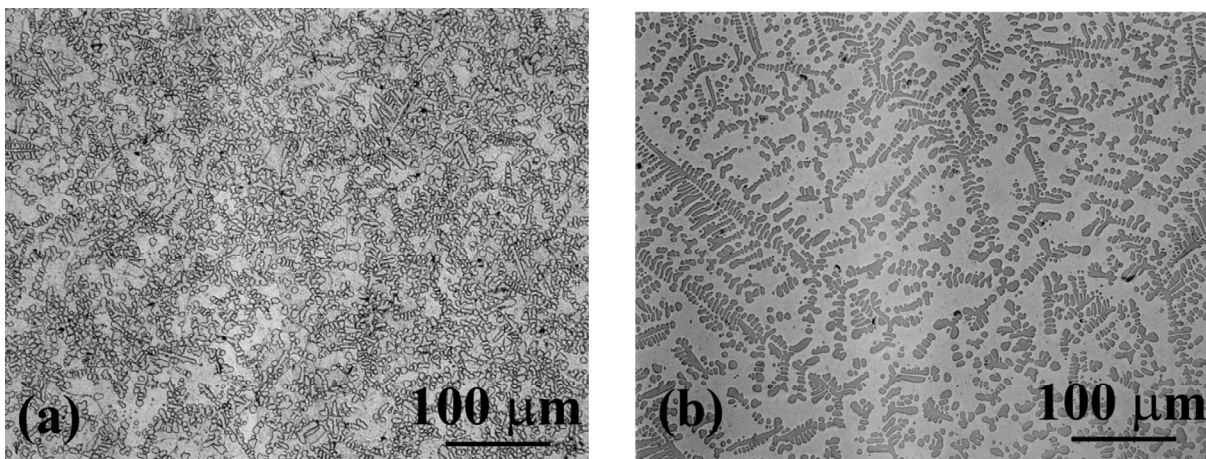


Figure 1.— Optical microstructures of as-cast alloys. (a) Cu-17%Cr. (b) Cu-17%Cr-5%Al.

### 3. Results

#### 3.1 Comparison of Weight Change Data

Figure 2(a) and (b) compare the TGA specific weight change,  $\delta W/A$ , where  $\delta W$  is the change in weight of the specimen and  $A$  is the exposed area for oxidation,<sup>2</sup> as a function of time,  $t$ , for Cu-17% Cr and Cu-17%Cr-5%Al tested between 773 and 1173 K, respectively.<sup>3</sup> The specific weight change is significantly larger for Cu-17%Cr compared to that for Cu-17%Cr-5%Al with the rate of oxidation decreasing with increasing time. In comparison, the Cu-17%Cr-5%Al alloy exhibits a very small or negligible weight change almost independent of time after a very short transient region in the temperature range 773 to 973 K. A longer transient region is observed at 1073 and 1173 K (Fig. 2(b)). The extent of the transient region is better depicted in Figure 3(a) to (e), which show plots of the rate of specific weight change,  $d(\delta W/A)/dt$ , against  $t$ , for Cu-17%Cr and Cu-17%Cr-5%Al, respectively. An examination of Figure 3 reveals that the transient region for the Cu-17%Cr alloy lasts between 30 and 70 h, while that for the Cu-17%Cr-5%Al typically lasts less than 5 h for temperatures less than 1173 K; the transient region lasts for about 15 h at 1173 K. A distinct advantage of showing these rate change plots over the representation shown in Figure 2 is that the steady-state oxidation regime can be clearly distinguished from the transient oxidation region thereby permitting an accurate and unbiased determination of the rate constants for oxidation irrespective of the nature of the oxidation kinetics.

Figures 2 and 3 clearly demonstrate that a 5% Al addition to the Cu-17%Cr base composition significantly increases its oxidation resistance. Figure 4 also confirms this remarkable improvement in oxidation behavior, where the specific weight change data for the Cu-17%Cr-5%Al alloy determined at 1173 K is significantly lower than that for the Cu-17%Cr alloy measured at 773 K. Thus, the addition of this amount of Al results in at least a 400 K improvement in the temperature capabilities of the new alloy over Cu-17%Cr.

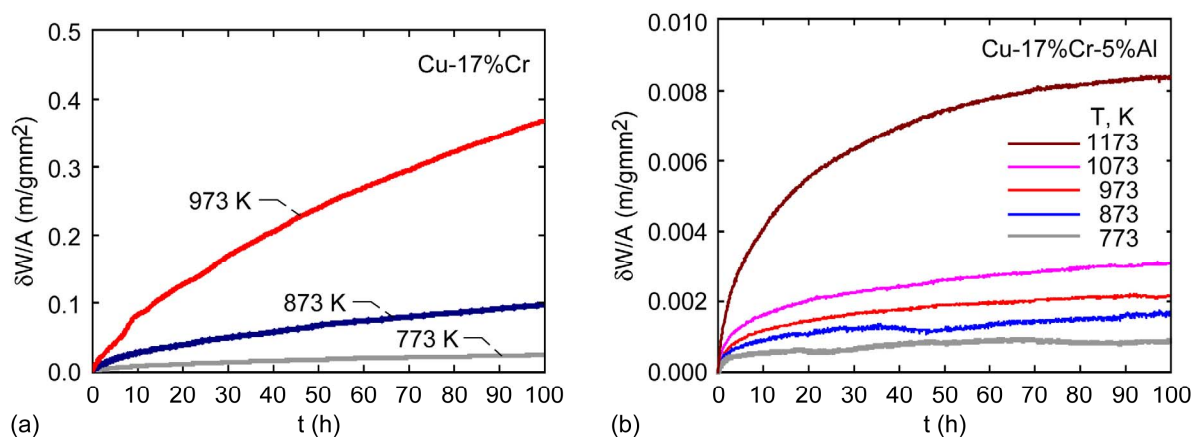


Figure 2.—Specific weight change versus time plots at temperatures ( $T$ ) between 773 and 1173 K.  
(a) Cu-17%Cr. (b) Cu-17%Cr-5%Al.

<sup>2</sup>This magnitude of  $A$  includes the sum of the areas of the two faces, the area of the outer edge of the specimen and the area of the specimen edge at the hole.

<sup>3</sup>It is noted that  $t = 0$  in this paper corresponds to the time at which the test temperature is attained.



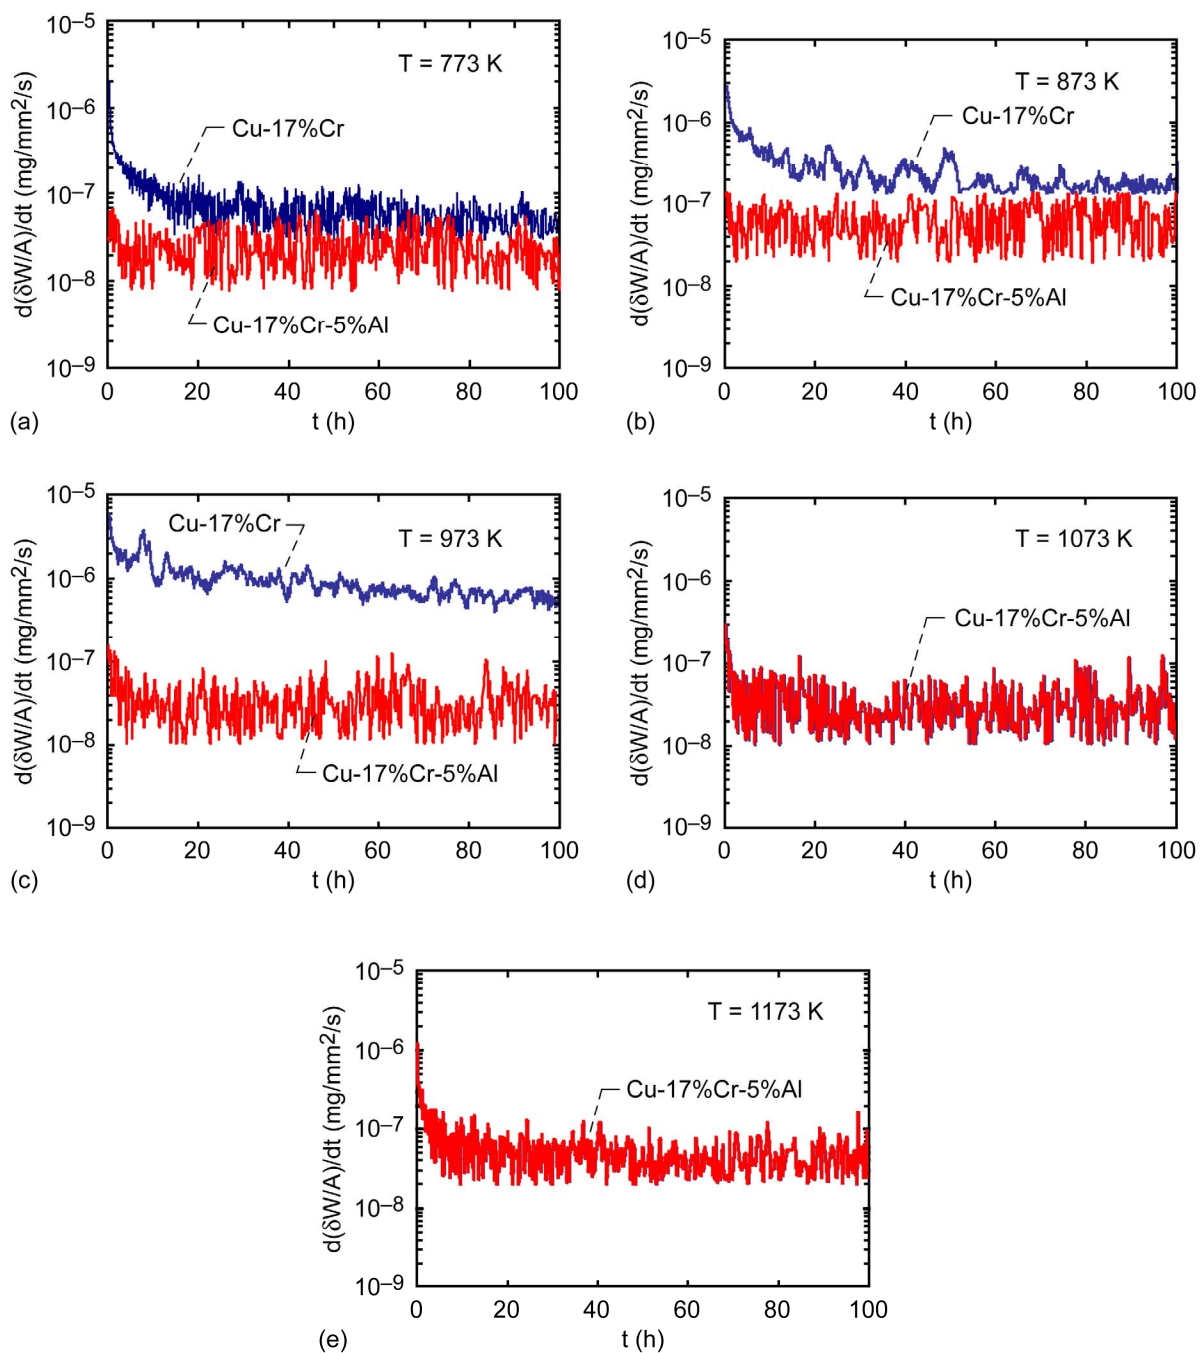


Figure 3.—Variation of the rate of the specific weight change with time for Cu-17%Cr and Cu-17%Cr-5%Al at different temperatures ( $T$ ). (a) 773 K. (b) 873 K. (c) 973 K. (d) 1073 K. (e) 1173 K.

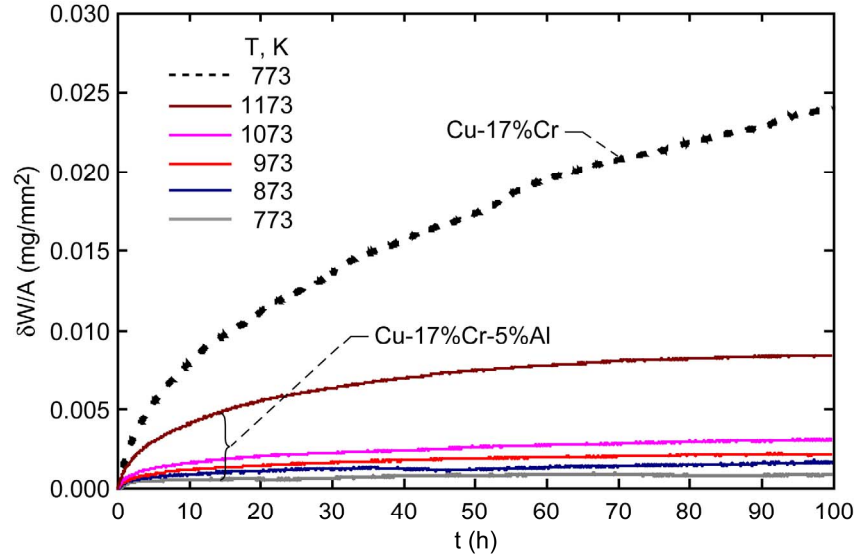


Figure 4.—Comparison of the specific weight change data for Cu-17%Cr determined at 773 K with those for Cu-17%Cr-5%Al determined between temperatures (T) 773 and 1173 K, demonstrating the superior oxidation behavior of the Al-containing alloy.

### 3.2 Oxidation Rate Equations

Although the parabolic rate equation is commonly used to describe the  $\delta W/A - t$  relationships for many materials undergoing oxidation, it is well documented that other relationships can be important to describe the oxidation behavior of many alloys (Refs. 14 and 15). Assuming that the steady-state region of oxidation can be described by a generalized power-law relationship given by Eq. (1)

$$(\delta W/A)^m = k_m t \quad (1)$$

where  $m$  is a constant and  $k_m$ <sup>4</sup> is the appropriate oxidation rate constant, the magnitudes of  $k_m$  and  $m$  can be determined from double logarithmic plots of  $\delta W/A$  and  $t$  without any *a priori* bias in the analysis (Ref. 14). Figure 5(a) to (e) show double logarithmic plots of  $\delta W/A$  and  $t$  for Cu-17%Cr and Cu-17%Cr-5%Al between 773 and 1173 K. The figures also show linear regression lines fitted to the nontransient data.

Table 2 lists the values of  $k_m$ ,  $m$  and the corresponding coefficients of determination,  $R_d^2$ , for the two alloys as a function of temperature describing these regression fits. The time range within which the data lie are also indicated. It is worth noting that the range of the steady-state oxidation regimes were defined to be consistent with Figure 3(a) to (e) in this regression analyses so that care was taken to ensure that the  $\delta W/A$  and  $t$  data pairs considered in the regression analyses were within this region. In the case of Cu-17%Cr-5%Al, the parabolic rate constants,  $k_p$ , were determined by linear regression analyses of the transient data within the first 15 h. The magnitudes of  $k_p$  for the oxidation of both Cu-17%Cr and Cu-17%Cr-5%Al were determined from  $(\delta W/A)^2 - t$  data pairs (i.e.,  $m = 2.0$ ) by assuming that the intercepts are zero. On the other hand, the magnitudes of quartic rate constant,  $k_q$ , were determined by linearly regressing  $\log(\delta W/A) - \log t$  data pairs lying in the time range shown in Table 2.

<sup>4</sup>In this paper, the subscripts  $m$ ,  $p$  and  $q$  denote generic, parabolic and quartic relationships, respectively.

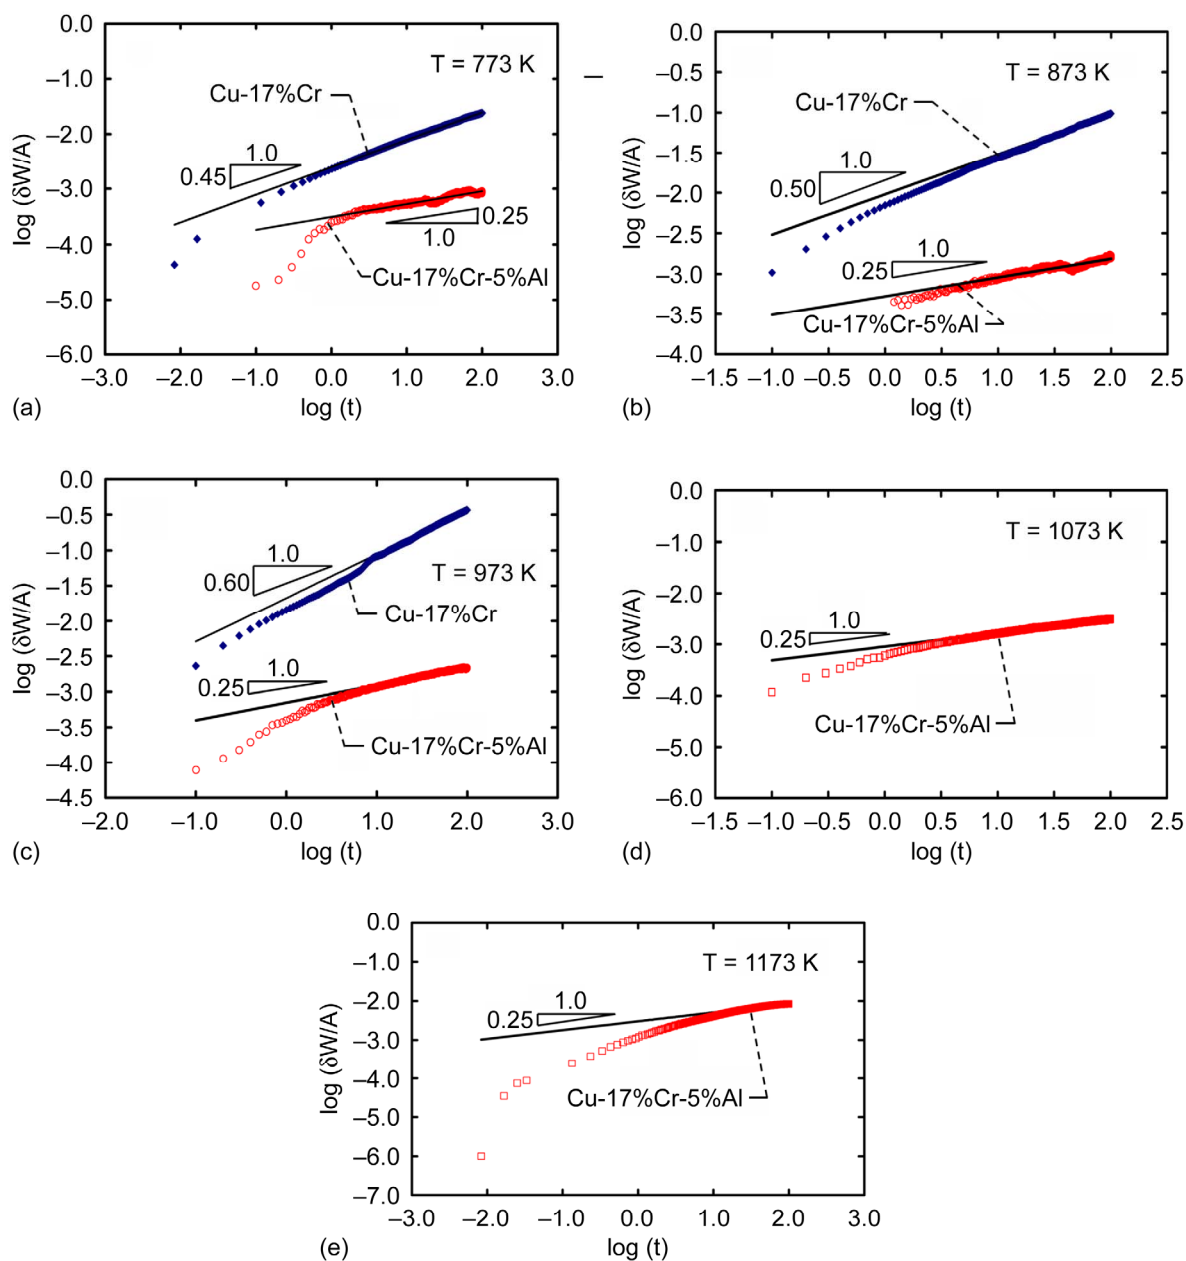


Figure 5.—Double logarithmic plots showing the variation of the specific weight change with time for Cu-17%Cr and Cu-17%Cr-5%Al at different temperatures (T). (a) 773 K. (b) 873 K. (c) 973 K. (d) 1073 K. (e) 1173 K.

TABLE 2.—MAGNITUDES OF THE OXIDATION RATE CONSTANTS FOR Cu-17%Cr AND Cu-17%Cr-5%Al ALLOYS BETWEEN 773 AND 1173 K

	773 K			873 K			973 K			1073 K			1173 K		
	$m$	$k_m$	$R_d^2$	$m$	$k_m$	$R_d^2$	$m$	$k_m$	$R_d^2$	$m$	$k_m$	$R_d^2$	$m$	$k_m$	$R_d^2$
Cu-17Cr (mg <sup>2</sup> /mm <sup>4</sup> /s) (parabolic) (time range analyzed)	2.0	$1.7 \times 10^{-9}$ (39 to 100 h)	0.999	2.0	$2.6 \times 10^{-8}$ (49.6 to 100 h)	0.998	2.0	$3.5 \times 10^{-7}$ (60 to 100 h)	0.992	---	-----	-----	---	-----	-----
Cu-17Cr-5Al (mg <sup>2</sup> /mm <sup>4</sup> /s) (parabolic) (time range analyzed)	2.0	$1.6 \times 10^{-11}$ (0 to 1.9 h)	0.981	2.0	$2.4 \times 10^{-11}$ (0 to 11 h)	0.982	2.0	$3.7 \times 10^{-11}$ (0 to 15 h)	0.987	2.0	$7.0 \times 10^{-11}$ (0 to 15 h)	0.987	2.0	$4.6 \times 10^{-10}$ (0 to 15 h)	0.999
Cu-17Cr-5Al (mg <sup>4</sup> /mm <sup>8</sup> /s) (quartic) (time range analyzed)	4.3	$2.4 \times 10^{-19}$ (2.2 to 100 h)	0.885	4.3	$2.4 \times 10^{-18}$ (15 to 100 h)	0.810	4.4	$5.6 \times 10^{-17}$ (19.6 to 100 h)	0.983	3.7	$1.4 \times 10^{-15}$ (22 to 100 h)	0.994	4.4	$2.2 \times 10^{-15}$ (30 to 100 h)	0.972

Note: Units for  $k_m$  are (mg/mm<sup>2</sup>)<sup>m</sup>.

An examination of Figure 5(a) to (e) and Table 2 reveals that the steady-state oxidation behavior of Cu-17%Cr is best described by a parabolic law, whereas the oxidation kinetics for the Cu-17%Cr-5%Al alloy is better represented by a quartic law. The regression equations fit the steady-state experimental data extremely well (Fig. 2(a) to (e)). Interestingly, the parabolic equations also represent the transient data fairly well in the case of the Cu-17%Cr-5%Al alloy. The parabolic oxidation kinetics observed for Cu-17%Cr in this investigation are consistent with similar observations for other Cu-Cr alloys (Refs. 20 and 21). Although no previous data appear to exist for the Cu-17%Cr-5%Al, the observation of quartic oxidation kinetics in the steady-state oxidation regime in the temperature range 773 to 1173 K is self consistent. The transition from a parabolic relationship in the transient oxidation region to quartic rate kinetics in the steady-state oxidation regime between 973 and 1173 K suggests a change in the nature of the dominant oxidation mechanism presumably due to the effect of Al.

Using the constants given in Table 2, it is evident from Figure 6(a) to (e) that the regressed equations fit the experimental data reasonably well for both alloys thereby confirming the general validity of these constants. In the case of Cu-17%Cr, the parabolic relationship with  $m = 2$  does not describe the  $\delta W/A$  data at 973 K as well as  $m = 1.6$  especially in the transient regions of the plot. The quartic relationship describes the experimental observations on Cu-17%Cr-5%Al at 773 and 873 K throughout the entire time scale, and the latter portions of the curves between 973 and 1173 K, fairly well. However, the parabolic relationship better represents the initial set of data at the higher temperatures. Although it is unclear why the quartic relationship represents the data for Cu-17%Cr-5%Al better than the parabolic rate equation, it will be demonstrated later in section 4.2 that the specific weight change data are better described by a logarithmic relationship.

### 3.3 Activation Energies for Oxidation

Figure 7 shows the variation of the rate constants,  $k_p$  and  $k_q$ , for Cu-17%Cr and Cu-17%Cr-5%Al, respectively, as a function of the inverse of the absolute temperature in an Arrhenius plot. The activation energy for oxidation,  $Q$ , of Cu-17%Cr, as determined from the slope of the linear regression line through the datum points, is  $165.9 \pm 9.4 \text{ kJ mol}^{-1}$  ( $R_d^2 = 0.997$ ), where  $R_d^2$  is the coefficient of determination and the errors represent the standard deviations about the regressed mean values, which is in excellent agreement with the value of  $163 \text{ kJ mol}^{-1}$  reported for Cu-29.5%Cr (35 vol.% Cr) (Ref. 21). These values are comparable to the value of  $172 \text{ kJ mol}^{-1}$  reported for the oxidation of high purity Cu oxidized in air or oxygen under 0.1 MPa pressure between 1073 and 1173 K, which was attributed to the outward lattice diffusion of Cu<sup>+</sup> in Cu<sub>2</sub>O (Ref. 22). It should be noted that the experimental activation energies for lattice

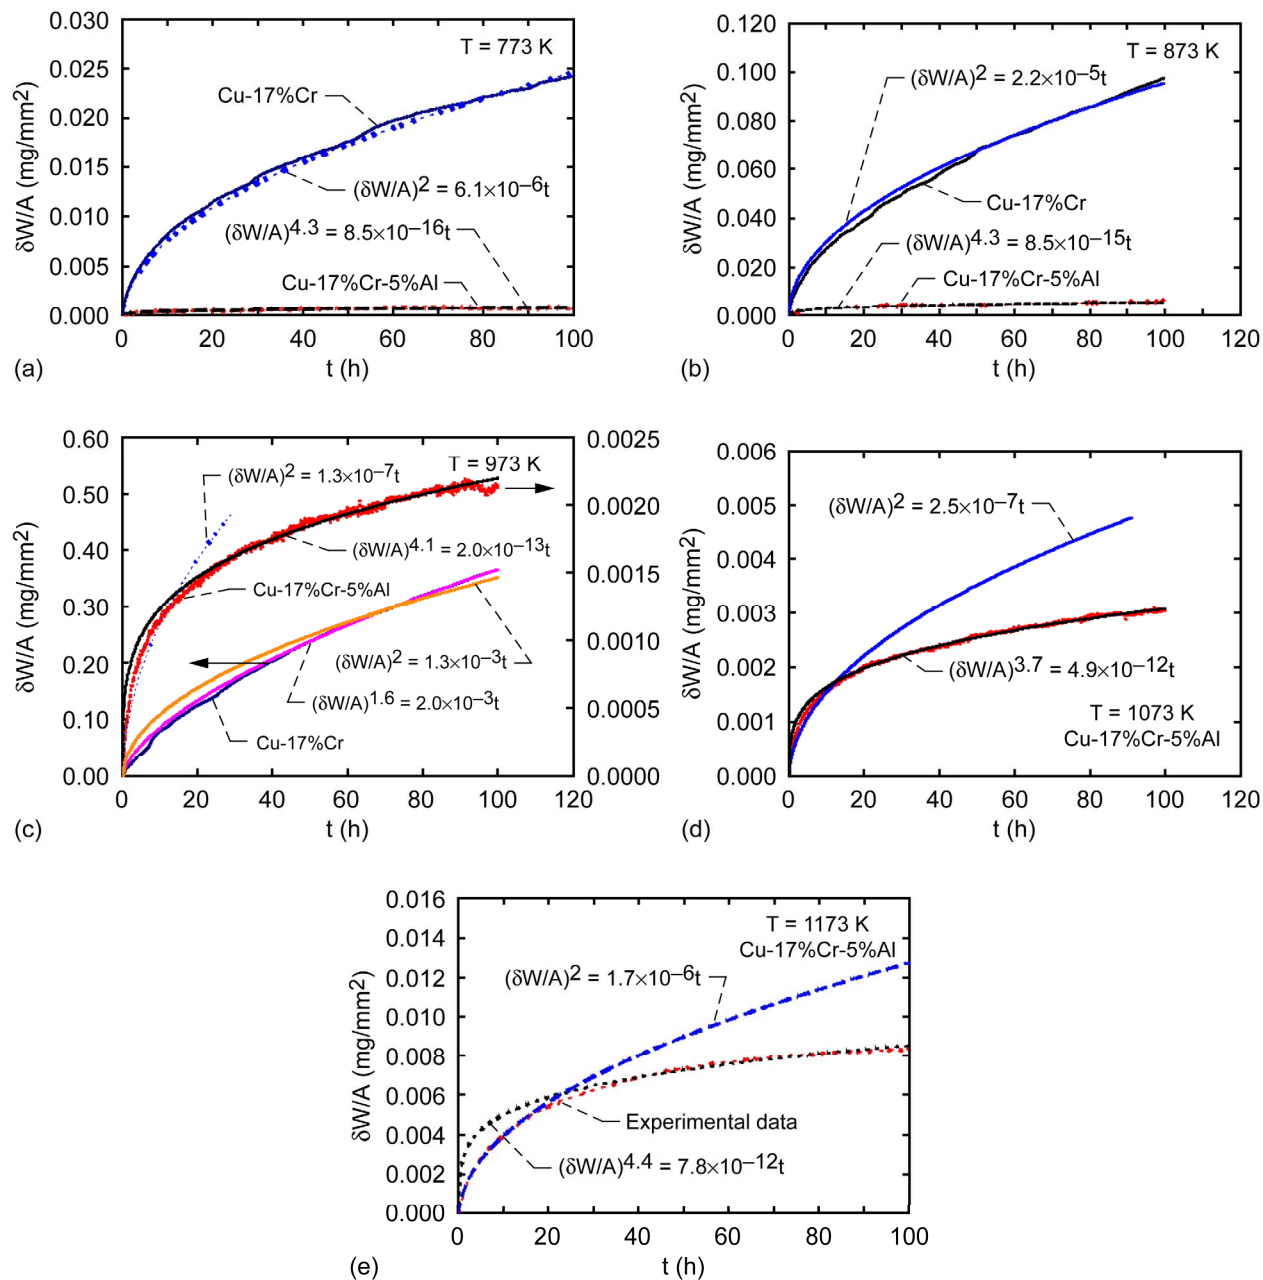


Figure 6.—Comparison of the regression equations with experimental data for Cu-17%Cr and Cu-17%Cr-5%Al at different temperatures (T). (a) 773 K. (b) 873 K. (c) 973 K. (d) 1073 K. (e) 1173 K.

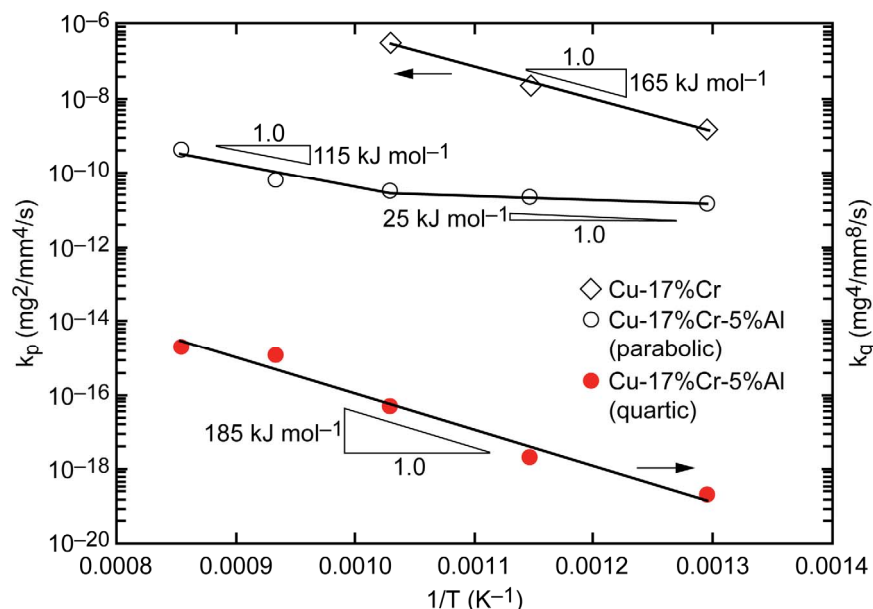


Figure 7.—Arrhenius plot showing the temperature dependence of the parabolic and quartic rate constants for Cu-17%Cr and Cu-17%Cr-5%Al.

diffusion of  $\text{Cu}^+$  and  $\text{O}^{2-}$  in  $\text{Cu}_2\text{O}$  reported in the literature are about 150 and 165  $\text{kJ mol}^{-1}$ , respectively, which were considered to be an insignificant difference by the authors (Ref. 46).

In the case of Cu-17%Cr-5%Al, the experimental values of  $Q$  in the parabolic regime corresponding to the initial stages of oxidation were  $24.9 \pm 2.6 \text{ kJ mol}^{-1}$  ( $R_d^2 = 0.989$ ) between 773 and 973 K and increased to  $114.6 \pm 40.0 \text{ kJ mol}^{-1}$  ( $R_d^2 = 0.896$ ) above 973 K. For comparison, Tylecote (Ref. 9) reported a value of 39  $\text{kJ mol}^{-1}$  for oxidation of Cu between 573 and 773 K. The present observation of 24.9  $\text{kJ mol}^{-1}$  is in excellent agreement with a value of 27  $\text{kJ mol}^{-1}$  observed in the oxidation of 6N purity Cu in the temperature range 873 to 1023 K, and 38  $\text{kJ mol}^{-1}$  in the oxidation of 2N purity Cu between 873 and 1223 K, corresponding to the oxidation of  $\text{Cu}_2\text{O}$  to CuO (Ref. 47). However, much higher values of  $Q = 186.5 \pm 17.2 \text{ kJ mol}^{-1}$  ( $R_d^2 = 0.975$ ) independent of temperature were observed for the alloy in the steady-state quartic oxidation regime.

## 4. Discussion

### 4.1 Comparison with Literature Data

Figure 8 compares the temperature dependence of  $k_p$  determined for Cu-17%Cr and Cu-17%Cr-5%Al in the present investigation with those reported for Cu (Refs. 6,9,10,16,18 to 22, and 44), Cu-Al (Refs. 44, 45, and 49), Cu-Cr (Refs. 20 and 21) and Cu-7(at.%)Cr-2%Al (Refs. 44 and 45) alloys.<sup>5</sup> The typical magnitudes of  $k_p$  for alumina and chromia formers are also indicated for comparison (Ref. 50). It should be noted that Cu-10%Al was a two phase alloy since it corresponds to the two phase region of the binary phase diagram (Refs. 26 and 27).

An examination of Figure 8 reveals two oxidation regimes for Cu. At temperatures exceeding 850 K, the temperature dependence of  $k_p$  is steeper than the trend in the data below this temperature. These two types of behavior have been attributed to oxidation mechanisms involving the lattice and grain boundary

<sup>5</sup>The parabolic rate constants shown in Figure 8 were determined from relatively short term tests lasting less than 24 h in most of the investigations. As shown in this investigation, oxidation to longer times can result in a change in the oxidation kinetics especially in Cu alloyed with Al.

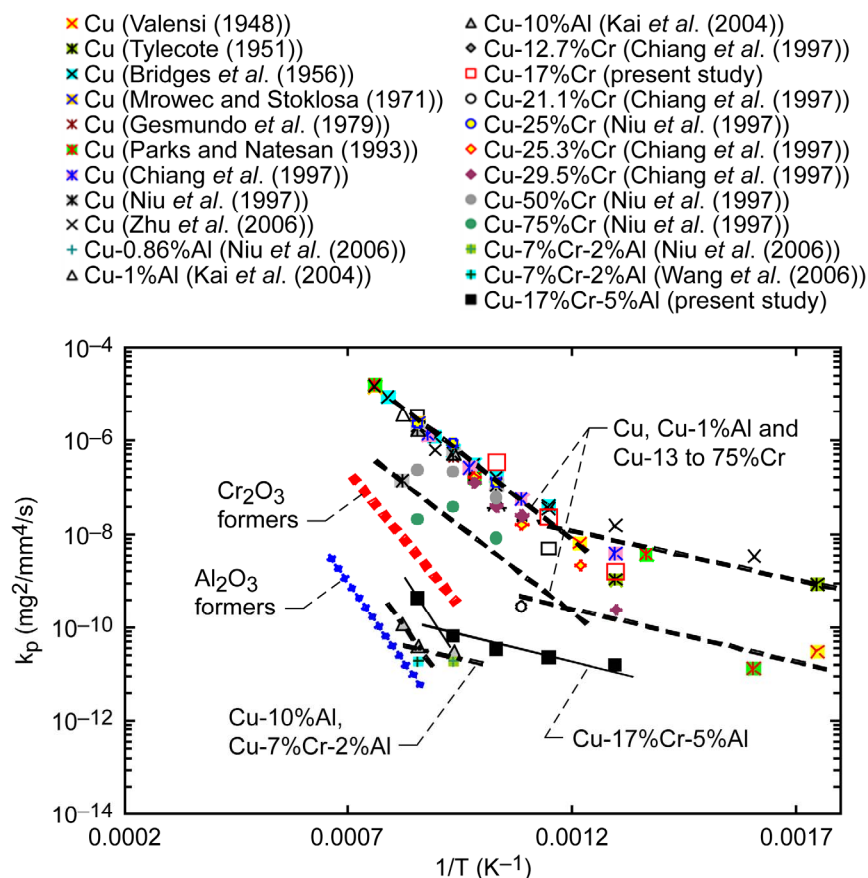


Figure 8.—Arrhenius plot comparing the parabolic rate constants for Cu (refs. 6, 9, 10, 16, 18, 19, 20, 21, 22, and 44), Cu-Al (44, 45, and 49), Cu-Cr (refs. 20 and 21), and (at.%) Cu-7%Cr-2%Al (44 and 45) reported in the literature with data obtained for Cu-17%Cr and Cu-17%Cr-5%Al in the present study.

diffusion of  $\text{Cu}^+$  in  $\text{Cu}_2\text{O}$  at high and low temperatures, respectively (Ref. 22). The addition of 1%Al appears to have no significant effect on the magnitudes of  $k_p$  but alloys containing 10%Al show a significant decrease in its value by about four orders of magnitude. In contrast, the addition of up to 50% Cr to Cu shows no significant decrease in the magnitude of  $k_p$  above the scatter in the data although the lattice diffusion controlled mechanism appears to be dominant even at 773 K. The data for Cu-75%Cr are too few and clustered to arrive at an unambiguous conclusion on whether this amount of Cr has had any effect on the magnitude of  $k_p$ . These observations demonstrate that Cr has no significant effect on the oxidation of as-cast Cu-Cr alloys.

The magnitudes of  $k_p$  determined for Cu-17%Cr in the present investigation are in reasonable agreement with the literature data. The  $k_p$  data for Cu-17%Cr-5%Al relating to the initial stages of oxidation are in agreement with the Cu-10%Al data within a factor of two. Three important points may be noted from these observations. First, the decrease in the  $k_p$  values is almost entirely due to the addition of Al with no significant synergistic effect of Cr on the oxidation behavior of the alloy. Second, the transition temperature from grain boundary to lattice diffusion controlled oxidation appears to have increased from 850 K for pure Cu to 1073 K for both these Al containing alloys, although this observation is ambiguous due to the limited or clustered data. Third, the rate-controlling oxidation mechanisms are similar to those dominant in pure Cu during the early stage of oxidation but transitions to a different mechanism resulting in the observed quartic relationship during the later stages of oxidation. Clearly, Wagner's parabolic model is not applicable to the secondary stage of oxidation of Cu-17%Cr-5%Al.



Figure 9 compares the activation energies for oxidation of pure Cu (Refs. 6, 9, 10, 16, 19 to 22), Cu-Al (Ref. 49), Cu-29.5%Cr (Ref. 21) with those observed for Cu-17%Cr and Cu-17%Cr-5%Al in the present investigation.<sup>6</sup> The activation energies for diffusion of  $\text{Cu}^+$  and  $\text{O}^{2-}$  in  $\text{Cu}_2\text{O}$ , which were reported to be 150 and 165  $\text{kJ mol}^{-1}$ , respectively (Ref. 47), are indicated in the figure. It is now well established that the oxidation of Cu is controlled by the outward diffusion of Cu in the alloy to the metal-oxide interface and in the oxide scale (Refs. 14, 15, 19, and 22). An examination of Figure 9 reveals that the experimental activation energies for Cu are clustered about three bands. Low values of  $Q \approx 40 \text{ kJ mol}^{-1}$  have been attributed to the diffusion of  $\text{Cu}^+$  along the grain boundaries of  $\text{Cu}_2\text{O}$  (Ref. 22). However, it should be noted that theoretical calculations of the activation energy for copper vacancy migration in  $\text{Cu}_2\text{O}$  at room temperature predict a value of about 25  $\text{kJ mol}^{-1}$  (Ref. 51). Intermediate values of  $Q \approx 75$  to 125  $\text{kJ mol}^{-1}$  have been attributed to either a mixture of grain boundary and lattice diffusion in  $\text{Cu}_2\text{O}$  (Ref. 22) or diffusion of  $\text{Cu}^+$  in  $\text{Cu}_2\text{O}$  under conditions where only a single  $\text{Cu}_2\text{O}$  scale is stable (Refs. 16 and 19). Since CuO is stable only at high oxidation pressures, scale compositions at low partial pressures of oxygen consist predominantly of  $\text{Cu}_2\text{O}$  (Refs. 10 and 19). However, if oxidation occurs under conditions where CuO is stable, then the scale consists of an outer layer of CuO and an inner layer of  $\text{Cu}_2\text{O}$  leading to higher observed values of  $Q$  between 150 and 175  $\text{kJ mol}^{-1}$ . These values compare fairly well with the reported values of activation energies for diffusion of  $\text{Cu}^+$  and  $\text{O}^{2-}$  in  $\text{Cu}_2\text{O}$  (Ref. 46), although it has been suggested that the lattice diffusion of  $\text{Cu}^+$  through the  $\text{Cu}_2\text{O}$  is the rate determining step for oxidation (Ref. 22).

It is evident from Figure 9 that the activation energy decreases from about 160  $\text{kJ mol}^{-1}$  for Cu-1%Al to 90  $\text{kJ mol}^{-1}$  for Cu-10%Al (Ref. 49). Correspondingly, the compositions of the scales formed on the Cu-1%Al and Cu-10%Al were CuO/ $\text{Cu}_2\text{O}$  and mostly  $\text{Al}_2\text{O}_3$ , respectively. The observed scale composition for Cu-1%Al is similar to that for pure Cu and consistent with the activation energies for oxidation observed in Cu for double scale formation (Fig. 10). However, the observation of mainly  $\text{Al}_2\text{O}_3$  in the scale for Cu-10%Al for which  $Q \approx 90 \text{ kJ mol}^{-1}$  is inconsistent with the typical values of  $Q \approx 240 \text{ kJ mol}^{-1}$  for alumina forming Ni-based superalloys reported in the literature (Ref. 52). It is also noted that the activation energies for cation grain boundary and lattice diffusion in alumina are 477 and 419  $\text{kJ mol}^{-1}$ , respectively, whereas those for anion grain boundary and lattice diffusion are 636 and 380  $\text{kJ mol}^{-1}$ , respectively (Ref. 53). Interestingly, the addition of Cr to Cu has no significant effect on the magnitude of the activation energy, which is similar to those observed for double layer scale formation in Cu.

The activation energies for Cu-17%Cr-5%Al representative of the initial stages of oxidation increase from about 25  $\text{kJ mol}^{-1}$  between 773 and 973 K to about 120  $\text{kJ mol}^{-1}$  between 1073 and 1173 K (Fig. 9). Based on the observations on pure Cu, it would appear that the low value of 25  $\text{kJ mol}^{-1}$  is due to grain boundary diffusion in  $\text{Cu}_2\text{O}$  at the lower temperatures and lattice diffusion in  $\text{Cu}_2\text{O}$ . It is reasonable to expect that the faster diffusion of Cu compared to Al and Cr would support the formation of an initial  $\text{Cu}_2\text{O}$  layer, which is consistent with the microstructural compositions of the oxide scale discussed in part II of this paper. The values of  $Q$  are independent of temperature and equal to about 185  $\text{kJ mol}^{-1}$  in the quartic oxidation regime. It has been suggested that the activation energy for diffusion of Al in Cu is 165  $\text{kJ mol}^{-1}$  (Ref. 40). However, since the activation energy for Cu-17%Cr was observed to be about 165  $\text{kJ mol}^{-1}$ , it is ambiguous to attribute the observed value of  $Q \approx 185 \text{ kJ mol}^{-1}$  to that due to Al diffusion in the alloy. It should be noted that the experimental value of  $Q$  lies between the lowest reported value of activation energy of 155  $\text{kJ mol}^{-1}$  for the oxidation of pure Cu (Ref. 10) and 240  $\text{kJ mol}^{-1}$  for the oxidation of alumina forming alloys (Ref. 52).

---

<sup>6</sup>The terms “single” and “double” layers refer to the ideal scale morphologies consisting of either only a  $\text{Cu}_2\text{O}$  layer or a combination of an outer CuO layer over an inner  $\text{Cu}_2\text{O}$  layer, respectively.



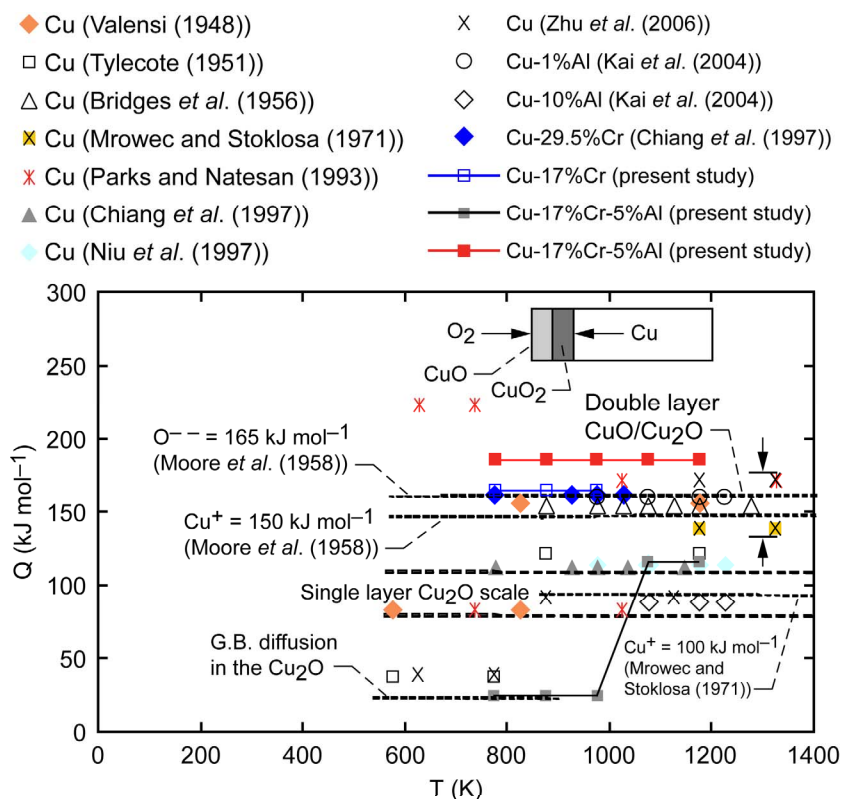


Figure 9.—Comparison of the activation energies for oxidation of pure Cu (refs. 6, 9, 10, 16, 19, 20, 21, and 22), Cu-Al (48), and Cu-29.5%Cr (21) with those for Cu-17%Cr and Cu-17%Cr-5%Al. The lower values of activation energies for oxidation of Cu-17%Cr-5%Al were determined using the parabolic relationship, whereas the higher values were determined from the quartic relationship.

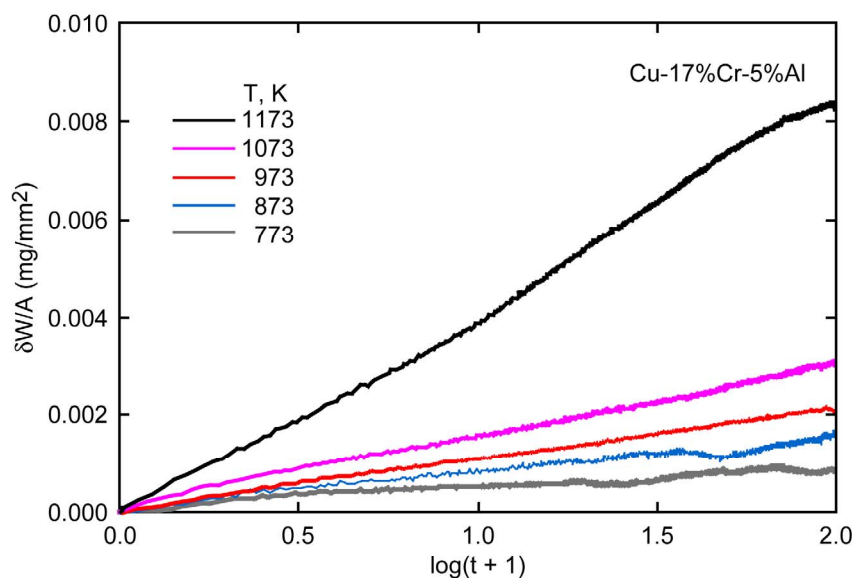


Figure 10.—Plot of the specific weight change versus  $\log(t + 1)$  at different temperatures ( $T$ ) demonstrating the applicability of the direct logarithmic relationship to describe the oxidation behavior of Cu-17%Cr-5%Al.

## 4.2 Effect of Al Addition

Thus far, the analyses of the  $(\delta W/A) - t$  data have assumed the validity of the power-law relationship given by Eq. (1). In the case of Cu-17%Cr, the parabolic relationship was shown to describe the data reasonably well over the entire time range between 773 and 973 K. In the case of Cu-17%Cr-5%Al the parabolic relationship is applicable for first 2 to 15 h depending on temperature after which a quartic relationship is obeyed. The addition of 5%Al to Cu-17%Cr resulted in a dramatic improvement in its oxidation properties (Fig. 4). An examination of Figures 2 to 4 reveals that the specific weight gain for Cu-17%Cr was greater than that for Cu-17%Cr-5%Al by factors of 17 to 27 between 773 and 973 K after 100 h. A comparison of the parabolic oxidation constants for Cu-17%Cr and Cu-17%Cr-5%Al showed that the addition of 5%Al resulted in a decrease in the magnitude of  $k_p$  by a factor of 2 to 4 in the temperature range 773 to 973 K. Since Cr had no significant effect on the oxidation of the binary as-cast Cu-Cr alloys, it must be concluded that this decrease in the magnitude of  $k_p$  is primarily due to the effect of Al.

Unlike the parabolic oxidation relationship, which has a physical basis in diffusion controlled mechanisms, such as Wagner's oxidation model (Refs. 14 and 15), the quartic relationship observed in this study is strictly empirical at present based solely on an objective and consistent data analysis. Although quartic oxidation behavior has been reported in the literature for other alloys (Refs. 14 and 15), there appears to be no physically based oxidation model at present to provide an insight into the causative nature of the oxidation process. Therefore, it is instructive to examine the degree of statistical fit of other equations reported in the literature to the present  $(\delta W/A) - t$  data for Cu-17%Cr-5%Al.

Alternative to the power-law relation Eq. (1), it is worthwhile to examine whether a logarithmic relationship would describe the  $(\delta W/A) - t$  data as well, especially since as discussed in part II of the paper, the oxide scales formed on the Cu-17%Cr-5%Al specimens were very thin. The  $(\delta W/A) - t$  data were regressed with the following logarithmic relationship to determine the regression parameters (Ref. 14):

$$(\delta W/A) = k_{\log} \log(t+1) + A \quad (2)$$

where  $k_{\log}$  and  $A$  are fitting constants. Figure 10 demonstrates that the variation of the experimentally measured values of  $(\delta W/A)$  with  $\log(t+1)$  is approximately linear and Table 3 gives the regressed magnitudes of  $k_{\log}$ ,  $A$  and  $R_d^2$ . It is evident that Eq. (2) describes the experimental data fairly well. In fact, a comparison of the regression fits to the experimental data for the logarithmic and quartic equations revealed an excellent correlation with the entire time span of the data for the former relationship at all temperatures (Fig. 11). The magnitudes of the activation energies determined from a semi-logarithmic plot of  $k_{\log}$  against  $1/T$  resulted in  $Q \approx 33 \text{ kJ mol}^{-1}$  between 773 and 1073 K and  $115 \text{ kJ mol}^{-1}$  between 1073 and 1173 K (Fig. 12). These values are similar to those determined from the parabolic rate constants.

TABLE 3.—REGRESSION COEFFICIENTS FOR Cu-17%Cr-5%Al USING THE  
DIRECT LOGARITHMIC RATE EQUATION,  $(\delta W/A) = k_{\log} \log(t+1) + A$

773 K			873 K			973 K			1073 K			1173 K		
$k_{\log}$	$A$	$R_d^2$	$k_{\log}$	$A$	$R_d^2$	$k_{\log}$	$A$	$R_d^2$	$k_{\log}$	$A$	$R_d^2$	$k_{\log}$	$A$	$R_d^2$
$3.8 \times 10^{-4}$	$1.3 \times 10^{-4}$	0.890	$6.9 \times 10^{-4}$	$1.5 \times 10^{-4}$	0.926	$1.1 \times 10^{-3}$	$7.6 \times 10^{-5}$	0.997	$1.5 \times 10^{-3}$	$6.8 \times 10^{-5}$	0.996	$4.5 \times 10^{-3}$	$-4.1 \times 10^{-4}$	0.995

The observed excellent correlation between Eq. (2) and the experimental specific weight change data (Fig. 10) is encouraging because a number of models have been proposed to describe low temperature oxidation, where the time dependent change in the thickness of a thin scale usually follows a logarithmic relationship (Refs. 14 and 15). An important point to note is that generally logarithmic rate equations describing the growth of thin scales are best suited for low temperature conditions, where the rates of

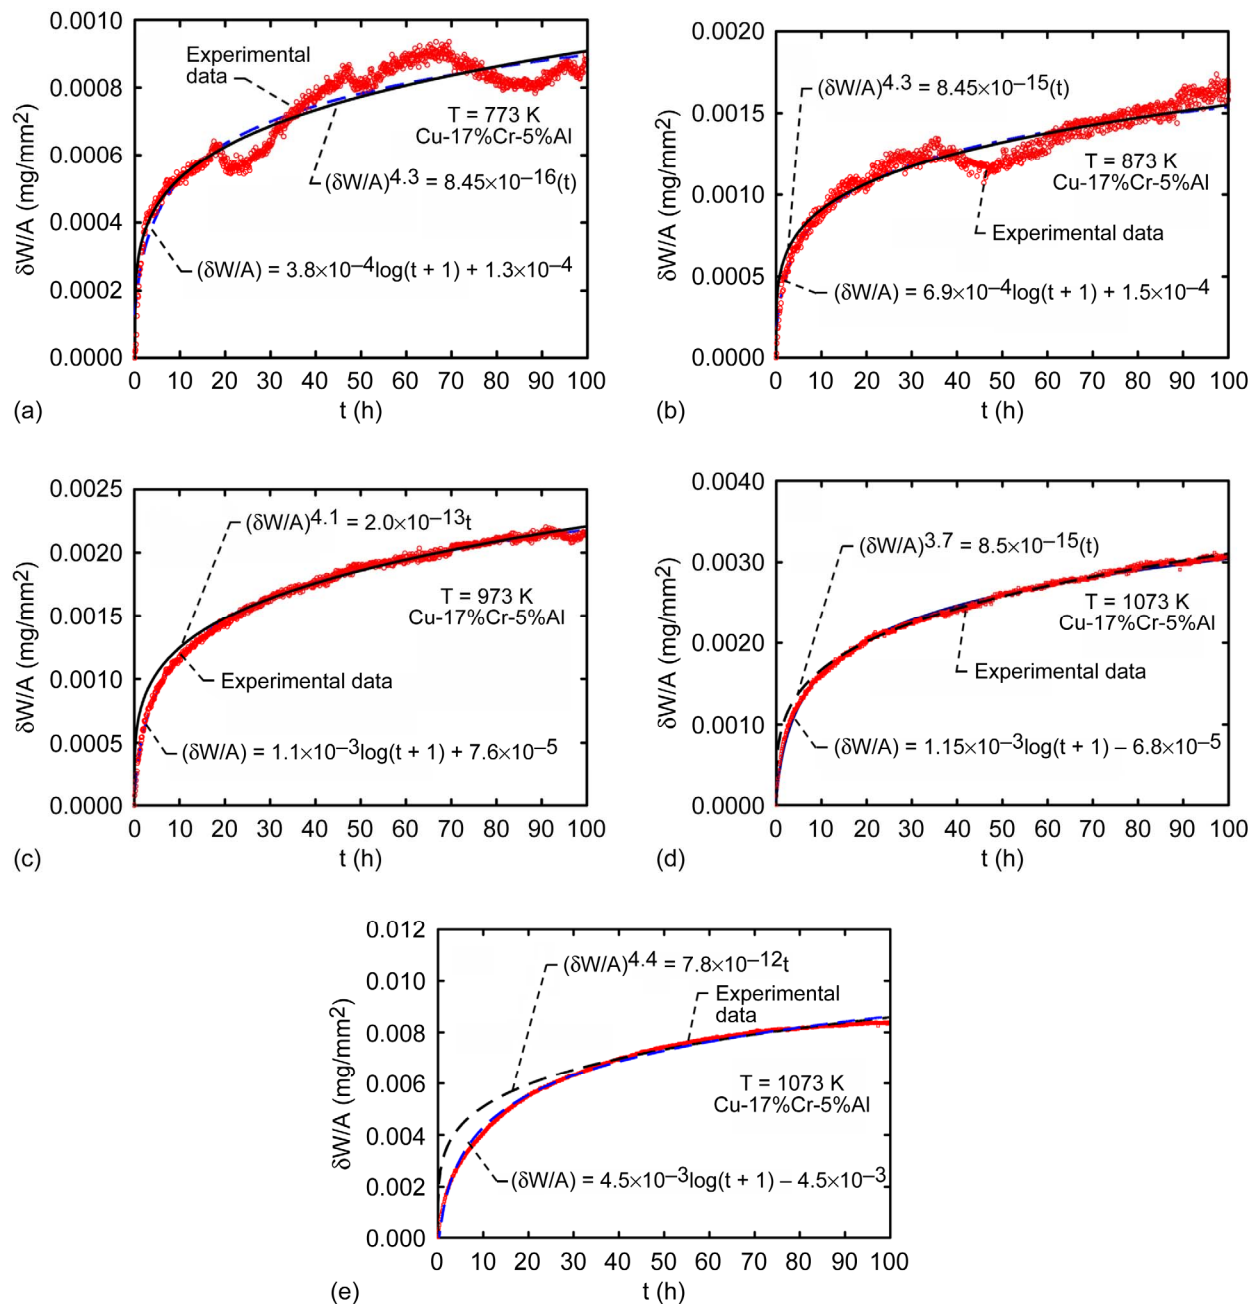


Figure 11.—Comparison of the logarithmic and quartic regression equations with the experimental data for Cu-17%Cr-5%Al at different temperatures (T). (a) 773 K. (b) 873 K. (c) 973 K. (d) 1073 K. (e) 1173 K.

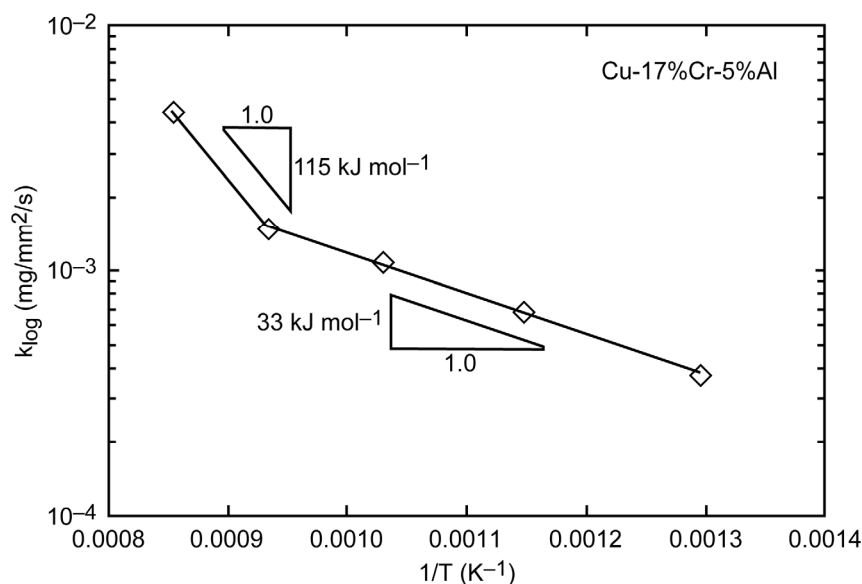


Figure 12.—Arrhenius plot of the logarithmic rate constant versus the inverse of the absolute temperature for Cu-17%Cr-5%Al.

diffusion of the reacting species are relatively small. In the present study, the test temperatures were sufficiently high to ensure higher rates of diffusion of the reacting species. This is certainly the case for the Cu-17%Cr alloy reported in this paper as well as for other Cu-Cr alloys (Refs. 20 and 21), where the parabolic rate law and the observance of thick  $\text{Cu}_2\text{O}$  and  $\text{CuO}$  scales formed a consistent picture. The fact that the addition of 5%Al to the base composition dramatically increased its oxidation resistance can be attributed to one or more factors, such as the formation of a protective oxide scale and a slower rate of diffusion of  $\text{Cu}^+$  in  $\text{Cu}_2\text{O}$  due to a change in its defect chemistry. In this connection, it is interesting to note that theoretical calculations suggest that the presence of Al in  $\text{Cu}_2\text{O}$  binds it to copper vacancies,  $V_{\text{Cu}}$ , with a binding energy of about  $320 \text{ kJ mol}^{-1}$  thereby inhibiting  $V_{\text{Cu}}$  diffusion in  $\text{Cu}_2\text{O}$  with the activation energy for the diffusion of  $V_{\text{Cu}}$  in  $\text{Cu}_2\text{O}$  calculated to be about  $25 \text{ kJ mol}^{-1}$  (Ref. 51). This theoretical value of  $25 \text{ kJ mol}^{-1}$  is in excellent agreement with the value of  $Q \approx 33 \text{ kJ mol}^{-1}$  determined in the present study using the logarithmic equation (Fig. 12). Therefore, it appears reasonable to suggest that the inhibition of  $\text{Cu}^+$  diffusion in  $\text{Cu}_2\text{O}$  by Al is the predominant mechanism governing oxidation behavior of the Cu-17%Cr-5%Al below 1073 K and the growth of a protective alumina scale above 1073 K is the dominant process.

## 5. Summary and Conclusions

The effect of 5% Al on the oxidation behavior of Cu-17%Cr was investigated. It was demonstrated that adding 5% Al resulted in:

- A decrease in the parabolic oxidation rate by factors of 100 to 1000 compared to pure Cu and Cu-17%Cr.
- An increased temperature capability up to 400 K compared to Cu-17%Cr.
- A change from parabolic oxidation kinetics for Cu-17% Cr to either a quartic or logarithmic rate law for Cu-17%Cr-5%Al.

The parabolic rate constants determined for Cu-17%Cr between 773 and 973 K were similar to those reported for pure Cu (Refs. 6, 9, 10, 16, 18 to 22, and 44), Cu-1%Al (Refs. 44, 45, and 49) and Cu-Cr

(Refs. 20 and 21) alloys, while the activation energy for oxidation of the alloy was  $165 \text{ kJ mol}^{-1}$ . This value of activation energy was comparable to the diffusion of  $\text{Cu}^+$  ions in pure Cu (Ref. 22) and Cu-Cr alloys (Ref. 21) oxidized under relatively high partial pressures of oxygen to form  $\text{CuO/Cu}_2\text{O}$  scales. It was concluded that Cr did not improve the oxidation behavior of as-cast Cu-17%Cr.

The oxidation kinetics for Cu-17%Cr-5%Al were more complex than pure Cu and Cu-17%Cr in the temperature range 773 to 1173 K. The initial variations in the specific weight change data with time were better described by a parabolic relationship while the latter portions of the specific weight change curves were better described by a quartic function. Using the parabolic relationship corresponding to the initial oxidation regime, the values of  $Q$  were observed to vary from  $25 \text{ kJ mol}^{-1}$  between 773 and 973 K and increased to  $115 \text{ kJ mol}^{-1}$  above 973 K. However, using the quartic relationship corresponding to the steady-state oxidation region, the value of  $Q$  was observed to be  $185 \text{ kJ mol}^{-1}$ . The weight change data could be better described by a logarithmic relationship, where the activation energy for oxidation increased from about  $35 \text{ kJ mol}^{-1}$  between 773 and 1073 K to  $115 \text{ kJ mol}^{-1}$  above 1073 K. Comparisons of the parabolic rate constants with literature data on Cu (Refs. 6, 9, 10, 16, 18 to 22, and 44), Cu-Al (Refs. 44 and 49), Cu-Cr (Refs. 20 and 21), Cu-7%Cr-2%Al (Refs. 44 and 45), and alumina (Ref. 50) and chromia (Ref. 50) scale formers revealed that the  $k_p$  values for Cu-17%Cr-5%Al were significantly less than those for Cu, Cu-1%Al and Cu-Cr alloys by factors of 100 to 1000. These values were also less than those published for chromia scale forming alloys published in the literature (Ref. 49) but close to those reported for alumina scale formers (Ref. 50) and Cu-10%Al (Ref. 48) and Cu-7(at.%)Cr-2%Al (Refs. 44 and 45) alloys. The activation energies determined using either the parabolic rate constants or the logarithmic rate constants were similar and varied from about 25 to  $35 \text{ kJ mol}^{-1}$  below 1073 K to  $115 \text{ kJ mol}^{-1}$  at higher temperatures. The values of activation energy at the lower temperatures are in excellent agreement with the theoretical value of  $25 \text{ kJ mol}^{-1}$  calculated for the diffusion of  $\text{V}_{\text{Cu}}$  diffusion in Al doped  $\text{Cu}_2\text{O}$ , where the Al atoms are predicted to bind to the copper vacancies (Ref. 51). Therefore, it is suggested that the inhibition of  $\text{Cu}^+$  diffusion in  $\text{Cu}_2\text{O}$  by Al is the predominant mechanism governing oxidation behavior of the Cu-17%Cr-5%Al below 1073 K. It is expected that the growth of a protective alumina scale will be the dominant process above 1073 K.

## References

1. H.J. Kasper, in: S.F. Morea and S.T. Wu (eds.), *Advanced High Pressure  $\text{O}_2/\text{H}_2$  Technology*, NASA CP-2372 (NASA Marshall Space Flight Center, Huntsville, AL, 1985), pp. 36–43.
2. D.B. Morgan, A.C. Kobayashi, *Main Combustion Chamber and Cooling Technology Study—Final Report*, NASA CR 184345 (NASA Marshall Space Flight Center, Huntsville, AL, 1989).
3. L. Ogbuji and D.L. Humphrey, *Oxid. Metals* **60**, 271–291 (2003).
4. E. Scheil, *Zeit. für Metallkde.* **29**, 209–214 (1937); translated version in NACA TM-1338, National Advisory Committee for Aeronautics, Washington, D.C. (1952).
5. H. Nishimura, J. Suyiokwai-shi **9**, 655–664 (1938).
6. G. Valensi, *Pittsburgh International Conference on Surface Reactions*, Electrochemical Society, Pittsburgh, PA (1948).
7. R.F. Tylecote, *J. Inst. Metals* **78**, 259–300 (1950–51).
8. R.F. Tylecote, *J. Inst. Metals* **78**, 301–326 (1950–51).
9. R.F. Tylecote, *J. Inst. Metals* **78**, 327–350 (1950–51).
10. D.W. Bridges, J.P. Baur, G.S. Baur and W.M. Fassell, *J. Electrochem. Soc.* **103**, 475–478 (1956).
11. P. Kofstad, *Nature* **179**, 1362–1363 (1957).
12. J.A. Sartell and C. H. Li, *Trans. ASM* **55**, 58–162 (1962).
13. L. Czerski, S. Mrowec and T. Werber, *Roczniki Chemii.* **38**, 643–654 (1964).
14. P. Kofstad, *High-Temperature Oxidation of Metals* (John Wiley, New York, NY, 1966).
15. O. Kubaschewski and B. E. Hopkins, *Oxidation of Metals and Alloys* (Butterworths, London, U.K., 1967).
16. S. Mrowec and A. Stoklosa, *Oxid. Metals* **3**, 291–311 (1971).

17. P.C. Donovan and C.J. Barton, Metall. Trans. **4**, 1765–1767 (1973).
18. F. Gesmundo, C. De Asmundis and S. Merlo, Werkstoffe Und Korrosion—Materials and Corrosion vol. 30, 114 (1979).
19. J. H. Park and K. Natesan, Oxid. Metals **39**, 411–435 (1993).
20. Y. Niu, F. Gesmundo, F. Viani and D. L. Douglass, Oxid. Metals **48**, 357–380 (1997).
21. K.T. Chiang, G.H. Meier and F.S. Pettit in: S.B. Newcombe and J.A. Little (eds.), *Microscopy of Oxidation*, pp.453–461 (The Institute of Metals, London, U.K., 1997).
22. Y.Zhu, K. Mimura, J W. Lim, M. Isshiki and Q. Jiang, Metall. Mater. Trans. A **37A**, 1231–1237 (2006).
23. F. Gesmundo, Y. Niu, F. Viani and D.L. Douglass, Oxid. Metals **49**, 147–167 (1998).
24. G.Y. Fu, Y. Niu and F. Gesmundo, Corr. Sci. **45**, 559–574 (2003).
25. L.U. Ogbuji, Surf. Coat. Tech. **197**, 327–335 (2005).
26. D.J. Chakrabarti and D. E. Laughlin, Bull. Alloy Phase Diagrams **5**, 59 (1984).
27. T.B. Massalski, H. Okamoto and P.R. Subramanian (eds.), *Binary Alloy Phase Diagrams* (ASM International, Materials Park, Cleveland, OH 1990).
28. K.T. Chiang, P.D. Krotz and J.L. Yuen, Surf. Coat. Technol. **76**, 14–19 (1995).
29. K.T. Chiang and J.P. Ampaya, Surf. Coat. Technol. **78**, 243–247 (1996).
30. T.A. Wallace, R. K Clark and K.T. Chiang, J. Spacecraft Rockets **35**, 546–51 (1998).
31. S.V. Raj, L.J. Ghosn, C. Robinson and D. Humphrey, Mater. Sci. Eng. A **457**, pp. 300–312 (2007).
32. S.V. Raj, unpublished research, NASA Glenn Research Center, Cleveland, OH (2003).
33. J. S. Dunn, J. Inst. Metals **46**, 25–48 (1931).
34. K. W. Frohlich, Zeits. Metallkunde. **28**, 368–375 (1936).
35. L. E. Price and G. J. Thomas, J. Inst. Metals **63**, 21–28 (1938).
36. J. P. Dennison and A. Preece, J. Inst. Metals **81**, 229–234 (1952).
37. J. C. Blade and A. Preece, J. Inst. Metals **88**, 427–432 (1959).
38. M. D. Saderson and J. C. Scully, Oxid. Metals **3**, 59–90 (1971).
39. K. Hauffe and E. Ofulue, Werkstoffe Und Korrosion—Mater. Corr. **23**, 351–355 (1972).
40. G. Plascencia, T. Utigard and T. Marín, JOM **57**, 80–84 (2005).
41. J.L. Smialek and G.H. Meier in: C.T. Sims, N.S. Stoloff and W.C. Hagel (eds.), *Superalloys II* (John Wiley, New York, 1987) pp. 293–326.
42. G. Ghosh in: G. Petzow and G. Effenberg (Eds.), *Handbook of Ternary Alloy Phase Diagrams*, vol. **4** (VCH Publishers, New York, NY, 1991), pp. 311–319.
43. B. Grushko, E. Kowalska-Strzeciwlk, B. Przepiorzynski and M. Surowiec, J. Alloys and Compounds **417**, 121–126 (2006).
44. Y. Niu, S.Y. Wang and F. Gesmundo, Oxid. Metals **65**, 285–306 (2006).
45. S.Y. Wang, F. Gesmundo, W.T. Wu and Y. Niu, Scripta Mater. **54**, 1563–1568 (2006).
46. S.V. Raj, C. Barrett, J. Karthikeyan, and R. Garlick, Surf. Coat. Tech. **201**, pp. 7222–7234 (2007).
47. W.J. Moore, Y. Ebisuzaki and J. A. Sluss, J. Phys. Chem. **62**, 1438–1441 (1958).
48. Y. Zhu, K. Mimura and M. Isshiki, Oxid. Metals **62**, 207–222 (2004).
49. W. Kai, G.W. Fan, P.C. Chen and Y.T. Lin, Oxid. Metals **61**, 439–461 (2004).
50. H. Hindam and D.P. Whittle, Oxid. Metals **18**, 245–284 (1982).
51. A.F. Wright and J.S. Nelson, J. Appl. Phys. **92**, 5849–5851 (2002).
52. R.H. Doremus, J. Appl. Phys. **95**, 3217–3222 (2004).
53. H.J. Frost and M.F. Ashby, *Deformation-Mechanism Maps: The Plasticity and Creep of Metals and Ceramics* (Pergamon Press, Oxford, 1982) p. 99.

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
<p>The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.</p> <p>PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.</p>					
1. REPORT DATE (DD-MM-YYYY) 01-10-2008		2. REPORT TYPE Technical Memorandum		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE Comparison of the Isothermal Oxidation Behavior of As-Cast Cu-17%Cr and Cu-17%Cr-5% Al Part I: Oxidation Kinetics				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Raj, S., V.				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER WBS 561581.02.08.03.15.02	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration John H. Glenn Research Center at Lewis Field Cleveland, Ohio 44135-3191				8. PERFORMING ORGANIZATION REPORT NUMBER E-16551	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001				10. SPONSORING/MONITORS ACRONYM(S) NASA	
				11. SPONSORING/MONITORING REPORT NUMBER NASA/TM-2008-215284-PART1	
12. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified-Unlimited Subject Categories: 26 and 15 Available electronically at <a href="http://gltrs.grc.nasa.gov">http://gltrs.grc.nasa.gov</a> This publication is available from the NASA Center for AeroSpace Information, 301-621-0390					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT The isothermal oxidation kinetics of as-cast Cu-17%Cr and Cu-17%Cr-5%Al in air were studied between 773 and 1173 K under atmospheric pressure. These observations reveal that Cu-17%Cr-5%Al oxidizes at significantly slower rates than Cu-17%Cr. The rate constants for the alloys were determined from generalized analyses of the data without an a priori assumption of the nature of the oxidation kinetics. Detailed analyses of the isothermal thermogravimetric weight change data revealed that Cu-17%Cr exhibited parabolic oxidation kinetics with an activation energy of 165.9±9.5 kJ mol <sup>-1</sup> . In contrast, the oxidation kinetics for the Cu-17%Cr-5%Al alloy exhibited a parabolic oxidation kinetics during the initial stages followed by a quartic relationship in the later stages of oxidation. Alternatively, the oxidation behavior of Cu-17%CR-5%Al could be better represented by a logarithmic relationship. The parabolic rate constants and activation energy data for the two alloys are compared with literature data to gain insights on the nature of the oxidation mechanisms dominant in these alloys.					
15. SUBJECT TERMS Coatings; GRCop-84; Copper alloys; Cyclic oxidation; Reusable launch vehicles					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES 24	19a. NAME OF RESPONSIBLE PERSON STI Help Desk (email: <a href="mailto:help@sti.nasa.gov">help@sti.nasa.gov</a> )
a. REPORT U	b. ABSTRACT U	c. THIS PAGE U			19b. TELEPHONE NUMBER (include area code) 301-621-0390





