

NASA/TM—1998-208828



Synchrotron VUV and Soft X-Ray Radiation Effects on Aluminized Teflon[®] FEP

Joyce A. Dever
Lewis Research Center, Cleveland, Ohio

Jacqueline A. Townsend
Goddard Space Flight Center, Greenbelt, Maryland

James R. Gaier
Lewis Research Center, Cleveland, Ohio

Alice I. Jalics
Cleveland State University, Cleveland, Ohio

Prepared for the
43rd International Symposium
sponsored by the Society for the Advancement of Materials and Process Engineering
Anaheim, California, May 31–June 4, 1998

National Aeronautics and
Space Administration

Lewis Research Center

November 1998

Acknowledgments

Research was carried out, in part, at the National Synchrotron Light Source, Brookhaven National Laboratory, which is supported by the U. S. Department of Energy, Division of Materials Sciences and Division of Chemical Sciences. The authors gratefully acknowledge the support of Michael Sagurton of SFA/Los Alamos National Laboratory, and Steven Hulbert of the NSLS, BNL during experiments conducted at the NSLS. The authors also acknowledge the following for their technical contributions to this paper: Bruce Banks of NASA Lewis Research Center; Thomas Stueber, Edward Sechkar and Mark Forkapa of NYMA, Inc.; Demetrios Papadopoulos of the University of Akron; and Elizabeth Gaier of Manchester College.

Trade names or manufacturers' names are used in this report for identification only. This usage does not constitute an official endorsement, either expressed or implied, by the National Aeronautics and Space Administration.

Available from

NASA Center for Aerospace Information
7121 Standard Drive
Hanover, MD 21076
Price Code: A03

National Technical Information Service
5285 Port Royal Road
Springfield, VA 22100
Price Code: A03

SYNCHROTRON VUV AND SOFT X-RAY RADIATION EFFECTS ON ALUMINIZED TEFLON[®] FEP

Joyce A. Dever
National Aeronautics and Space Administration
Lewis Research Center
Cleveland, Ohio 44135

Jacqueline A. Townsend
National Aeronautics and Space Administration
Goddard Space Flight Center
Greenbelt, Maryland 20771

James R. Gaier
National Aeronautics and Space Administration
Lewis Research Center
Cleveland, Ohio 44135

Alice I. Jalics
Cleveland State University
Cleveland, Ohio 44115

ABSTRACT

Surfaces of the aluminized Teflon[®] FEP multi-layer thermal insulation on the Hubble Space Telescope (HST) were found to be cracked and curled in some areas at the time of the second servicing mission in February 1997, 6.8 years after HST was deployed in low Earth orbit (LEO). As part of a test program to assess environmental conditions which would produce embrittlement sufficient to cause cracking of Teflon[®] on HST, samples of Teflon[®] FEP with a backside layer of vapor deposited aluminum were exposed to vacuum ultraviolet (VUV) and soft x-ray radiation of various energies using facilities at the National Synchrotron Light Source, Brookhaven National Laboratory. Samples were exposed to synchrotron radiation of narrow energy bands centered on energies between 69 eV and 1900 eV. Samples were analyzed for ultimate tensile strength and elongation. Results will be compared to those of aluminized Teflon[®] FEP retrieved from HST after 3.6 years and 6.8 years on orbit and will be referenced to estimated HST mission doses of VUV and soft x-ray radiation.

1. INTRODUCTION

Since the Hubble Space Telescope (HST) was deployed in low Earth orbit (LEO) in April 1990, two servicing missions have been conducted to upgrade its scientific capabilities. The first servicing mission (SM1) was conducted in December 1993, 3.6 years after deployment. The second servicing mission (SM2) was conducted in February 1997, 6.8 years after deployment. The HST servicing missions provided an opportunity for on-orbit examination and retrieval of second-surface metalized Teflon[®] FEP (fluorinated ethylene propylene) used as the top layer of multi-layer insulation (MLI) blankets and on radiator surfaces. Minor cracking of FEP surfaces on HST was first observed upon close examination of samples with high solar exposure retrieved during SM1 (1). During SM2, astronaut observations and photographic documentation revealed cracks in the FEP layer of the MLI on both solar-facing and anti-solar facing surfaces of the telescope.

The efforts reported in this paper were conducted as part of a test program to identify the LEO environmental constituent(s) responsible for cracking and embrittlement of Teflon[®] FEP on HST (2). Soft x-ray radiation from solar flares has been investigated previously as a possible cause for mechanical properties degradation of Teflon[®] FEP (3). This paper describes an investigation of the effects of vacuum ultraviolet (VUV) and soft x-ray radiation on Teflon[®] FEP. Samples of aluminized Teflon[®] FEP were exposed to synchrotron radiation of various VUV and soft x-ray wavelengths between 18 nm (69 eV) and 0.65 nm (1900 eV), and doses and fluences were compared to those estimated for the HST mission. Synchrotron radiation exposures were conducted using the National Synchrotron Light Source (NSLS), Brookhaven National Laboratory (BNL). Tensile testing was conducted on synchrotron radiation-exposed samples to determine tensile strength and elongation.

2. X-RAY AND SOLAR EXPOSURE ENVIRONMENT ON HST

Table 1 provides information about the x-ray and solar exposure environment on HST from deployment to SM1, SM2 and end-of-life (EOL) (4-6). Radiation in the x-ray wavelength regions 0.05-0.4 nm (3-25 keV) and 0.1-0.8 nm (1.5-12 keV) is attributed primarily to solar flares (3). Based on the x-ray fluence data for these two wavelength regions given in Table 1, it is evident that the majority of the solar flare x-ray fluence is in the 0.4 - 0.8 nm wavelength range, or 1.5-3 keV. The data in Table 1 are for the incident x-ray fluence and do not necessarily indicate the radiation dose absorbed by the Teflon® material.

TABLE 1. X-RAY AND SOLAR EXPOSURE ENVIRONMENT ON HST (4-6)

| | SM1 3.6 years | SM2 6.8 years | EOL 20 years |
|--|------------------|------------------|-----------------|
| X-ray fluence, 0.05-0.4 nm or 3-25 keV (J/m ²) | 14.7 | 16 | 47.15 |
| X-ray fluence, 0.1-0.8 nm or 1.5-12 keV (J/m ²) | 222.6 | 252.4 | 699.6 |
| Solar exposure for solar-facing surfaces (equivalent sun hours) | 16,670 | 33,638 | 100,000 |

In addition to the data shown in Table 1 for the two regions of x-ray radiation, Reference 7 provides spectral flux data for VUV to soft x-ray wavelengths. From these data, HST fluences for narrow wavelength bands centered on wavelengths between 18 nm (69 eV) and 1.77 nm (700 eV), which were included in the synchrotron exposure experiments, were calculated and are shown in Table 2. Data for the additional synchrotron exposure energies up to 1900 eV were not available from this reference.

TABLE 2. SOFT X-RAY AND VUV FLUENCES FOR NARROW ENERGY BANDS ON HST

| Energy Range, Ave. (eV) | Wavelength Range, Ave. (nm) | Moderate Solar Activity Flux (photons/cm ² s) (7) | Estimated Fluence on HST, Assuming Moderate Solar Activity (J/m ²) | | |
|-------------------------------|-----------------------------------|--|---|-------------------|------------------|
| | | | SM1 (3.6 yrs.) | SM2 (6.8 yrs.) | EOL (20 yrs.) |
| 68.6-69.4, 69 | 17.9-18.1, 18.0 | 1.10E+08 | 515 | 969 | 2943 |
| 283-297, 290 | 4.18-4.38, 4.28 | 4.00E+06 | 126 | 238 | 722 |
| 490-532, 510 | 2.33-2.53, 2.43 | 2.00E+06 | 133 | 251 | 761 |
| 663-742, 700 | 1.67-1.87, 1.77 | 1.00E+06 | 65 | 123 | 373 |

In order to determine the radiation dose absorbed by the Teflon® layer of the MLI, it is necessary to know how radiation is absorbed as a function of energy in Teflon®.

3. RADIATION ABSORPTION IN TEFLON®

Figure 1 shows the attenuation length of Teflon®, modeled as C₂F₄ as a function of energy (8). Attenuation length is defined as the depth into the material where the radiation intensity has fallen to 1/e (0.368) of its intensity at the surface. As shown, attenuation length is dependent on energy or wavelength. The absorption edges at approximately 290 and 700 eV are for carbon and fluorine, respectively. Crosses shown on the curve indicate the energies used for exposure of samples to synchrotron radiation, 69-1900 eV.

In order to calculate the absorbed radiation dose in Teflon®, it was necessary to use the fluence data for 0.05-0.4 nm and 0.1-0.8 nm along with the data for attenuation length. The equation for photon intensity at a specific energy as a function of depth in a material, I_E , is given as follows:

$$I_E = I_{0E} \exp(-(\mu/\rho)x) \quad [1]$$

where I_{0E} is the incident intensity at a specific energy, μ is the extinction coefficient, ρ is the density, and x is the depth into the material. The term μ/ρ is referred to as the linear absorption coefficient.

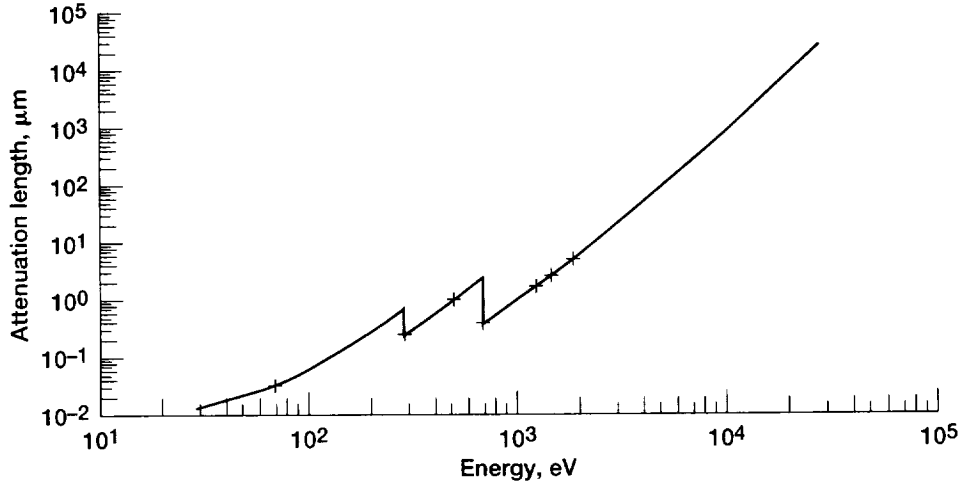


Figure 1.—Attenuation length of Teflon[®], modeled as C₂F₄ (8).

The definition of attenuation length can be stated as the value of x where

$$I_E = I_{0E}/e. \quad [2]$$

Substituting Equation 2 into Equation 1 gives:

$$I_{0E}/e = I_{0E} \exp(-(\mu/\rho)x). \quad [3]$$

Solving Equation 3 for μ/ρ gives:

$$1/x = \mu/\rho \quad [4]$$

or

$$\text{attenuation length} = \rho/\mu.$$

Figure 1 provided x vs. energy, so, $1/x$ vs. energy can be obtained from the data in Figure 1. At energies above 1.5 keV, the energies provided for the HST exposure environment, the $1/x$ vs. energy data was curve-fitted to provide the linear absorption coefficient, μ/ρ , as a function of energy, E :

$$\mu/\rho = 3.46 \times 10^9 E^{-3.12}. \quad [5]$$

Then, this was substituted into Equation 1 to give:

$$I_E = I_{0E} \exp((-3.46 \times 10^9 E^{-3.12})(x)). \quad [6]$$

Equation 6 provides the intensity of radiation at depth x into the material for a specific energy, I_E . Therefore, the absorbed intensity at a specific energy, A_E , is given as

$$A_E = I_{0E} - I_E \quad [7]$$

or

$$A_E = I_{0E} (1 - \exp((-3.46 \times 10^9 E^{-3.12})(x))). \quad [8]$$

Because I_{0E} and I_E represent intensity, they are expressed in units of W/m² or J/m²s. Therefore, they can be described as values of x-ray flux at a specific wavelength or energy. A_E is then the absorbed x-ray flux at a

particular energy. The incident HST x-ray fluence values indicated in Table 1 are reported in units of J/m² over a range of energies to indicate flux integrated over a specific mission duration. This can be represented by the following equation:

$$F_0 = \int I_0 dt \quad [9]$$

where F_0 is the incident fluence over a specific mission duration given in J/m², I_0 is the incident flux at a specific time, and t is time. Multiplying both sides of Equation 8 by time, we obtain the following:

$$F_{AE} = F_{0E} (1 - \exp((-3.46 \times 10^9 E^{-3.12})x)) \quad [10]$$

where F_{AE} and F_{0E} are the absorbed and incident values of fluence, respectively, at a specific energy. Because fluence values in Table 1 are for the rather broad energy/wavelength bands indicated rather than for discrete energies/wavelengths,

$$F_{0E} = \frac{F_{0E_1-E_2}}{E_2 - E_1} \quad [11]$$

Equation 11 was then substituted into Equation 10 and the result was numerically integrated over each energy range, 1.5-12 keV and 3-25 keV, using the HST incident fluence data from Table 1. For example, the numerical integration approximated the absorbed fluence for the 1.5-12 keV range given by the following equation:

$$F_{A,1.5-12 \text{ keV}} = \frac{F_{0,1.5-12 \text{ keV}}}{12 - 1.5} \int_{1.5 \text{ keV}}^{12 \text{ keV}} (1 - \exp((-3.46 \times 10^9 E^{-3.12})x)) dE \quad [12]$$

The absorbed x-ray radiation fluence was thus determined for specific depths, x , into the Teflon[®] material. Fluence of absorbed x-ray radiation was converted to dose, in units of rads, using the following equation:

$$\text{Dose, rads} = F_A (1/\rho) (1/x) (1 \text{ rad}/(0.01 \text{ J/kg})) \quad [13]$$

where absorbed fluence over a particular energy range is F_A , in units of J/m²; density, ρ , is in units of kg/m³; and thickness, x , is in units of m. Because the outer layer of MLI or HST is comprised of 127 μm thick Teflon[®] FEP, absorbed radiation dose was calculated for this thickness and is shown in Table 3.

TABLE 3. X-RAY RADIATION DOSE ON HST FOR 127 μm FEP

| | SM1 3.6 years | SM2 6.8 years | EOL 20 years |
|--|------------------|------------------|-----------------|
| X-ray dose, 0.05-0.4 nm or 3-25 keV (krads) | 0.99 | 1.08 | 3.18 |
| X-ray dose, 0.1-0.8 nm or 1.5-12 keV (krads) | 9.2 | 44.4 | 123 |

4. SYNCHROTRON RADIATION EXPOSURE CONDITIONS

Samples of second-surface aluminized Teflon[®] FEP were exposed to synchrotron radiation of various energies between 69 eV and 1900 eV. Two different beamlines at the NSLS were used to conduct experiments. As indicated in Table 4, Beamline U16B was used to provide radiation between 69 eV and 700 eV, and Beamline X8A was used to provide radiation between 510 eV and 1900 eV. Table 4 shows the energies and wavelengths used in these experiments including the calculated bandwidth at full-width, half-maximum and the estimated spot size for the beam. Also shown are attenuation lengths for each energy, as shown in Figure 1. As indicated by the attenuation lengths, the majority of radiation from these synchrotron radiation exposures is deposited within the first few micrometers of material.

TABLE 4. SYNCHROTRON RADIATION EXPOSURE CONDITIONS

| NSLS Beamline Name | Energy (eV) | Wavelength (nm) | Approx. Spot Size, h x w (mm) | Attenuation Length, μm |
|--------------------|----------------|-------------------|-------------------------------|-----------------------------------|
| U16B | 69 ± 0.1 | 18.00 ± 0.026 | 3 x 5 | 0.033 |
| | 290 ± 1.7 | 4.28 ± 0.025 | 3 x 4.5 | 0.262 |
| | 700 ± 10 | 1.77 ± 0.025 | 3 x 4 | 0.403 |
| X8A | 510 ± 2.6 | 2.44 ± 0.012 | 10 x 4 | 1.06 |
| | 700 ± 3.5 | 1.77 ± 0.0089 | 10 x 4 | 0.403 |
| | 1256 ± 6.3 | 0.99 ± 0.005 | 10 x 4.5 | 1.74 |
| | 1489 ± 7.4 | 0.83 ± 0.004 | 10 x 4 | 2.74 |
| | 1900 ± 9.5 | 0.65 ± 0.003 | 10 x 4 | 5.36 |

5. EXPERIMENTAL PROCEDURES

5.1 Samples Samples for synchrotron radiation exposure were fabricated from Teflon® FEP of 127 μm thickness with approximately 100 nm of vapor deposited aluminum. Samples were exposed to the synchrotron radiation beam such that the FEP surface faced the beam and the aluminum surface was the back surface of each sample. Samples for tensile testing were “dog bone” shaped and were die-cut with a die manufactured according to ASTM Standard D638-95, Type V (9). For this sample size, the width of the narrow section of the dog bone was 3.18 mm, and the gauge length was 9.53 mm. The beam size for each synchrotron energy used is shown in Table 4 for comparison. For experiments at both beamlines, the beam covered the width of the narrow section of the dogbone. For experiments conducted at Beamline X8A where the beam was approximately 10 mm in height, the full gauge length of each specimen was illuminated by the beam. For samples exposed at Beamline U16B, the full gauge length was not covered by the beam. Additional samples included in the experiments which were not intended for tensile testing were nominally 3 to 5 mm maximum width and 15 mm length.

5.2 Apparatus Figure 2 shows the sample/detector holder which was able to hold up to seven pairs of samples as shown. When pairs of samples were exposed, each pair consisted of one tensile specimen and one non-tensile specimen.

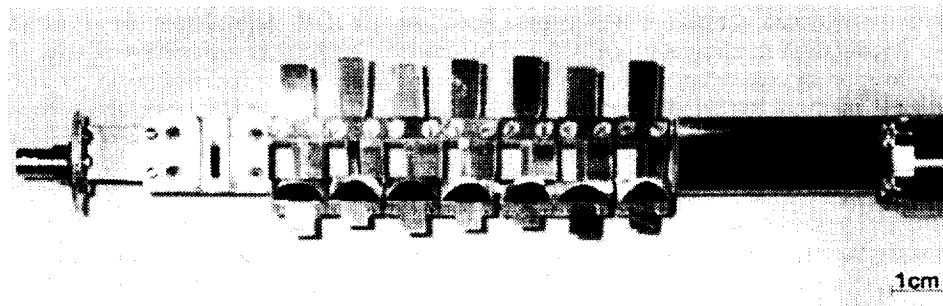


Figure 2.—Sample holder for synchrotron radiation exposure of FEP samples.

In most cases, the tensile specimen was centered on the synchrotron beam, and the other sample received the “tail” of the synchrotron beam, typically a small fraction of the intensity provided by the beam center. Shown at the left of the sample holder is the silicon photodiode used to measure the synchrotron beam intensity for each sample exposure. The sample/detector holder was attached to a linear positioner with a movement scale allowing positioning accurate to ± 0.01 mm. Prior to installation in the vacuum chamber, distances between the photodiode and samples were measured with digital calipers to assure accuracy in placement of the samples in the synchrotron beam. Measurements of synchrotron beam intensity were made before and after each exposure and were averaged to determine photon fluence for each sample exposed. A mask was used over the photodiode providing a measurement area 3 mm wide by 10 mm high, comparable to the gauge size of a tensile specimen.

5.3 Tensile Testing Tensile testing was conducted to determine degradation in tensile strength and elongation for synchrotron radiation-exposed FEP samples as compared to pristine material. Sample dimensions were described in Section 5.1. Samples exposed at Beamline X8A were tensile tested using an Instron 4505 load frame with Instron Series IX data acquisition software. Samples exposed at Beamline U16B were tensile tested using an automated bench-top tensile tester and data acquisition software. A strain rate of 0.212 mm/s was used for all tests. Because samples from each beamline were tested using different instruments at different times, results for each set of synchrotron-exposed samples were compared to a set of pristine samples tensile tested at the same time.

6. RESULTS AND DISCUSSION

Table 5 shows results of tensile testing of synchrotron radiation-exposed second surface aluminized FEP. For each sample the exposure energy, measured fluence, absorbed dose, and comparison to orbital doses are provided. Samples U5T and U2T were exposed to both 290 eV and 700 eV radiation, sequentially, as shown. The objective of these experiments was to determine whether exposure to radiation at both the carbon and fluorine absorption edges would produce synergistic degradation.

The HST EOL 0.05-0.4 nm (1.5-25 keV) doses at the attenuation length of the exposure energy were calculated using the data in Table 1 and equations 1-11. For 69-700 eV the narrow-band energy doses for HST EOL at the attenuation length of the exposure energy are also shown for comparison. These narrow-band energy dose values were calculated using the data in Table 2 and equations 2, 7, 9, and 13. As shown in Table 5, in most cases, the sample dose significantly exceeded the HST EOL dose.

The ultimate tensile strength (UTS) and elongation were measured for each tensile specimen, and data are provided in Table 5 with the percent changes from pristine specimens. The tensile test data for pristine specimens are given in Table 6. The tensile test data in Table 5 can be compared to the changes in tensile strength and elongation experienced for aluminized FEP materials retrieved from HST during the first and second servicing missions which are provided in Table 7 (10).

For most synchrotron radiation-exposed samples, some degradation in tensile strength and elongation was observed. However, the degradation in tensile strength and elongation experienced by the synchrotron radiation-exposed samples was not comparable to that demonstrated by samples retrieved from HST after 3.6 years and 6.8 years. The worst degradation in tensile strength was 30.3%, for sample X1T, which received 256 times the HST EOL x-ray dose or an equivalent of over 5000 years in space. This result can be compared to that of an HST specimen retrieved during SM1 after 3.6 years in space. This material showed a degradation in tensile strength of 37-42%, greater than that of the worst damaged synchrotron-exposed sample. The synchrotron radiation-exposed sample which experienced the greatest degradation in elongation was X14T which showed a degradation in elongation of 83%. This sample received an equivalent of over 1500 times the HST EOL x-ray dose or an equivalent of over 30,000 years in space. Compare this result to the complete loss of elongation for the material retrieved from HST after 6.8 years. It is obvious from these results that at the energies used for these synchrotron radiation exposures, VUV radiation and soft x-ray radiation were not sufficient to cause the degradation in mechanical properties displayed by 6.8 year HST-exposed aluminized FEP.

All synchrotron-exposed tensile specimens were examined using optical microscopy for evidence of surface embrittlement or cracking. This effect was described in Reference 3. The only specimens showing evidence of surface cracking after tensile testing were those samples exposed to 290 eV synchrotron radiation, samples U1T and U4T. Figure 3 shows a photomicrograph of sample U4T after tensile testing as compared to sample U6T, exposed to 69 eV synchrotron radiation of a higher absorbed radiation dose. Sample U6T was comparable to all other synchrotron-exposed specimens in that it showed no evidence of surface cracking. It is possible that because 290 eV is at the carbon absorption edge, more severe degradation in the radiation-absorbing layer may occur.

TABLE 5. TENSILE TESTING OF SYNCHROTRON RADIATION-EXPOSED FEP SAMPLES

| Sample Label | Energy (eV) | Incident Fluence (J/m ²) | Dose at atten. length (krads) | | | Ultimate Tensile Strength, UTS (MPa) | Elongation (%) at Break | % Change in UTS from pristine | % Change in % Elongation from pristine |
|--------------|-------------|--------------------------------------|-------------------------------|--------------------------|---------------------------------|--------------------------------------|-------------------------|-------------------------------|--|
| | | | Sample Dose | HST EOL 0.05-0.8 nm Dose | HST EOL Narrow Energy Band Dose | | | | |
| U3T | 69 | 5304 | 4.73E+06 | 839 | 2.7E+06 | 19.48 | 214 | 0.2 | 4.4 |
| U6T | 69 | 5076 | 4.52E+06 | | | 17.29 | 176 | -11.0 | -14.1 |
| U4T | 290 | 3136 | 3.52E+05 | 825 | 5.6E+04 | 15.08 | 107 | -22.4 | -47.8 |
| U1T | 290 | 3099 | 3.48E+05 | | | 14.76 | 114 | -24.1 | -44.4 |
| U5T | 290 | 1583 | 1.78E+05 | 825 | 5.6E+04 | > 14.34* | > 134* | > -26.2* | > -34.6* |
| | 700 | 1534 | 1.12E+05 | 816 | 2.1E+04 | | | | |
| U2T | 290 | 1611 | 1.81E+05 | 825 | 5.6E+04 | 14.25 | 87.6 | -26.7 | -57.3 |
| | 700 | 1521 | 1.11E+05 | 816 | 2.1E+04 | | | | |
| X6T | 510 | 474 | 1.31E+04 | 777 | 1.6E+04 | 22.36 | 649 | 16.0 | 11.1 |
| X17T | 700 | 973 | 7.10E+04 | 816 | 2.1E+04 | 16.18 | 434 | -16.1 | -25.7 |
| X15T | 700 | 3055 | 2.23E+05 | | | 17.60 | 489 | -8.7 | -16.3 |
| X16T | 700 | 10347 | 7.55E+05 | | | 16.97 | 484 | -12.0 | -17.2 |
| X10T | 1256 | 17982 | 3.04E+05 | 742 | N/A | 16.23 | 406 | -15.8 | -30.4 |
| X3T | 1489 | 161 | 1.73E+03 | 695 | N/A | 20.34 | 626 | 5.5 | 7.2 |
| X2T | 1489 | 8211 | 8.81E+04 | | | 20.56 | 629 | 6.7 | 7.7 |
| X1T | 1489 | 16123 | 1.73E+05 | | | 13.45 | 194 | -30.3 | -66.8 |
| X8T | 1489 | 21938 | 2.35E+05 | | | 14.36 | 322 | -25.5 | -44.8 |
| X14T | 1489 | 95859 | 1.03E+06 | | | 13.85 | 98 | -28.2 | -83.2 |
| X4T | 1900 | 32 | 1.76E+02 | 599 | N/A | 17.30 | 516 | -10.3 | -11.6 |
| X5T | 1900 | 3014 | 1.65E+04 | | | 19.32 | 596 | 0.2 | 2.0 |
| X12T | 1900 | 6632 | 3.64E+04 | | | 16.58 | 440 | -14.0 | -24.6 |

*Due to power failure, test stopped at this point prior to sample break

TABLE 6. TENSILE TESTING OF PRISTINE ALUMINIZED FEP

| Specimen Description | Ultimate Tensile Strength (MPa) | Elongation (%) |
|--|---------------------------------|----------------|
| X7T, Unexposed witness | 20.48 | 600.3 |
| Pristine, Avg. for 5 specimens, comparison for U samples | 19.43 ± 1.9 | 205 ± 28 |
| Pristine, Avg. for 3 specimens, comparison for X samples | 19.28 ± 3.2 | 584 ± 126 |

TABLE 7. TENSILE TEST DATA OF HST-EXPOSED MATERIALS (10)

| Sample | Yield Strength (MPa) | Ultimate Tensile Strength, UTS (Mpa) | % Change in UTS from Pristine | Elongation (%) | % Change in % Elongation from Pristine |
|---|----------------------|--------------------------------------|-------------------------------|----------------|--|
| Pristine aluminized FEP, 3 samples | 14.1±0.3 | 26.5±1.7 | | 363±25 | |
| SM1-retrieved MLI, 3.6 yrs., 11,339 ESH | 14.3 | 15.4 | -42 | 196 | -46 |
| | 14.3 | 16.6 | -37 | 116 | -68 |
| SM2-retrieved MLI, 6.8 yrs., 33,638 ESH | N/A | 13.2 | -50 | 0 | -100 |
| | N/A | 2.2 | -92 | 0 | -100 |

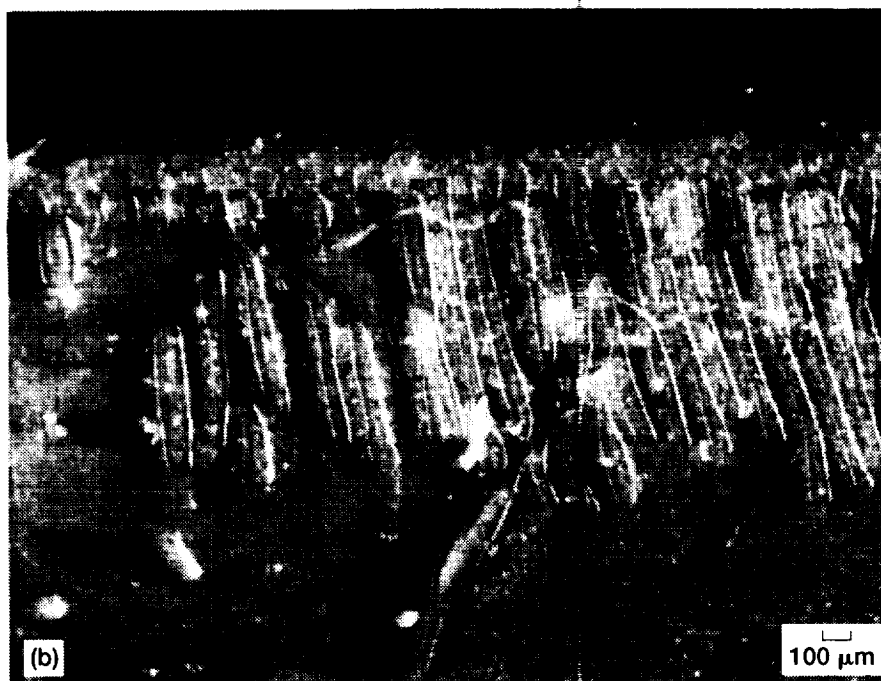
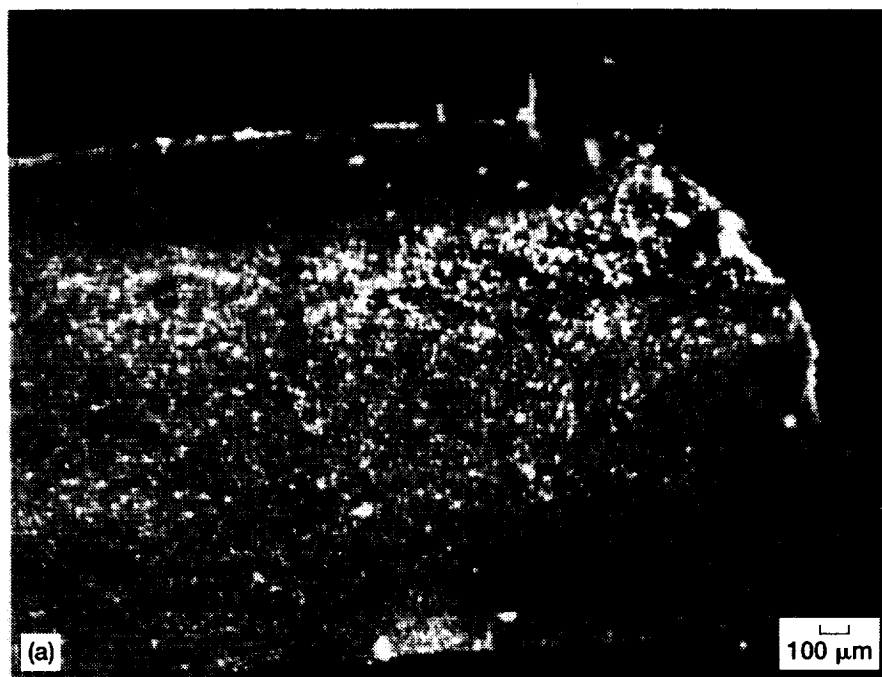


Figure 3.—Photomicrographs of tensile-tested, synchrotron radiation-exposed samples. (a) U6T exposed to 5076 J/m² at 69 eV. (b) U4T exposed to 3136 J/m² at 290 eV.

7. CONCLUSIONS

Exposure to synchrotron radiation in the VUV and soft x-ray range of energies is capable of causing degradation in the mechanical properties of Teflon[®] FEP. However, FEP samples exposed to synchrotron radiation of doses significantly greater than HST EOL doses did not show loss of tensile strength or elongation comparable to that of the severely embrittled aluminized FEP retrieved from HST during SM2 which experienced 6.8 years on orbit. Some evidence of wavelength-dependence of damage was observed for samples exposed to 290 eV synchrotron radiation which is at the carbon absorption edge. These samples showed surface cracking after tensile testing. Based on these results, exposure to VUV and soft x-ray radiation alone is not sufficient to cause the severe degradation in mechanical properties observed for FEP materials exposed to the HST environment.

8. ACKNOWLEDGMENTS

Research was carried out, in part, at the National Synchrotron Light Source, Brookhaven National Laboratory, which is supported by the U. S. Department of Energy, Division of Materials Sciences and Division of Chemical Sciences. The authors gratefully acknowledge the support of Michael Sagurton of SFA/Los Alamos National Laboratory, and Steven Hulbert of the NSLS, BNL during experiments conducted at the NSLS. The authors also acknowledge the following for their technical contributions to this paper: Bruce Banks of NASA Lewis Research Center; Thomas Stueber, Edward Sechkar and Mark Forkapa of NYMA, Inc.; Demetrios Papadopoulos of the University of Akron; and Elizabeth Gaier of Manchester College.

9. REFERENCES

1. Zuby, T. M., de Groh, K. K., Smith, D. C., "Degradation of FEP Thermal Control Materials Returned from the Hubble Space Telescope," NASA Technical Memorandum 104627, December 1995.
2. Townsend, J. A., Hansen, P. A., Dever, J. A., and Triolo, J. J., "Analysis of Retrieved Hubble Space Telescope Thermal Control Materials," Sci. Adv. Matl. Proc. Eng. Ser., 43, 000 (1998).
3. Milintchouk, A., Van Eesbeek, M., Levadou, F. and Harper, T. "Influence of X-ray Solar Flare Radiation on Degradation of Teflon[®] in Space," Journal of Spacecraft and Rockets, Vol. 34, No. 4, July-August 1997, p. 542-8.
4. NASA Memorandum from J. Barth to P. Hansen, July 7, 1997.
5. Jackson and Tull Technical Note from T. H. Gregory to P. Hansen, May 12, 1997.
6. Jackson and Tull Technical Note from T. H. Gregory to J. Townsend, June 25, 1997.
7. Tobiska, W. K., "A Brief History of Empirical Modeling of the Solar EUV Spectral Irradiance," in Proceedings of the Workshop on the Solar Electromagnetic Radiation Study for Solar Cycle 22, Richard F. Donnelly, ed., July 1992, pp. 338-53.
8. Calculation done interactively using Lawrence Berkeley Laboratory Center for X-Ray Optics, Internet Website, <http://www-crxo.lbl.gov>.
9. ASTM D638-95, "Standard Test Method for Tensile Properties of Plastics," 1995.
10. Dever J. A., de Groh, K. K., Townsend, J. A., Wang, L. L., "Mechanical Properties Degradation of Teflon FEP Returned from the Hubble Space Telescope," AIAA-98-0895, presented at the AIAA 36th Aerospace Sciences Meeting, Reno, NV, Jan. 12-16, 1998, NASA Technical Memorandum 1998-206618.

REPORT DOCUMENTATION PAGEForm Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

| | | | |
|--|---|--|--|
| 1. AGENCY USE ONLY (Leave blank) | | 2. REPORT DATE November 1998 | 3. REPORT TYPE AND DATES COVERED Technical Memorandum |
| 4. TITLE AND SUBTITLE Synchrotron VUV and Soft X-Ray Radiation Effects on Aluminized Teflon® FEP | | | 5. FUNDING NUMBERS WU-632-1A-1E-00 |
| 6. AUTHOR(S) Joyce A. Dever, Jacqueline A. Townsend, James R. Gaier, and Alice I. Jalics | | | |
| 7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Lewis Research Center Cleveland, Ohio 44135-3191 | | | 8. PERFORMING ORGANIZATION REPORT NUMBER E-11439 |
| 9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001 | | | 10. SPONSORING/MONITORING AGENCY REPORT NUMBER NASA TM-1998-208828 |
| 11. SUPPLEMENTARY NOTES Prepared for the 43rd International Symposium sponsored by the Society for the Advancement of Materials and Process Engineering, Anaheim, California, May 31-June 4, 1998. Joyce A. Dever and James R. Gaier, NASA Lewis Research Center, Jacqueline A. Townsend, NASA Goddard Space Flight Center, and Alice I. Jalics, Cleveland State University, Cleveland, Ohio 44115-2403. Responsible person, Joyce A. Dever, organization code 5480, (216) 433-6294. | | | |
| 12a. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified - Unlimited Subject Categories: 27 and 18 This publication is available from the NASA Center for AeroSpace Information, (301) 621-0390. | | | 12b. DISTRIBUTION CODE |
| 13. ABSTRACT (Maximum 200 words) Surfaces of the aluminized Teflon® FEP multi-layer thermal insulation on the Hubble Space Telescope (HST) were found to be cracked and curled in some areas at the time of the second servicing mission in February 1997, 6.8 years after HST was deployed in low Earth orbit (LEO). As part of a test program to assess environmental conditions which would produce embrittlement sufficient to cause cracking of Teflon® on HST, samples of Teflon® FEP with a backside layer of vapor deposited aluminum were exposed to vacuum ultraviolet (VUV) and soft x-ray radiation of various energies using facilities at the National Synchrotron Light Source, Brookhaven National Laboratory. Samples were exposed to synchrotron radiation of narrow energy bands centered on energies between 69 eV and 1900 eV. Samples were analyzed for ultimate tensile strength and elongation. Results will be compared to those of aluminized Teflon® FEP retrieved from HST after 3.6 years and 6.8 years on orbit and will be referenced to estimated HST mission doses of VUV and soft x-ray radiation. | | | |
| 14. SUBJECT TERMS Synchrotron Vacuum Ultraviolet; Soft X-ray radiation; Teflon® degradation | | | 15. NUMBER OF PAGES 15 |
| | | | 16. PRICE CODE A03 |
| 17. SECURITY CLASSIFICATION OF REPORT Unclassified | 18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified | 19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified | 20. LIMITATION OF ABSTRACT |