

8-1 10.00

NATIONAL BUREAU OF STANDARDS REPORT

7589

THE APPLICATION OF X-RAY PROJECTION MICROSCOPY TO ROOFING ASPHALT SYSTEMS

by

Sidney H. Greenfeld



**U. S. DEPARTMENT OF COMMERCE
NATIONAL BUREAU OF STANDARDS**

THE NATIONAL BUREAU OF STANDARDS

Functions and Activities

The functions of the National Bureau of Standards are set forth in the Act of Congress, March 3, 1901, as amended by Congress in Public Law 619, 1950. These include the development and maintenance of the national standards of measurement and the provision of means and methods for making measurements consistent with these standards; the determination of physical constants and properties of materials; the development of methods and instruments for testing materials, devices, and structures; advisory services to government agencies on scientific and technical problems; invention and development of devices to serve special needs of the Government; and the development of standard practices, codes, and specifications. The work includes basic and applied research, development, engineering, instrumentation, testing, evaluation, calibration services, and various consultation and information services. Research projects are also performed for other government agencies when the work relates to and supplements the basic program of the Bureau or when the Bureau's unique competence is required. The scope of activities is suggested by the listing of divisions and sections on the inside of the back cover.

Publications

The results of the Bureau's research are published either in the Bureau's own series of publications or in the journals of professional and scientific societies. The Bureau itself publishes three periodicals available from the Government Printing Office: The Journal of Research, published in four separate sections, presents complete scientific and technical papers; the Technical News Bulletin presents summary and preliminary reports on work in progress; and Basic Radio Propagation Predictions provides data for determining the best frequencies to use for radio communications throughout the world. There are also five series of non-periodical publications: Monographs, Applied Mathematics Series, Handbooks, Miscellaneous Publications, and Technical Notes.

A complete listing of the Bureau's publications can be found in National Bureau of Standards Circular 460, Publications of the National Bureau of Standards, 1901 to June 1947 (\$1.25), and the Supplement to National Bureau of Standards Circular 460, July 1947 to June 1957 (\$1.50), and Miscellaneous Publication 240, July 1957 to June 1960 (Includes Titles of Papers Published in Outside Journals 1950 to 1959) (\$2.25); available from the Superintendent of Documents, Government Printing Office, Washington 25, D. C.

NATIONAL BUREAU OF STANDARDS REPORT

NBS PROJECT

NBS REPORT

1004-12-10141

August 10, 1962

7589

THE APPLICATION OF X-RAY PROJECTION MICROSCOPY TO ROOFING ASPHALT SYSTEMS

by

Sidney H. Greenfeld

Research Associate
Asphalt Roofing Industry Bureau

Organic Building Materials Section
Building Research Division

Jointly Sponsored by

Asphalt Roofing Industry Bureau

and

National Bureau of Standards

IMPORTANT NOTICE

NATIONAL BUREAU OF STANDARDS
Intended for use within the Government
to additional evaluation and revision
listing of this Report, either in
the Office of the Director, National
Bureau of Standards, or by the Government agency
to reproduce additional copies

Approved for public release by the
Director of the National Institute of
Standards and Technology (NIST)
on October 9, 2015.

gress accounting documents
ally published it is subjected
production, or open-literature
n is obtained in writing from
ich permission is not needed,
pared if that agency wishes



U. S. DEPARTMENT OF COMMERCE
NATIONAL BUREAU OF STANDARDS

THE APPLICATION OF X-RAY PROJECTION MICROSCOPY TO ROOFING ASPHALT SYSTEMS

1. INTRODUCTION

The ability to see within an asphalt or an asphalt product has always been hampered by the general opacity of the materials involved. The optical microscope has been used on very thin sections of asphalts, but its contributions have been limited primarily to surface configurations [1, 2]^{1/} and phase separations [3]. The electron microscope has been applied to asphalt problems, but it has been shown that the observations reported were largely of artifacts introduced by specimen preparation [4, 5, 6].

X-rays have been used on asphalts in a number of types of analyses. While normal radiology has produced little useful information because of the transparency of asphalts to the wavelengths of x-rays normally used, x-ray diffraction and x-ray scattering studies have produced some useful information [7, 8]. However, the patterns have been quite diffuse and the interpretations have been questioned.

In recent years a point-projection microscope has been developed, which can be used with soft x-rays to "see" the interior of asphalt specimens as thick as 50 mils. Preliminary results of the application of this technique to asphalt problems will be covered in this report. This study was made in close collaboration with Dr. S. B. Newman, who is in charge of the microscopy laboratory at the National Bureau of Standards.

2. APPARATUS

The point-projection x-ray microscope, shown schematically in Figure 1, was of the Cosslett and Nixon type [9], manufactured by Micro X-Ray Laboratories, Ltd., of Surrey, London, England. It consisted of a Wehnelt type electron gun with grid bias, electromagnetic condenser and objective lenses and a series of interchangeable targets. The spot size on the targets was about one micron; however, slight scattering of the x-rays resulted in an effective x-ray source slightly larger than this. All x-ray photographs were made with an aluminum target, yielding x-rays of 8.34 Å wavelength.

The electron gun was evacuated by mechanical and oil diffusion pumps to a pressure of 10^{-4} mm. of mercury. A complete description of this apparatus may be found in reference [9].

^{1/} Numbers in brackets refer to literature references at the end of this report.

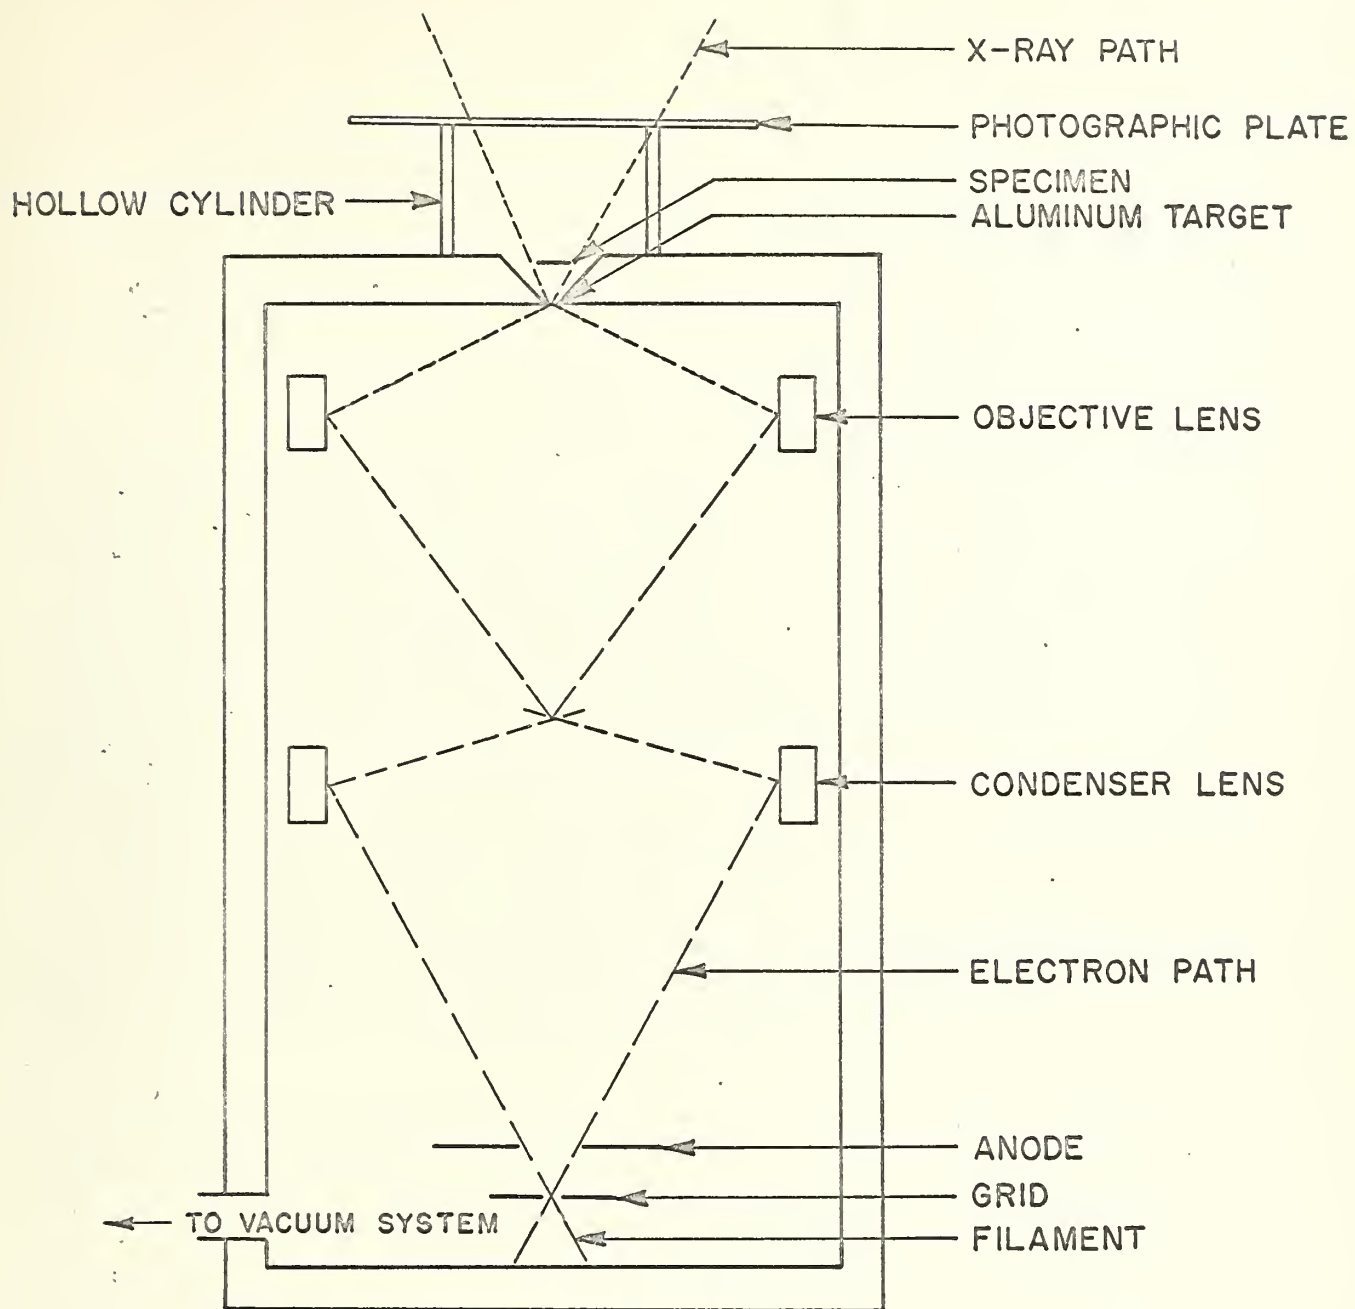


FIGURE 1. SCHEMATIC OF X-RAY PROJECTION MICROSCOPE

3. PROCEDURE

At the beginning of each day the electron gun of the x-ray projection microscope must be evacuated and focused. The focusing is accomplished by placing a small piece of screen grid on the aluminum target and projecting its image on to a phosphor-coated sheet of lead glass. Adjustments are made by changing the magnetic fields in the lenses. When the microscope is ready the specimen is placed in position, a hollow cylinder of appropriate height to produce the desired magnification placed concentric with the specimen, a photographic plate placed on the cylinder and the exposure made. The plate is developed and viewed immediately. The gun was operated at 12.5 KV and 30 μ A for all of the photographs in this report.

As seen in Figure 1, the focusing is entirely within the gun, all points in the x-ray path are always in focus when the gun is properly focused. Thus, the magnification is controlled by regulating the relative distances of the specimen and the plate from the x-ray source, the target of the electron gun. All points in the specimen are in focus, but points in different planes within the specimen are magnified to different degrees.

The photographs in this report are at various magnifications. No effort was made to position the specimen or control its thickness precisely. Thus, the results must be interpreted on a qualitative basis only.

4. RESULTS AND DISCUSSION

Figure 2 - Unexposed Asphalt

This photomicrograph is typical of many taken of commercial samples of coating-grade asphalt. There are indications of materials of different densities dispersed in the asphalt. These range from air bubbles, the white, round area, to various types of debris. Some of this litter may be introduced during specimen preparation, for dust and lint tend to collect on the freshly cut asphalt surfaces, but the bulk of the foreign material is in the asphalt.



FIGURE 2. A COMMERCIAL COATING-GRADE ASPHALT

123456789

Figure 3 - Cross Section of Asphalt Film Weathered for 88 Months on the Roof of the Industrial Building - Magnification 120X

In all weathered films, a more-or-less stratified appearance has been found. There is a surface layer, which is obviously less dense than the rest of the coating. This layer is the "velvet" film seen on asphalts, which consists of partially oxidized organic material. The more-completely oxidized material has been leached from this layer, leaving a film of low density. Below this surface layer is a denser layer; this second layer possibly consists of an accumulation of non-diffusing materials (primarily asphaltenes) which have partially collapsed on themselves because of a deficiency of oils. The third layer is again less dense, possibly because the oils have diffused out, leaving an incompletely filled, but not collapsed, asphaltene structure. Finally, the bulk of the asphalt remains below.

This particular film is 19.5 mils thick; it had lost 6.5 mils in thickness and 24% of its initial weight.

Figure 4 - Cross-Section of Asphalt with 50% Dolomite Weathered 75 Months on the Roof of the Industrial Building - Magnification 240X

Several strata of varying density are quite apparent. The surface layer seems to be almost entirely mineral matter with little asphalt to hold it together. The specimen is unsupported; hence, the apparently detached mineral matter is actually held in position by some material transparent to x-rays of this wavelength.

Below the low-density surface layer is a high-density layer. This area seems to be unusually rich in material between the dolomite particles.

The lowest layer, almost 50% of the film, is of an intermediate density.

A possible interpretation of this picture may be that the weathering at the surface has depleted the surface of asphalt binder through oxidation followed by solution of water-soluble end products. The second layer is of high density because the least dense material, the oils, have diffused to the surface and have left the more dense resins and asphaltenes behind. The rest of the film is changed to a lesser degree. It is more akin to the original coating.

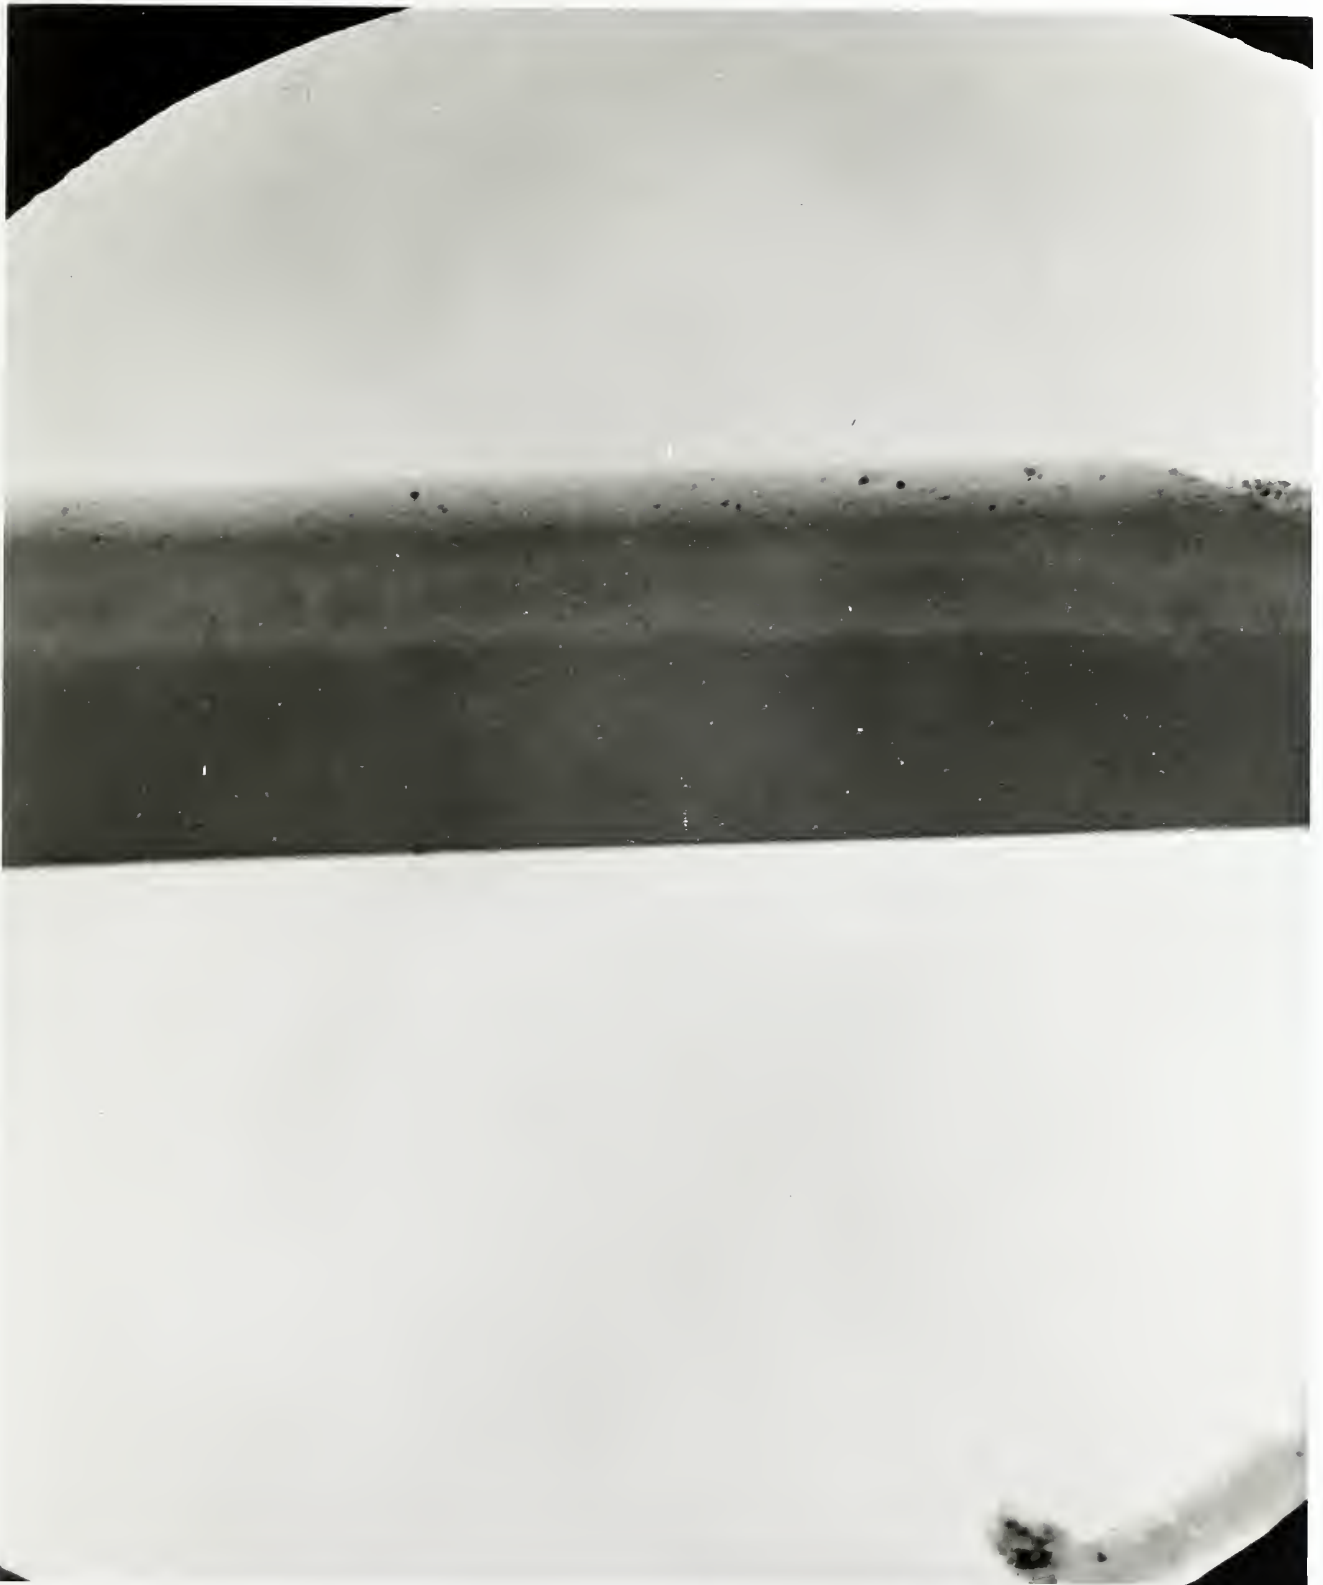


FIGURE 3. AN ASPHALT FILM WEATHERED 88 MONTHS OUT
OF DOORS - 120X

301242

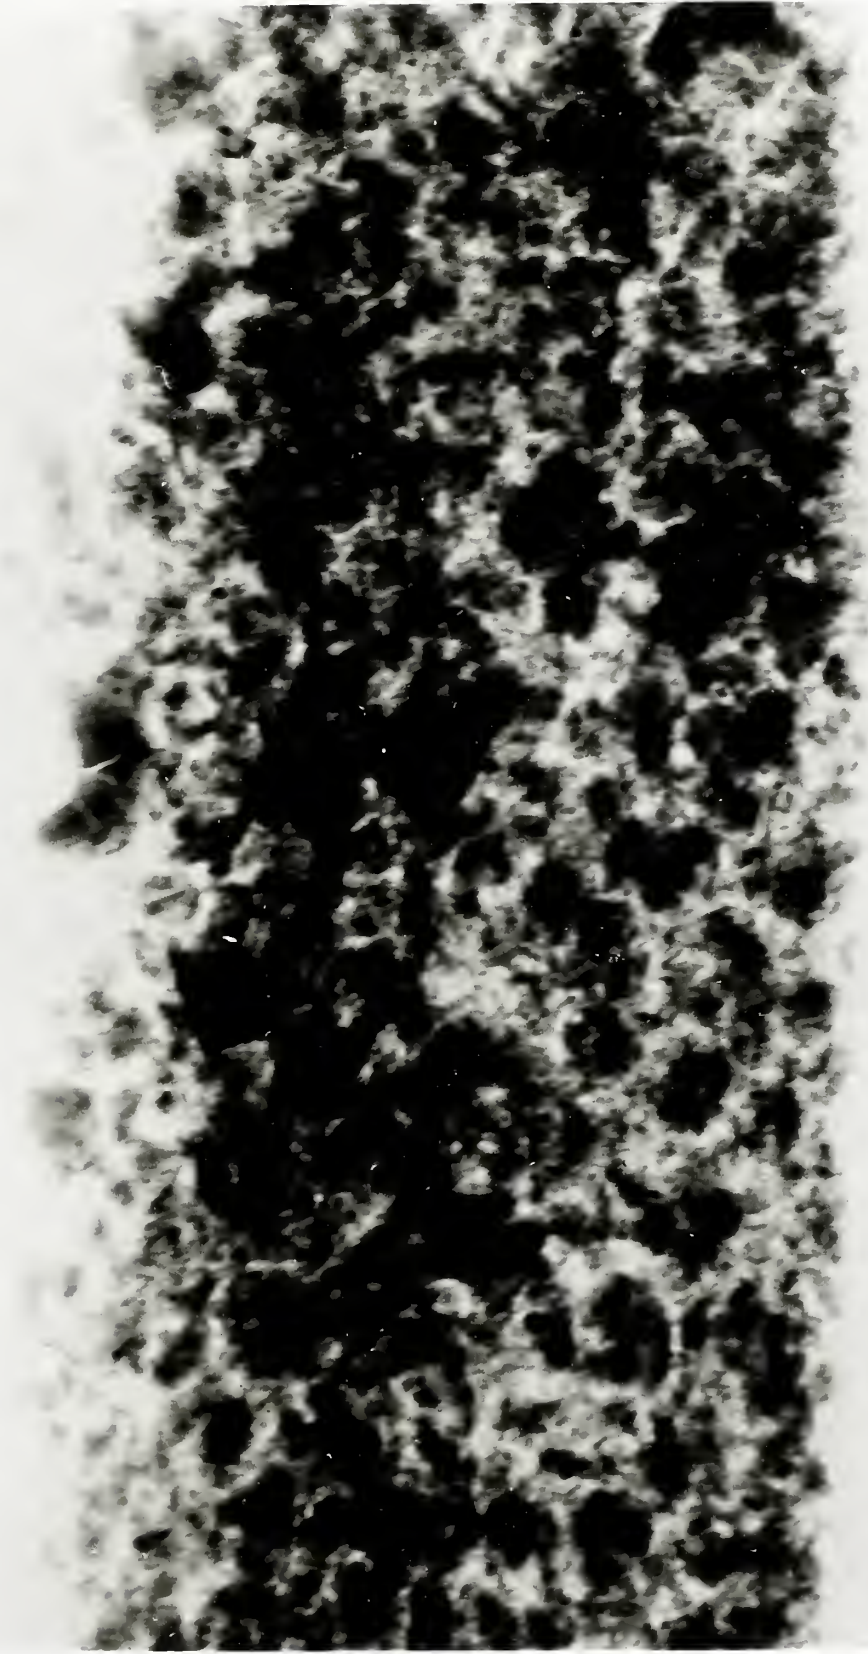


FIGURE 4. AN ASPHALT FILM CONTAINING 50% DOLOMITE,
WEATHERED 75 MONTHS OUT OF DOORS - 24OX

31/12/20

Figure 5 - Random Sample of 215-pound Uniform-Thickness Asphalt Shingle - Magnification 70X

This sample of a commercial asphalt strip shingle may not be typical, but it demonstrates vividly the value of the x-ray microscope for observing latent failures in roofing products. The mechanical embedment of the granules is quite evident. There is no contact (let alone adhesion) of coating and granules in large areas of their interface.

Some coating has been brought on to the exposed surface of the granule in the center of the photograph, possibly by rotation of the granule during embedment. A thin spot in the coating exists just to the right of this granule.

Regions in the saturated felt show significantly lower density than others. If these areas are less dense because of lower saturant, it would appear that the interfaces between coating and felt have become depleted in saturant. The saturant could have fluxed with the coating or could have been driven back into the felt. Small isolated areas in the body of the felt seem to be lacking saturant as well.

The variation in thickness of back-coating and back surfacing is quite apparent.

Figure 6 - Shingle That Has Clawed - Magnification 70X

This section taken from the center of a tab of a clawed, thick-butt shingle shows the condition existing when extreme clawing has occurred. The double overlay construction is apparent and still in good condition. A thin strata of saturated felt, just below the coating, also seems to be in good condition. (The low-saturation interface area seen in Figure 5 is not apparent here.) However, just below this layer is the bulk of the saturated felt, largely deteriorated. The back surfacing is full of holes and some of it has worked up into the felt. It appears that the original shingle may have had a light back-coating.

Figure 7 - Peace River Glass Mat with Kansas Asphalt. Thickness - 42 mils. Exposed 600 hrs to 51-9C cycle. Magnification - 110X

The glass mat occupies the lower two-thirds of the total thickness of this film. The mat is quite open and the individual fibers are surrounded by asphalt. The asphalt surface shows some signs of weathering; it is less dense than the interior and seems to have a fuzzy texture. The mottled appearance of the asphalt is difficult to explain, but is not untypical. Many asphalt specimens, before exposure, appear like this one.

OFFICE FILE COPY

DIVISION _____ SECTION _____

PRINT FROM BUREAU OF STANDARDS

PHOTOGRAPHIC LABORATORY

ORDER DUPLICATE COPIES

BY NUMBER

309244



FIGURE 5. A COMMERCIAL, UNEXPOSED UNIFORM-THICKNESS
ASPHALT SHINGLE - 70X

30924 4

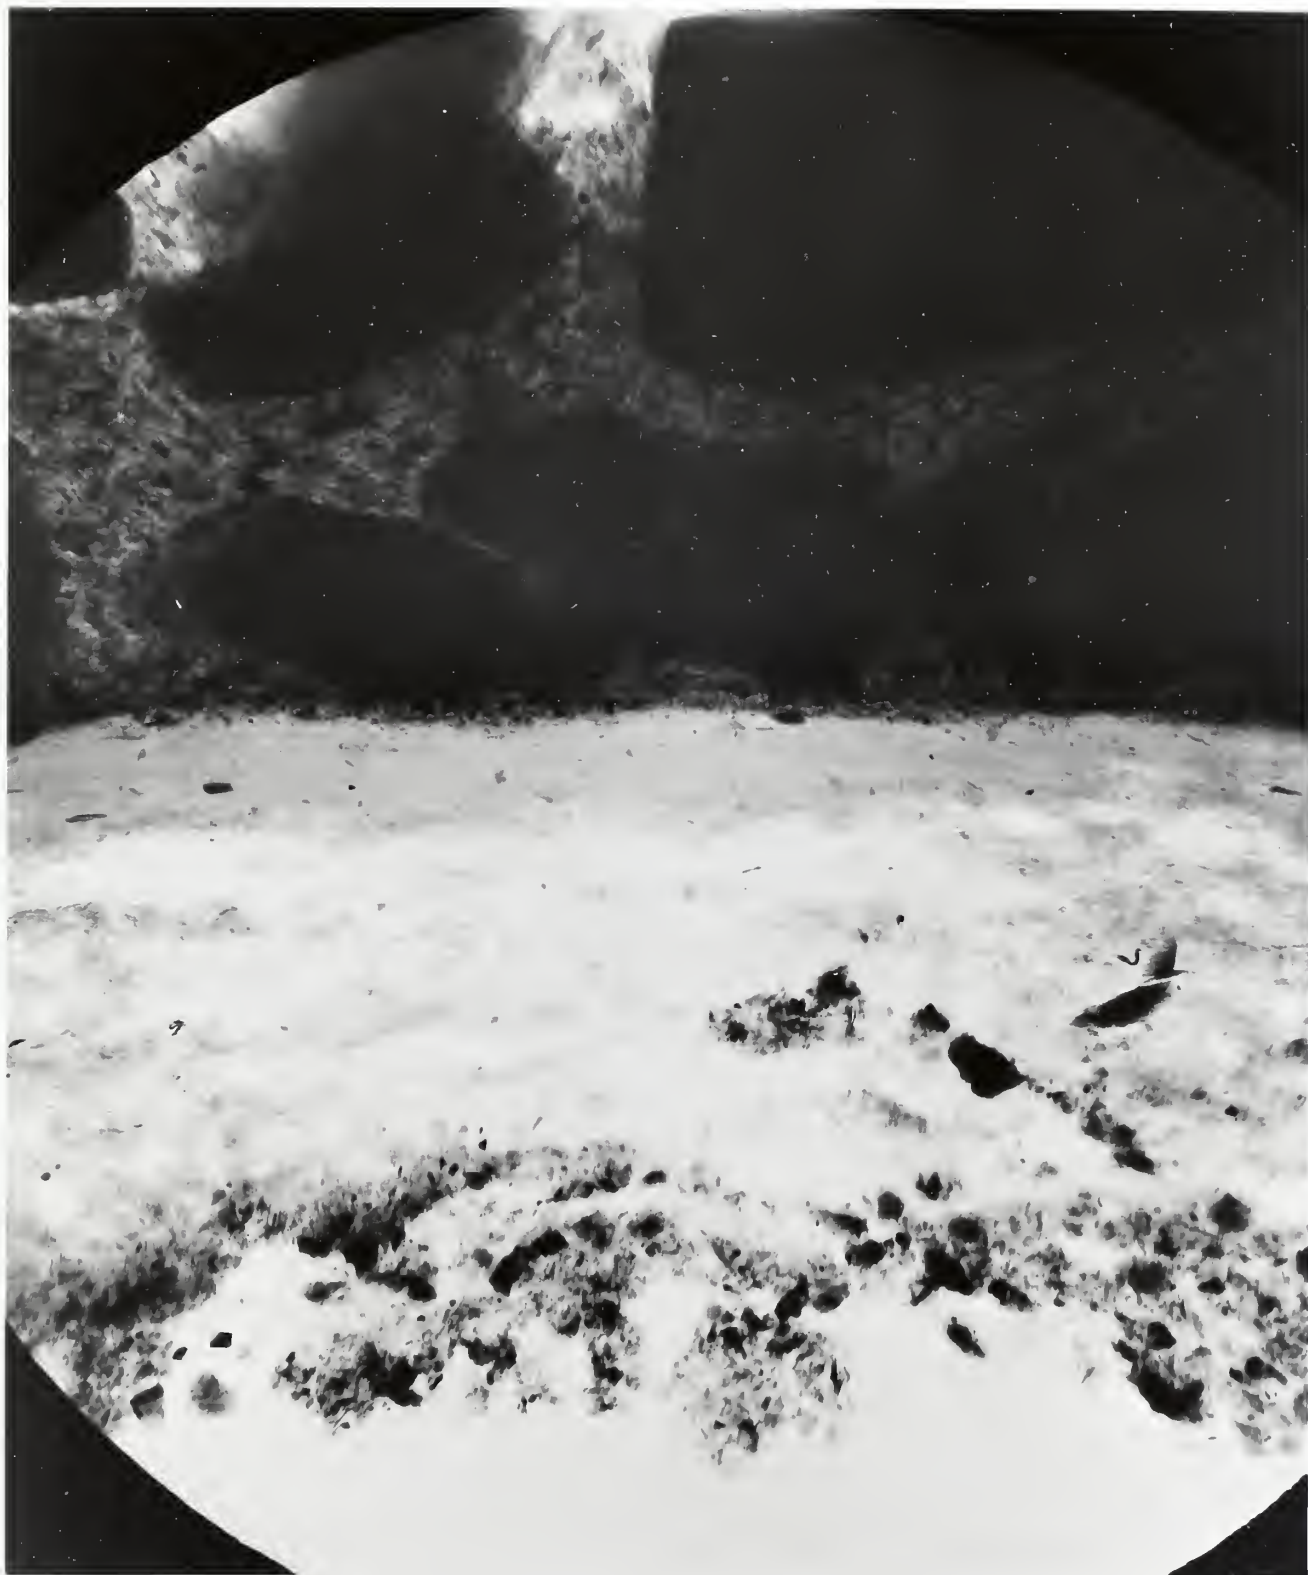


FIGURE 6. A THICK BUTT SHINGLE THAT HAS DEVELOPED SEVERE CLAWING - 70X

8/10/10

OFFICE FILE COPY

DIVISION _____ SECTION _____
PRINT FROM BUREAU OF STANDARDS
PHOTOGRAPHIC LABORATORY
ORDER DUPLICATE COPIES
BY NUMBER

309246



FIGURE 7. AN ASPHALT FILM CONTAINING A PEACE RIVER
GLASS MAT AFTER 600 HOURS IN THE WEATHER-
OMETER - 110X

8-12-0

Figure 8 - Johns-Manville Glass Mat with Kansas Asphalt. Thickness - 30 mils.
Exposed 600 hrs to 51-9C cycle. Magnification 120 X.

The stratification occurring during weathering is quite apparent in this picture. The glass mat, which is of the same weight as the one in Figure 7, tends to be concentrated in the lowest part of the asphalt film. Some debris is clearly seen in the asphalt.

Figure 9 - Monoform Roofing - Clay Emulsion Reinforced with Chopped Glass Fibers on a Coated Sheet - Magnification Not Determined.

The mineral matter in the coating on the saturated felt is visible at the bottom of the picture. The random and irregular distribution of the glass fibers, as individuals and in clusters, throughout the clay emulsion residue is quite apparent. Clay particles are also quite apparent.

5. SUMMARY

The application of the x-ray point projection microscope to asphalt problems has been demonstrated through a number of photographs. The use of soft x-rays permits observance of variations in the asphalts as well as differences in absorbences among asphalts and additives.

6. REFERENCES

- [1] Schwarz, F., Asphalt und Strassenbau, Supplement No. 5 of Petroleum Zeitschrift 28 (1932).
- [2] Traxler, R. N. and Coombs, C. E., Proc. ASTM 37, II, 549 (1937).
- [3] Benson, J. R., Proc. AAPT 9, 63, 102-132 (1937).
- [4] Preckshot, G. W., DeLisle, N. G., Cottrell, C. E., and Katz, D. L., Trans. Inst. Min. & Met. Engrs 151, 188 (1943).
- [5] Katz, D. L. and Beu, K. E., Ind. Eng. Chem. 37, 195 (1945).
- [6] Ellis, S. H., Pet. Refiner 27, 410 (1948).
- [7] Williford, C. L., Bull. A & M College of Texas, 73, 7 (1943).
- [8] Yen, T. F., Erdman, J. G., and Pollack, S. S., Anal. Chem. 33, 1587 (1961).
- [9] Cosslett, V. E. and Nixon, W. C., "X-Ray Microscopy", Cambridge University Press, London (1960).

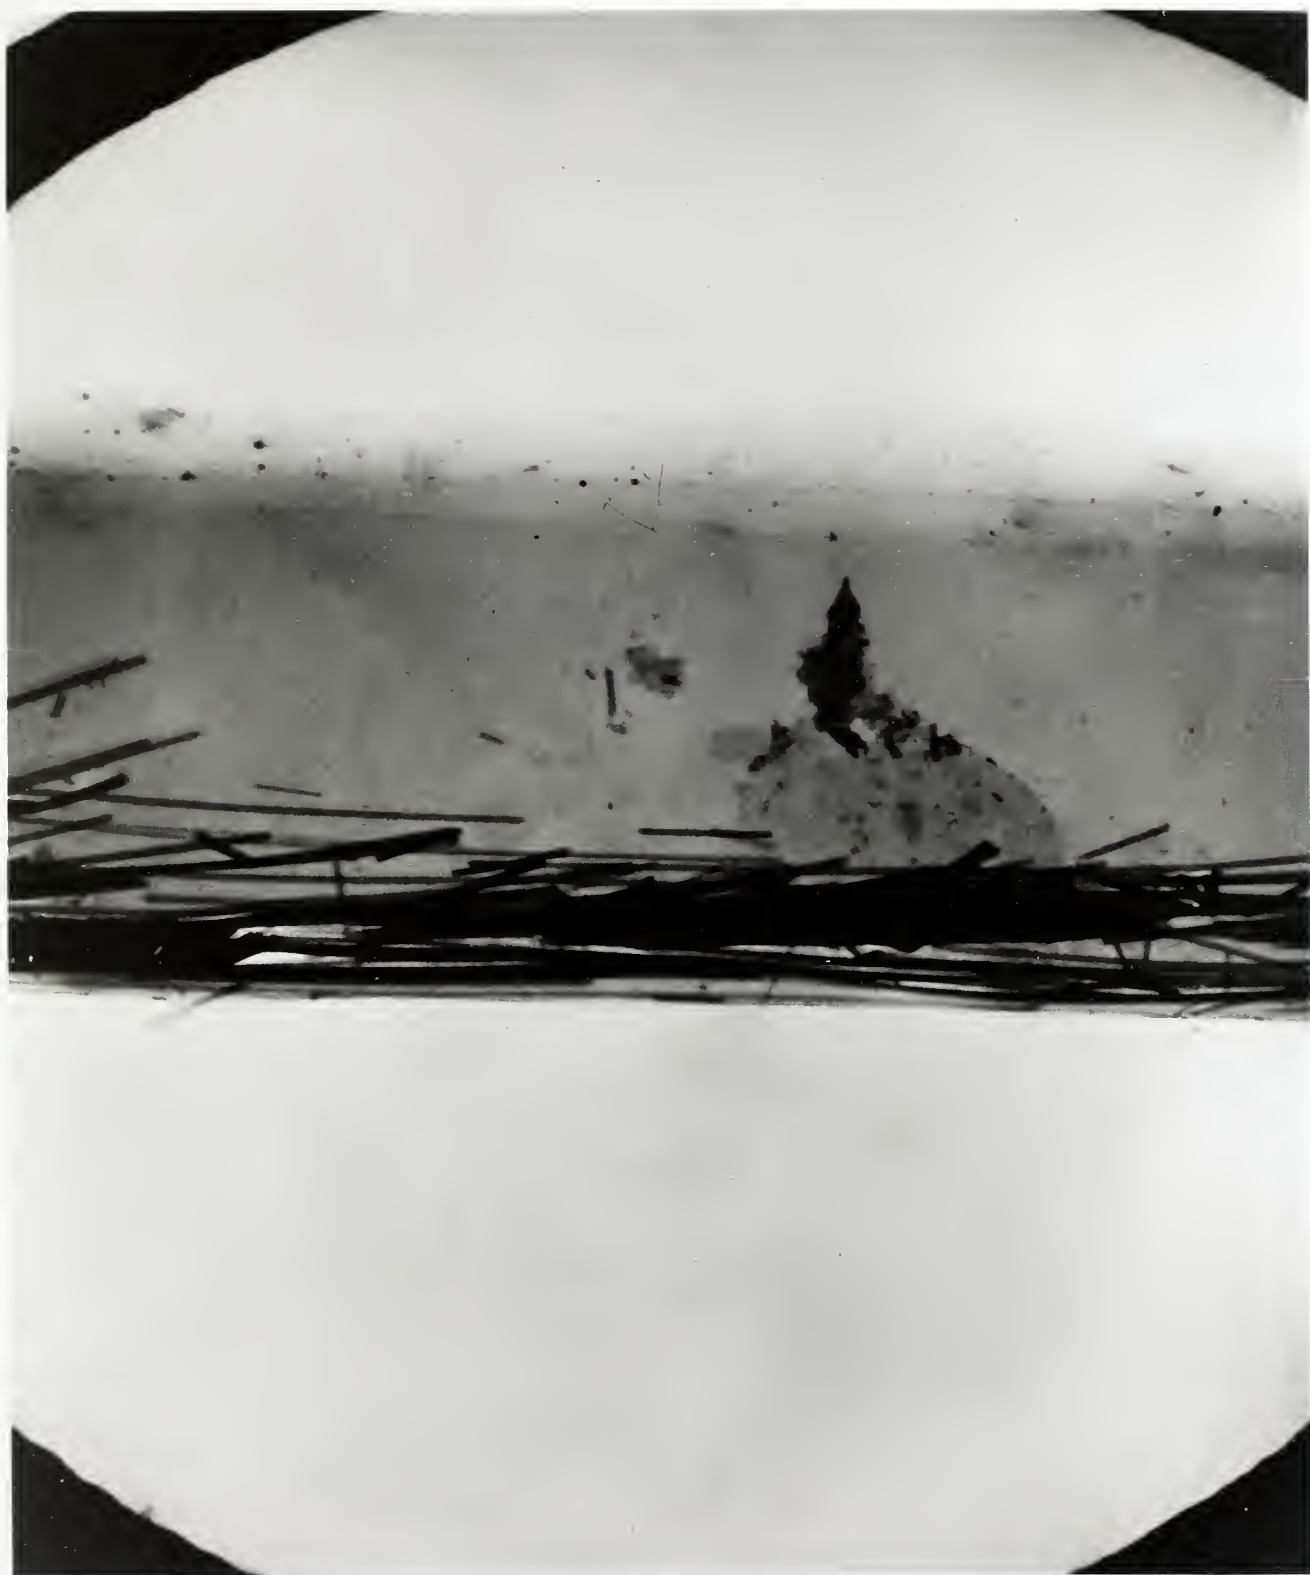


FIGURE 8. AN ASPHALT FILM CONTAINING JOHNS-MANVILLE
GLASS MAT AFTER 600 HOURS IN THE WEATHER-
OMETER - 120X

807347



FIGURE 9. GLASS FIBER REINFORCED CLAY EMULSION ON A
COATED BASE SHEET

809248

U. S. DEPARTMENT OF COMMERCE

Luther H. Hodges, *Secretary*

NATIONAL BUREAU OF STANDARDS

A. V. Astin, *Director*



THE NATIONAL BUREAU OF STANDARDS

The scope of activities of the National Bureau of Standards at its major laboratories in Washington, D.C., and Boulder, Colorado, is suggested in the following listing of the divisions and sections engaged in technical work. In general, each section carries out specialized research, development, and engineering in the field indicated by its title. A brief description of the activities, and of the resultant publications, appears on the inside of the front cover.

WASHINGTON, D. C.

Electricity. Resistance and Reactance. Electrochemistry. Electrical Instruments. Magnetic Measurements. Dielectrics. High Voltage.

Metrology. Photometry and Colorimetry. Refractometry. Photographic Research. Length. Engineering Metrology. Mass and Scale. Volumetry and Densimetry.

Heat. Temperature Physics. Heat Measurements. Cryogenic Physics. Equation of State. Statistical Physics.

Radiation Physics. X-ray. Radioactivity. Radiation Theory. High Energy Radiation. Radiological Equipment. Nucleonic Instrumentation. Neutron Physics.

Analytical and Inorganic Chemistry. Pure Substances. Spectrochemistry. Solution Chemistry. Standard Reference Materials. Applied Analytical Research. Crystal Chemistry.

Mechanics. Sound. Pressure and Vacuum. Fluid Mechanics. Engineering Mechanics. Rheology. Combustion Controls.

Polymers. Macromolecules: Synthesis and Structure. Polymer Chemistry. Polymer Physics. Polymer Characterization. Polymer Evaluation and Testing. Applied Polymer Standards and Research. Dental Research.

Metallurgy. Engineering Metallurgy. Microscopy and Diffraction. Metal Reactions. Metal Physics. Electrolysis and Metal Deposition.

Inorganic Solids. Engineering Ceramics. Glass. Solid State Chemistry. Crystal Growth. Physical Properties. Crystallography.

Building Research. Structural Engineering. Fire Research. Mechanical Systems. Organic Building Materials. Codes and Safety Standards. Heat Transfer. Inorganic Building Materials. Metallic Building Materials.

Applied Mathematics. Numerical Analysis. Computation. Statistical Engineering. Mathematical Physics. Operations Research.

Data Processing Systems. Components and Techniques. Computer Technology. Measurements Automation. Engineering Applications. Systems Analysis.

Atomic Physics. Spectroscopy. Infrared Spectroscopy. Solid State Physics. Electron Physics. Atomic Physics.

Instrumentation. Engineering Electronics. Electron Devices. Electronic Instrumentation. Mechanical Instruments. Basic Instrumentation.

Physical Chemistry. Thermochemistry. Surface Chemistry. Organic Chemistry. Molecular Spectroscopy. Molecular Kinetics. Mass Spectrometry.

Office of Weights and Measures.

BOULDER, COLO.

Cryogenic Engineering Laboratory. Cryogenic Equipment. Cryogenic Processes. Properties of Materials. Cryogenic Technical Services.

CENTRAL RADIO PROPAGATION LABORATORY

Ionosphere Research and Propagation. Low Frequency and Very Low Frequency Research. Ionosphere Research. Prediction Services. Sun-Earth Relationships. Field Engineering. Radio Warning Services. Vertical Soundings Research.

Radio Propagation Engineering. Data Reduction Instrumentation. Radio Noise. Tropospheric Measurements. Tropospheric Analysis. Propagation-Terrain Effects. Radio-Meteorology. Lower Atmosphere Physics.

Radio Systems. Applied Electromagnetic Theory. High Frequency and Very High Frequency Research. Modulation Research. Antenna Research. Navigation Systems.

Upper Atmosphere and Space Physics. Upper Atmosphere and Plasma Physics. Ionosphere and Exosphere Scatter. Airglow and Aurora. Ionospheric Radio Astronomy.

RADIO STANDARDS LABORATORY

Radio Physics. Radio Broadcast Service. Radio and Microwave Materials. Atomic Frequency and Time-Interval Standards. Millimeter-Wave Research.

Circuit Standards. High Frequency Electrical Standards. Microwave Circuit Standards. Electronic Calibration Center.

